



New data and insights on the secondary glass workshop of Comacchio (Italy): MgO contents, steatite crucibles and alternatives to recycling

Elisabetta Gliozzo¹ · Eleonora Braschi² · Margherita Ferri³

Received: 2 April 2024 / Accepted: 15 June 2024
© The Author(s) 2024

Abstract

This study introduces a collection of 33 glass samples, encompassing production indicators (blocks, fluidity tests, drops, cuts and wastes) and finished products (mainly goblets and probably a lamp) dating to the second half of the 7th century, except for a single more recent specimen (12th-14th). Additionally, a fragment was taken from a crucible bearing a thin layer of glass inside it. This new collection complements the investigation of glass materials from the Comacchio workshop previously analysed by Bertini et al. (2020).

Measurements were performed using scanning electron microscopy, electron microprobe, laser ablation inductively coupled plasma mass spectroscopy on all samples and Sr–Nd isotopic analyses on 5 blocks.

The results showed how the entire collection can be classified as natron-based silica-soda-lime glass and that the high MgO contents frequently observed are due to contamination with the steatite crucible. Contextually, the hypothesis of using plant ash-based glass mixed with natron-based glass formulated in the previous literature seems to have run out, along with the use of plant ash-based glass itself, further weakened by the very low representativeness of this latter type of glass on the site. The technological investigation further elucidated that recycling may not singularly account for the Comacchio glass technology. Discernible correlations may suggest the introduction of different types of metals, indicating a specialised control over the production process. Notably, the preference for green–blue glass emerges as a distinctive hallmark, underscoring the deliberate pursuit of a specific aesthetic taste.

Lastly, the provenance analysis showed that over three-quarters of production was based on semi-finished products from Egypt, while only the remaining quarter came from the Levantine coast.

Keywords Glass technology · Secondary production · Steatite crucibles · Metals and glass colouring

Introduction

Before the early 2000s, there were very few written sources on Comacchio and limited archaeological data. The archaeological area of Comacchio was thoroughly investigated from 2006 to 2009 under the direction of Prof. Sauro Gelichi. In 2021, the comprehensive volume summarising this archaeological research was published (Gelichi et al. 2021), including Ferri's works on glass (2021a) and the glass workshop (2021b).

Comacchio is situated on the Adriatic coast, north of Ravenna, at the mouth of the Po. It is from this area (44°41'45.3"N 12°10'52.5"E). The town of Comacchio has several distinctive features, mainly ecological. Before its establishment, the area was characterised by scattered settlements whose main economic activities included fish farming, salt production and brick manufacturing. Some of

¹ Department of History, Archaeology, Geography, Fine and Performing Arts, University of Florence, Via San Gallo 10, Florence, Italy

² Institute of Geosciences and Georessources, CNR, Via La Pira 4, 50121 Florence, Italy

³ Department of Humanities, Ca' Foscari University Venezia, Malcantone-Marcorà Dorsoduro 3484/D, 30123 Venice, Italy

these settlements evolved into religious centres in the sixth century. The historic centre's current boundaries align with its original layout, comprising a series of small islands in brackish lagoons. In the eastern part of the settlement, which is less explored archaeologically, there was likely a monastery. To the west, a port area with docks and wharves has been identified in the Villaggio San Francesco area. In the central part of the settlement, corresponding to the present Piazza XX Settembre, excavations have uncovered evidence of the bishop's residence, preceded by an artisan workshop.


In the artisanal area, dating to the second half of the 7th century, various productive activities occurred (Fig. 1). The best-preserved remains belong to a glass kiln, a third of which has been excavated, and a forge of the metal workshop. Bone working probably took place in an adjacent, unexcavated room since the remains of carved bones

have also been found in the area (Garavello 2021 on animal bones).

The glass kiln had a semicircular shape, ca. 2.4 m (south side) by ca. 1.2 m, and the workshop was in use long enough to have undergone some renovations. It was built in an area previously occupied by residential buildings. Based on the traces left on the ground surface, two different working places can be described quite clearly to the northeast, while the access to the combustion chamber and the fuel loading area were located in the area to the northwest (not excavated).

To the east of the kiln, there must have been a passageway connecting the various workplaces to each other and with the other workshops in the immediate vicinity of the kiln itself, as no further structures or holes have been found. In this earlier phase, the room to the east was

Fig. 1 A-B) Location of the archaeological site of Comacchio. **C)** The glass kiln during the excavation (credits: Laboratorio di Archeologia Medievale Ca' Foscari)

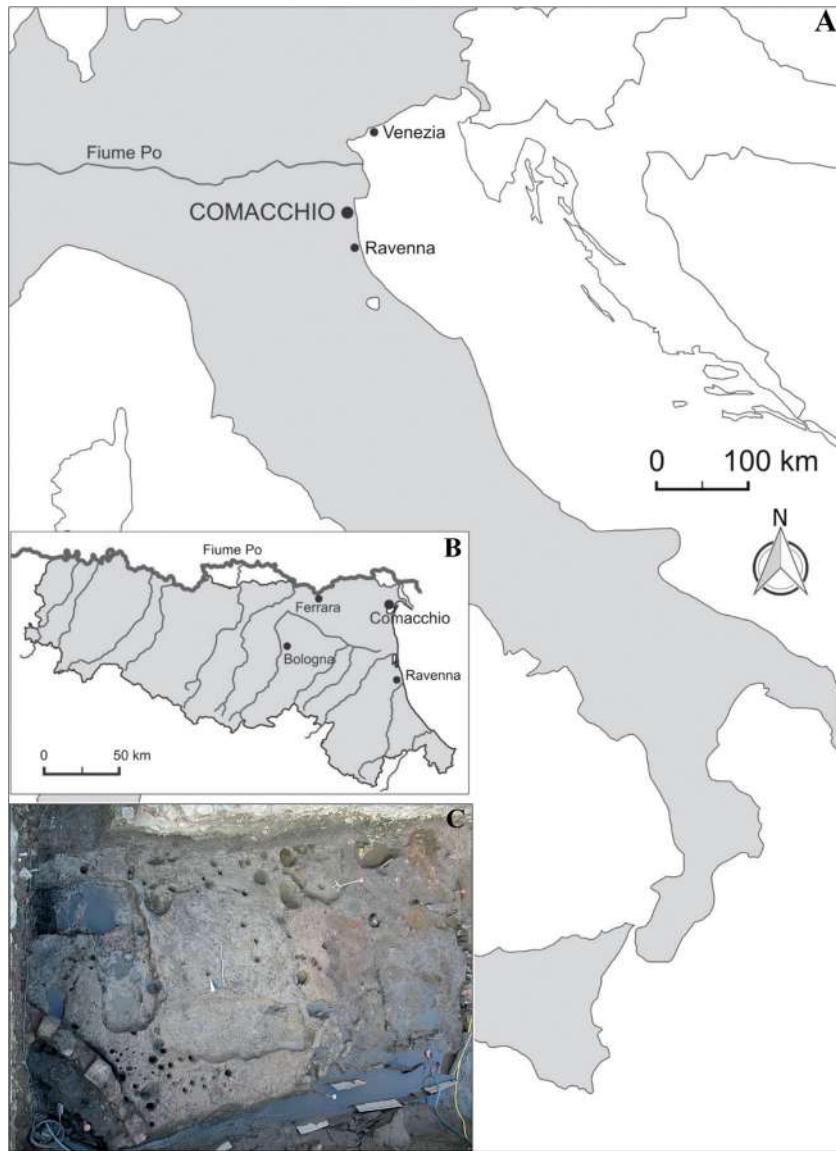

divided by a wooden partition, behind which was a quadrangular structure that did not appear to be related to the kiln or the glassmaking process.

In a short space of time, the work area was reorganised. The wooden partition was demolished and the eastern part of the workshop was converted into a metalworking area. In this new building reconfiguration, the metal and glass workshops were thus arranged in the same large room. The passageway to the east of the kiln was maintained and a free space of about 1 m in width remained between the glassworking area and the forge's service structures.

The production indicators testify that, later in time, the blowing of glass, the production of iron tools (especially nails but also tools for ironworking) and lead objects (weights for fishing nets) took place at the same time and in the same area (Rapone 2021). Some finds also indicate that copper (bronze) alloys were worked in the same area. The evidence that testifies to the polyvalence of the Comacchio workshop is numerous and all converge to reconstruct an activity aimed at the production of both everyday objects (goblets, nails, net weights) and sophisticated, technically complex objects such as double-layered cameos or bronze letters for epitaphs. For example, it is possible to cite the discovery of a Cu-Sn-Pb mould for cameos (Gagetti 2021; Galli and Bonizzoni 2021), a stone mould for casting the letter N (found in a phase dating from the 10th century but stylistically compatible with early mediaeval production; Mitchell 2021), and a small crucible, made of refractory ceramic, deemed for precious metals works but bearing remains of coloured glass (Ferri 2021a, p. 408).

Before the end of the 7th century, the entire room was redesigned. The glass kiln must have already been decommissioned since no waste was found during this phase. Some of the structures remained, probably for a short period of only a few years. The presence of a blacksmith strongly marked this phase. The main forge was moved to the east, closer to the kiln, thus occupying part of the space that was previously reserved for the movement of the glassmakers.

At the end of the 7th century and the beginning of the 8th century, the entire area was affected by extensive demolition and levelling work, which marked the end of all the artisanal activities that had previously been established in the area. The remains of the working structures were flattened to make way for a burial ground.

In the late 7th and early 8th centuries, Comacchio functioned primarily as a specialised trade nexus rather than a primarily land-based economy. It played a vital role in facilitating the flow of Mediterranean goods to inland regions. The significance of Comacchio in the history of the early medieval Mediterranean underscores the importance of characterising the glass artifacts found here and understanding the production technology employed.

A comprehensive examination of 89 samples found in the 7th to 11th c. phases of the Comacchio workshop was provided by Bertini et al. (2020). They divided their glass collection into plant ash glass ($n=3$) and natron-based glass ($n=86$), further grouped as Levantine A *Apollonia*-type glass ($n=12$), Levantine B *Jalame*-type glass ($n=5$), HIMT glass ($n=2$), Foy 2 ($n=4$ samples) and a mixed composition named "intermediate", "similar to that of the Foy-2 compositional group" ($n=63$). Further groups, such as the Foy 2 high-Fe variant, were intentionally omitted by the authors. Focused on recycling, the authors recognised crucible contamination by higher Al_2O_3 and Fe contents, contaminants from the fuel ash based on the increase of K_2O or MgO levels and limited natron-plant ash mixing based on MgO , K_2O and P_2O_5 amounts. The overall reconstruction proposed by the authors is summarised in the following sentence: "*all major natron glass compositions were involved in heavy recycling practices (...), minus the intermediate group, for which we suggest is the result of mixing reserves of heavily recycled glass with unrecycled glass (...)*". The authors also extensively discussed plant ash-based glass as one of the components used for local production, mixed with natron-based glass.

This study intends to expand the collection of previously analysed materials by adding 34 samples of production indicators, vessels and a crucible. The research objectives fit into the frame of the Food & S.T.O.N.E.S. project aimed at studying the circulation of different types of early medieval goods, especially glass, in the Adriatic Sea (Gliozzo et al. 2023a-c). The archaeometric investigation seeks to obtain additional data on the provenance of the semi-finished products and the production technique of Comacchio glass-workers. In particular, it seems necessary to re-discuss the presence and use of plant ash-based glass already from the 7th century (Bertini et al. 2020) and to frame Comacchio's production in the wider context of early mediaeval Adriatic trade. An expansion of the database and new considerations on the use of steatite crucibles may indeed provide new food for thought both in terms of glass production technology and the type of Adriatic imports during the late antiquity and early mediaeval ages.

Materials

The samples were selected based on typological and stratigraphic criteria to obtain a representative collection of raw materials, objects -which are both products (*i.e.* goblets: Ferri 2021a) and objects intended for recycling- and glass-working wastes (Table 1). As for the latter, some of them were found in the stratigraphic phase subsequent to the period of activity of the kiln. However, these findings were contemporary with the production of glass but were subsequently disturbed and brought to the surface due to

Table 1 Basic information on investigated samples: the inventory no. (inv.); the context and the period of discovery; the shape and colour abbreviated as aB (aqua blue), laB (light aqua blue), dB (dark blue), C (colourless), IG (light green), Y (yellow). Reference to the shape as in Stiaffini (1985). All finds, except for CO530, were attributed to the glass workshop, which dates from the second half of the seventh century, even if they were found in later stratigraphic units

Inv	Context	Period	Shape	Colour	Typology
Finished objects					
CO92	1842	7.1	Goblet	IG	A2
CO93	1842	7.1	Goblet (marvered)	IG	A2
CO94	1842	7.1	Goblet	IG	A2
CO95	1842	7.1	Goblet	IG	A2
CO96	1842	7.1	Goblet	IG	A2
CO325	1956	8.1	Goblet	IG	A2
CO366	2172	8.3	Goblet	laB	A2
CO368	2172	8.3	Goblet	laB	A2
CO530	2418	4.3	Lamp?	G (with red strips)	A2
CO88	1842	7.1	Wall (marvered)	C	A2
CO99	1842	7.1	Pad-base	Y	-
CO233 A	2019	8.3	Window	G	-
CO233 B	2019	8.3	Window	G	-
CO233 C	2019	8.3	Window	dB	-
CO25	1851 t. 60	7.1	Tessera	C	-
Production indicators					
CO24	1851 t. 60	7.1	Block	dB	-
CO58 A	1701 t 43	6	Block	aB	-
CO100 B	1842	7.1	Block	G	-
CO121 E	1185	6	Block	IG	-
CO122	1185	6	Block	B	-
CO184 B	1826 t. 56	7.1	Block	G	-
CO100 A	1842	7.1	Moil	IG (with red strips)	-
CO121 C	1185	6	Moil	G	-
CO121 D	1185	6	Moil	IG (greyish)	-
CO230	2019	8.3	Moil	G	-
CO184 A	1826 t. 56	7.1	Cutting	G (greyish)	-
CO58 B	1701 t 43	6	Dripping	IG	-
CO121 A	1185	6	Dripping	IG	-
CO121 B	1185	6	Dripping	IG	-
CO23(a)	1851 t. 60	7.1	Fluidity test or test droplet?	G	-
CO23(b)	1851 t. 60	7.1	=	aB	-
CO58 C	1701 t 43	6	Glass on crucible	G	-
CO365	2172	8.3	Waste	laB	-
CO184 C	1826 t. 56	7.1	Waste (deformed wall)	IG	-


the excavation of burial pits (9th-11th centuries) and the construction of the episcopal buildings (12th-14th centuries). The production indicators were undoubtedly part of the glassworks of the mid-7th century, thus earlier than the context in which they were found.

The total number of glass fragments found at Comacchio was about 2000 and the finished glass objects found were numerous (531 fragments attributable to 269 individual objects). The 34 samples selected for this study correspond to 33 objects that can be divided into working wastes (19), tableware (9 goblets and 1 beaker/cup resting on a pad-base), lighting vessel (1 lamp) and glass for

architectural use including 1 mosaic tessera and 3 fragments of window glass (Table 1; Figs. 2–3).

Among the most attested vessels are stemmed goblets, which correspond to the late antique type Isings no. 111 (Isings 1957, p. 139; on the Italian early mediaeval evolution of type, see Stiaffini 1985, type A2, pp. 669–670). In these goblets, the foot and the bowl are obtained by working a single blown *parison*, which is folded back on itself to form the foot, characterised by a tubular rim, with a bell-shaped profile or, as more common in Comacchio, with a flattened profile (CO94; CO95; CO96). The stem is short and hollow (CO366). The cup has a fire-polished rim (CO92;

Fig. 2 Glass typology. Representative shapes (credits: Laboratorio di Archeologia Medievale Ca' Foscari)

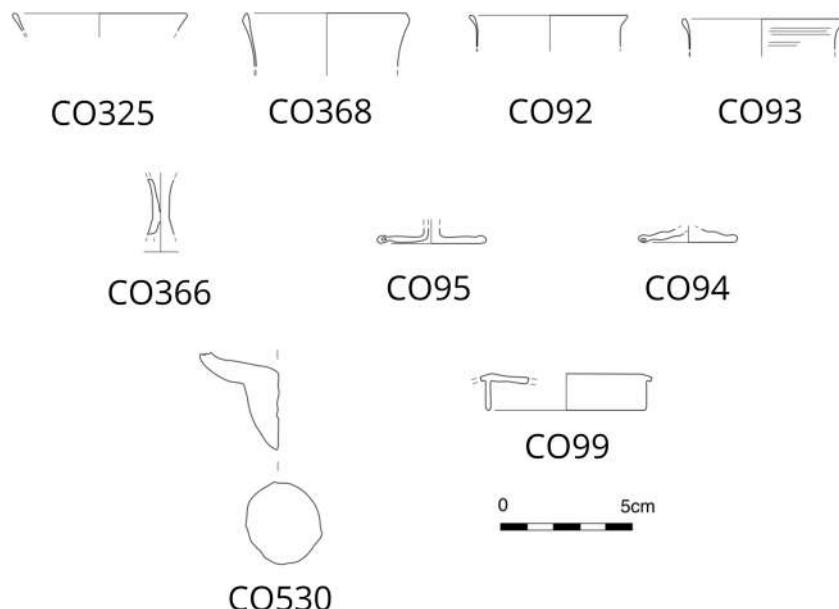

CO93; CO325; CO368). The body may have a deep bowl with an inverted conical or bell-shaped profile (with a flared upper rim and a wall that descends in a more or less/ slightly S-shaped curve). Some vessels have a white marvered in trail positioned 1–2 cm below the rim (CO88; CO93; Fig. 3). Small goblets with a flattened disc base between 3.6 and 4 cm in diameter were the main output of the late seventh-century workshop, as they were the only failed vessels found. This type of goblet was produced throughout the Mediterranean from the 5th century onward, possibly until the 8th-10th centuries, and was widely used among glassware. It is a multipurpose object that could also be used for lighting domestic spaces.

Some lamps have been found in Comacchio, but far from the workshop and close to the site where the cathedral would be built a few decades later. Moreover, the absence of wastes that can be typologically assigned to lamps with certainty suggests that these vessels were not produced in the Comacchio workshop. The sampled handle presumably belonging to this type was found in contexts dating from the 12th to the 14th centuries and was chosen for its double colour (CO530).

A few bottles and the base CO99, probably belonging to a late antique cup, have peculiar formal characteristics, unparalleled in the Comacchio repertoire. The hypothesis is that they are broken fragments collected for recycling. Part of the sample set is further represented by windowpanes (CO233a; CO233b; CO233c) and mosaic *tesserae* (CO25).

Working wastes include drops, drips and filaments (CO23a; CO23b; CO58b; CO121a; CO121b; CO365), small blocks (CO24; CO58a; CO100b; CO121e; CO122; CO184b), moils (remains of the detachment of the vessel from the blowpipe: CO100a; CO121c; CO121d; CO230),

and cut-outs produced during the finishing of the objects (CO184a; CO184c); none are attributable to a specific form.


Finally, a fragment of a crucible bearing an internal thin layer of glass was also retrieved and archaeometrically investigated (CO58c).

Experimental

The chemical composition of all samples was obtained through electron microprobe analysis (EMPA) and laser ablation inductively coupled plasma mass spectrometry (LA-ICP-MS). A small set of 5 blocks, was processed for Sr and Nd isotopic analysis. Lastly, the crucible and the glass attached to it was further investigated through optical microscopy (OM), scanning electron microscopy (SEM-EDS) and EMPA.

EMPA The quantitative determination of major and selected minor elements (Cu, Sb and Pb), as well as volatiles (Cl and S) was performed at the joined laboratory of the DST-UNIFI and CNR-IGG of Florence, using a JEOL Superprobe JXA-8230, equipped with five wavelength-dispersive spectrometers (WDS), under the following operating conditions: 15 kV, beam current at 10nA and beam diameter 10 µm. The peak counting time was of 10 s for Na, 15 s for MgO, Al₂O₃, SiO₂, K₂O, CaO, FeO, TiO₂, 30 s for P₂O₅, Cl, S and 40 s for MnO, Sb₂O₅, SnO₂, PbO and CuO. Matrix effects were corrected by ZAF algorithm. A selection of natural phases is used as primary standard for the elemental calibration (Astimex albite for Si and Na, plagioclase for Al, olivine for Mg, diopside for Ca, sanidine for K, apatite for P, celestine for S, tugtupite for Cl, barite for Ba and Smithsonian

Fig. 3 Representative images of the glass collection. At the top: rim of a goblet with white marvered trails and windowpanes. In the centre: drops, filaments, moils and small blocks. At the bottom: crucible with an inner layer of glass (credits: Laboratorio di Archeologia Medievale Ca' Foscari)

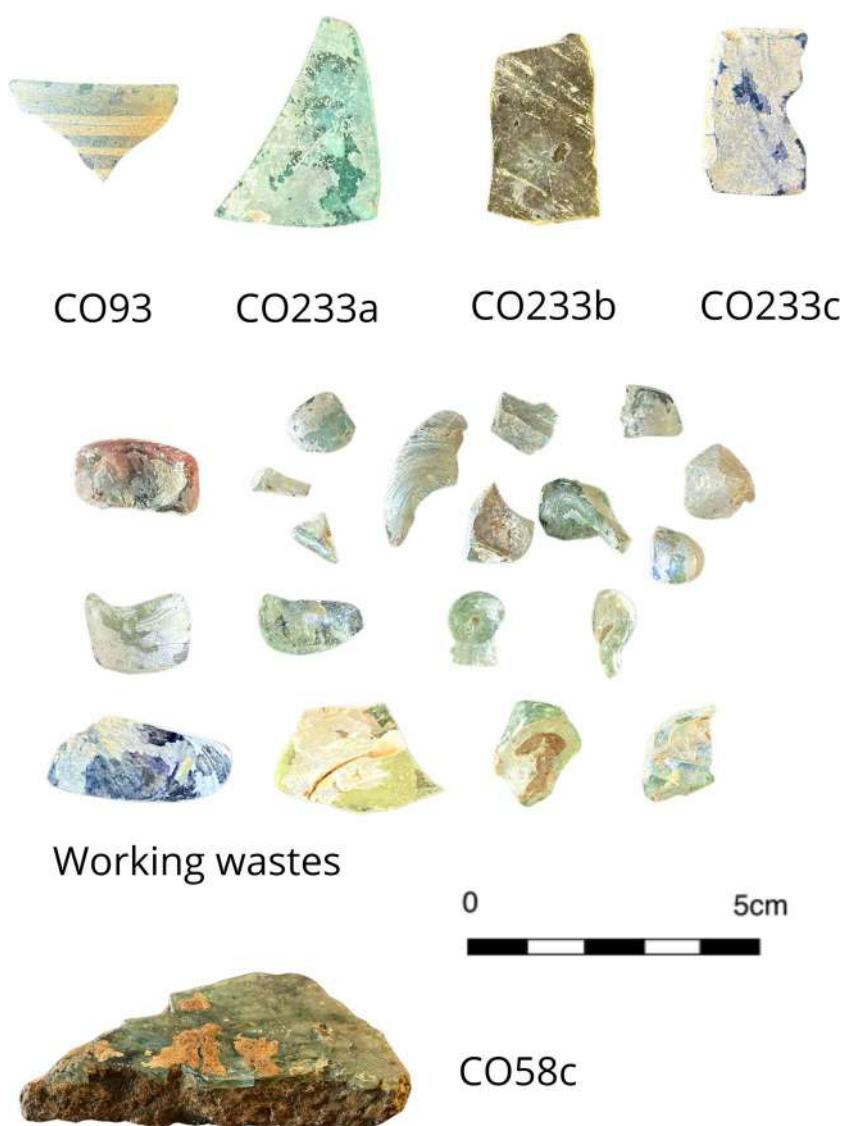

ilmenite for Ti and Fe). Synthetic reference material glass NIST-SRM1832 and three different Smithsonian Corning glasses (Corning-A NMNH 117218–4, Corning-B NMNH 117218–1 and Corning-D NMNH 117218–3; Vicenzi et al. 2002) are used as specific secondary standards for the analytical quality control. Replicate measurements (10 to 25) on the above-mentioned international reference standards show a good precision with a variation coefficient lower than 1% for silica, up to 2% for the other major elements and up to 5% for minor elements. Accuracy is lower than 0.5% for silica, up to 0.5% for the other major elements, between 0.8–1% for most minor elements while up to 2% for Sb_2O_5 and PbO. The total R^2 is considerably lower than 1 for all the analysed standards.

LA-ICP-MS The trace element content was determined by laser ablation-inductively coupled plasma-mass

spectrometry (at IGG-CNR, Pavia, Italy). The instrument combined an ablation microbeam, based on a Nd:YAG laser source (Brilliant, Quantel) operating at 266 nm (for details see Tiepolo et al. 2003), and a quadrupole ICP-MS (Drc-e, Perkin Elmer). Forty masses were acquired; the laser was operated at 10 Hz of repetition rate, the power on the sample was 1.5 mW and the spot size was set at 40 μm . Accuracy was assessed on the USGS BCR-2 reference glass (analysed as an unknown in each analytical run) and was better than 20% at the sub ppm level. Data reduction was carried out with the software package GLITTER (Van Achterbergh et al. 2001) and using NIST SRM 610 and ^{29}Si as external and internal standards, respectively.

Sr and Nd isotopes Samples preparation and isotopic analysis were performed at the DST-UNIFI Laboratory of Geochemistry of Radiogenic Isotopes. The selected samples

were preliminary crushed in small shards and weighted to an amount of some 150–200 mg, to get enough material for Sr and Nd isotopic measurements. The shards were then placed in an ultrasonic bath with ethanol for few minutes to remove any external impurities.

Sample dissolution was carried out through acid digestion using concentrated HF and multiple additions of HNO₃ in the first step, followed by diluted 6N HCl (Avanzinelli et al. 2005 for details). The separation and purification of Sr and Nd were performed using cation-exchange AG W5x mesh and Ln-spec reusable resins respectively by sequential additions of properly diluted HCl Suprapure acid. A representative international standard reference material (USGS granite standard G-2) was also processed together with samples for data validation (Table S3). The G-2 standard is well defined in terms of Sr and Nd isotope values, as demonstrated by Weiss et al. (2006), showing good homogeneity in isotopic composition. Moreover, being a granite, which represents one of the more common protoliths for sands and is compositionally representative of crustal-derived material, it is the most suitable choice for a sand-dominated matrix, such as artificial glass. The total procedural blank for Sr was 300 pg, resulting in a negligible effect on isotope results, considering the amount of the processed material. Isotope ratios were measured via Thermo Finnigan Triton-Ti® thermal ionization mass spectrometer (TIMS) equipped with nine movable collectors. Sr isotopic compositions were measured in dynamic mode and corrected for mass fractionation, normalising to the natural value of ⁸⁸Sr/⁸⁶Sr = 8.375209. Possible ⁸⁷Rb interference has been corrected using the natural ⁸⁷Rb/⁸⁵Rb ratio of 0.386, resulting in minor or negligible variations in the measured isotope value. International standard NIST-SRM 987 and USGS G-2, used to check for data quality, yielded results of 0.710264 ± 0.000004 (2sd, average of two measurements) and 0.709777 ± 0.000006 (2se), respectively. These results overlap within the error margins (2sd) of the known values from literature references by Thirlwall (1991) and Weis et al. (2006) (Table S3). Nd isotopic ratios were measured in static mode, using the natural ¹⁴⁶Nd/¹⁴⁴Nd value of 0.7219 for correction of mass fractionation. Internal NdFi and international USGS G-2 standard were used as quality control, providing values of 0.511463 ± 0.000005 (2sd, average of two measurements) and 0.512219 ± 0.000007 (2se), respectively well within the error (2sd) of the literature reference values provided by Avanzinelli et al. (2005) and Weis et al. (2006) (Table S3).

SEM-EDS For the crucible, a small slice was cut perpendicular to the sample surface to prepare the polished thin section. Morphological and semi-quantitative micro-chemical analyses were obtained by means of a SEM-EDS electronic microscope (ZEISS EVO MA 15; M.E.M.A. University

of Florence) equipped with an analytical system in dispersion of energy EDS/SDD, Oxford Ultimax 40 (40mm² with resolution 127 eV @5.9 keV). The operative conditions were: acceleration potential of 15 kV, 500 pA beam current, working distance of 9–8.5 mm; 20 s live time as acquisition rate useful to archive at least 600.000 cts, on Co standard, process time 4 for point analyses. The microanalysis software (Aztec 5.0 SP1) applies the XPP matrix correction scheme developed by Pouchou & Pichoir (1991). This is a Phi-Rho-Z approach which uses exponentials to describe the shape of the φ (pz) curve. XPP matrix correction was chosen because of its favourable performance in situations of severe absorption, such as the analysis of light elements in a heavy matrix. The quantitative analysis is “standard-less”, *i.e.* using pre-acquired standard materials for calculations, and the achievement of constant analytical conditions (*i.e.* filament emission) is obtained through repeated analyses of a Co metallic standard. Detection limits and precision were of 0.1 wt% and ~ 2%, respectively. Observations were mainly performed in backscattered electrons on carbon-coated polished surfaces and compositional maps were further acquired.

Results

The results of the analyses conducted by EMPA, LA-ICP-MS and isotopic analyses are shown in Supplementary Tables S1, S2 and S3, respectively. EMPA and LA-ICP-MS full data set is also provided in Supplementary Tables S4 and S5. A further file containing measurements has been provided as supporting documentation in Supplementary Materials (Excel Table).

Textural features

The collection mainly includes homogeneous glass but also numerous banded samples (CO23A, 92, 100A, 121A, 121B, 230, 325, 365, 530; Supplementary Fig. S1). Among banded samples, the compositional differences vary from sample to sample and are related to changes in the levels of Cu and/or Sb and/or Pb. The lighter bands show higher Cu, Sb and Pb levels than dark bands in CO92 (light green), higher Pb in CO325 (green), higher Pb and, to a lesser extent Sb, in CO121A-B (light green), CO230 (green) and CO365 (green). In samples CO100A and CO530, dark and light bands macroscopically correspond to green and red glass, respectively. Green glass is characterised by lower Fe, Cu and Pb contents than red glass. Sb levels do not show consistent variation between the two glass colours. The fluidity test no. CO23 comprises a homogeneous, likely fresh, aqua blue portion (CO23B) and a finely banded, intentionally coloured, green portion (CO23A). The latter was obtained due

to the addition of Cu, Sb and Pb and does not show colour variations on a macroscopic scale. Moreover, a heterogeneous aggregate (Supplementary Fig. S2) has been found close to the surface. It contains wollastonite -incorporating other elements such as Na, Al, Fe, Mn, Mg and Sb (Supplementary Table S6)—and clinopyroxene. The latter shows a Na-rich composition, ranging from a Mg- and Ca-poor diopside to a Fe-poor salitic augite and an aegirine-augite (Supplementary Table S7).

In Supplementary Table S1 (EMPA results), the bands are indicated as db (dark grey bands), mb (grey bands), lb (light grey bands) and wb (white bands) and the composition of each band is provided together with their average (av.) values.

Glass components

Based on MgO-K₂O ratio, the glass collection is all made of natron-based glass, although samples CO58B and CO58C are characterised by high K₂O (2.73 wt%) and MgO (4.33 wt%) levels, respectively (Lilyquist and Brill 1993). As will be explained later, while the increase in K₂O levels can be mainly due to environmental contamination, those of MgO can be explained by the use of steatite crucibles. Al₂O₃ contents ranging between 1.95 and 3.42 wt% point to the use of impure sands as the vitrifying agent (Henderson et al. 2004). Nevertheless, other values such as FeO, TiO₂ and Zr, clearly indicate the use of different types of sands. The stabilising agent is CaO in all samples (3.9–9.5 wt%). Sr contents show a wide range of values (from 176 to 612 ppm) and those above 350 may further suggest the presence of shells, either deliberately added to the glass batch or naturally present in the sand (Freestone et al. 2003; Degryse 2014), as it further discussed below commenting on isotopic analyses.

Regarding colouring agents, one aqua blue fluidity test (CO23B) and two goblets (aqua blue CO368 and light green CO94) show MnO contents below 0.025 wt% and negligible levels of decolouring/colouring agents (each < 10 ppm Cu, Sn, Sb and Pb each). Therefore, they are considered naturally coloured by the iron present in the sand. Similarly, the green sample CO233Ais deemed naturally coloured glass, assuming the use of a MnO-richer sand (MnO 0.179 wt%).

All other samples can be classified as either recycled or intentionally de/coloured by using the conventional thresholds of 100 ppm and 1000 ppm, respectively, for the contents of Cu, Sn and Sb (Jackson 1996; Gliozzo 2017). Based on this criterion, a small group of 8 samples, including the crucible glass, exhibit concentrations of at least one of these elements between 100 and 1000 ppm (CO23A, CO25, CO58A, CO58C, CO230, CO233B, CO365 and CO366).

Among the remaining 22 intentionally coloured samples, the green olive pad-base CO99 had only FeO and MnO added, while the light green block CO121E had only Sb

added to a MnO-rich glass (2019 ppm Sb; 0.385 wt% MnO). All the other 20 samples show Cu and/or Sb or even Sn concentrations above 1000 ppm, with none of the indicative elements below 100 ppm. Within this subgroup, the green-red samples (CO100A and CO530) and the blue glass samples (CO24, CO122 and CO233C) warrant further attention. Concerning the former, despite iron levels not being particularly high (0.97 and 1.33 wt% FeO, respectively), as might be expected to favour reducing conditions for red glass (Cable and Smedley 1987), it is noteworthy that Pb and Sn amounts are double or even triple in the red areas compared to the green ones, while copper and antimony show similar levels in all bands. Overall, the low iron levels and, particularly, the green-red banded texture suggest the mixing of green and red glass. Regarding the blue blocks and the blue window, glass colour was obtained by the addition of cobalt, and the Co/Ni ratio—varying between 6.9 to 10.2—fits well within the 2–23 range indicated by Gratuze et al. (2018) for Byzantine glass.

Additionally, most of the green and blue-green glass exhibit strong linear correlations between several de/colouring agents, providing compelling evidence that warranted the in-depth analysis presented in the Discussion section.

Isotopic composition

The isotopic systematics of strontium (Sr) and neodymium (Nd) in ancient glasses offer valuable insights into the sources of the different components utilised in the glass-making process. In the case of natron-based glass, the isotopic ratios of Sr are significantly influenced by the carbonates that act as stabilizing agents. In contrast, the isotopic ratios of Nd are primarily linked to the sand used as a vitrifying agent.

Five blocks were selected for Sr and Nd isotopic analyses (Supplementary Table S3). These specimens were chosen because they are more likely to represent the original composition of the imported materials.

In these samples, the elevated Sr concentrations (above 400 ppm) may suggest the presence of shells. These shells could either have occurred naturally in the sand or been intentionally added to the glass batch (Freestone et al. 2003; Degryse 2014). The measured ⁸⁷Sr/⁸⁶Sr isotopic ratios vary from 0.70882 ± 0.000005 (CO121E) to 0.70894 ± 0.000005 (CO58A), indicating values slightly lower than the modern seawater standard of 0.709165 (Stille & Shields 1997; Banner 2004), but higher than the typical signature of the ancient Mesozoic carbonate platform (0.707–0.7075) extensively exposed in the Mediterranean region (Fig. 4A). While these initial findings seem to rule out the addition of limestones, they align with the utilisation of coastal sand, potentially containing abundant carbonate shells.

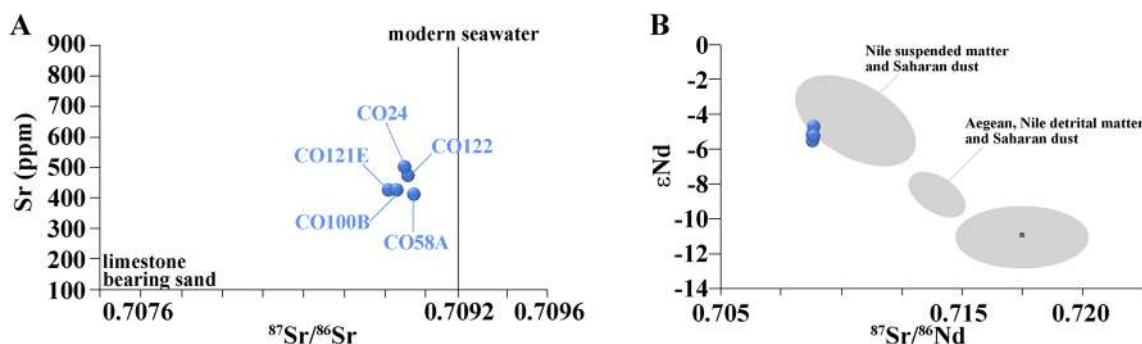


Fig. 4 The Sr, Nd isotopic values in Comacchio blocks. Measurements errors are encompassed within the symbol size

In terms of neodymium, the absolute concentrations among the five samples are notably consistent (5.6/7.0 ppm). However, there is relative heterogeneity in the $^{143}\text{Nd}/^{144}\text{Nd}$ isotopic ratios, ranging from 0.512357 (CO121E) to 0.512399 (CO58A), corresponding to -5.48 and -4.66 ϵ_{Nd} , respectively. Notably, samples CO121E and CO58A exhibit the lowest and highest isotopic ratios for both $^{143}\text{Nd}/^{144}\text{Nd}$ and $^{87}\text{Sr}/^{86}\text{Sr}$, respectively, indicating variations in the materials used compared to the other three samples. In a broader context, the integration of Sr and Nd isotopic signatures with additional geochemical parameters linked to sand composition (such as Ti_2O , Al_2O_3 and Zr) offers insights into the provenance of the sands employed. While it is conceivable that CO24 and CO122 may have utilised similar sands, the remaining three samples exhibit a discernible heterogeneity. This observation suggests the potential utilisation of different sands or variability in composition within the sourcing locale.

Lastly, it should be noted that all the samples fall within the range of variability of the surface sediments of the Nile River's riverine suspended matter and Saharan dust as characterised by Weldeab et al. (2002), among the various comparisons that can be proposed (Fig. 4B). This suggests a

possible provenance of the sands used as a vitrifying agent from the easternmost regions of the Mediterranean basin.

The crucible – CO58c

This small fragment, measuring 5 cm in width and 2.5 cm in thickness, exhibits three distinct layers, as depicted in Fig. 5. The bottom layer comprises quartz, K-feldspar, albitic plagioclase, orthoamphibole, calcite and rare Mg-Fe chlorite (typically below 150 μm), embedded in a poorly sintered clayey matrix. The presence of calcite and the poor sintering of the matrix suggests that this layer did not undergo high temperatures. However, it remains uncertain whether this layer represents a fragment of earth inadvertently adhered to the crucible or a deliberately laid layer. While the former hypothesis would explain the low temperatures observed, the latter hypothesis appears less plausible, albeit ceramic linings of crucibles have been known to effectively mitigate heat loss and prevent cracking of the overlying layers, a technique frequently observed in other crucibles (Bayley and Rehren 2007; Thornton and Rehren 2009).

The middle layer is a carbonate talc schist, commonly referred to as steatite or soapstone, subjected to high temperatures. It is worth noting that the process

Fig. 5 The crucible layering



of transforming talc ($\text{Mg}_3\text{Si}_4\text{O}_{10}(\text{OH})_2$) into enstatite ($\text{Mg}_2\text{Si}_2\text{O}_6$) begins at a temperature of 900 °C. This transformation is then followed by two more between 1000 °C and 1200 °C (from enstatite to protoenstatite), and between 1300 °C and 1400 °C (from protoenstatite to clinoenstatite). The process ends with complete melting, which occurs between 1405 °C and 1545 °C. This information has been supported by research from Antonelli et al. (2006), Silva Torres et al. (2015), and Baehre et al. (2019). Due to these transformations, it is possible to hypothesise a mixture of these phases from the internal to the external section of the crucible, although not inferable by SEM–EDS.

Chlorite breakdown products with acicular habitus are ubiquitous and show a Mg-rich and Cr-rich composition. Forsterite is sporadic and areas rich in calcite and magnesium probably testify to the original presence of dolomite and magnesite (both decomposed at 700 °C; see, e.g., Tian et al. 2014, Olszak-Humienik and Jablonski 2015). Iron compounds (hematite and/or magnetite?) and Mn-rich apatite are the prevalent accessory phases.

Lastly, the outermost layer is made up of glass corresponding to sample CO58C. In this layer, newly formed diopside is present at the interface with the steatite. Five transects were carried out by SEM–EDS to investigate the potential diffusion of elements between the crucible and the glass (Supplementary materials Figs. S3–S7). Both materials were crossed by these transects. The full documentation is available in the Supplementary materials, where the total transect and two partial transects—one on the glass and one on the crucible—are shown, leaving out the altered surface and the interface where newly formed crystals are sometimes present.

Regarding the glassy portion, it is worth noting that in all transects, a few elements consistently display the same trend. MgO continually increases as the analysis proceeds toward the crucible once the surface alteration has been overcome. On the other hand, CaO shows the opposite trend, with a constant decrease from the glass to the crucible.

Despite modest quantities and a more heterogeneous distribution do not allow the variation to be equally clear, also K_2O and FeO show a similar trend to MgO (especially in transect no. 1). Na_2O 's behaviour is more similar to that of CaO but not as consistent. Al_2O_3 , SiO_2 , TiO_2 , and MnO do not show significant changes.

The crucible portion has a composition so diverse from that of the glass and so heterogeneous that it does not allow continuous diffusion to be observed, except for CaO . Therefore, the relevant data primarily concerns (a) MgO and, to a lesser extent, K_2O and FeO , whose contents are enriched proportionally to the proximity to the crucible, and (b) CaO with the opposite behaviour, perhaps partly followed by Na_2O .

Discussion

Glass provenance

In a secondary production context like Comacchio, determining provenance can be challenging. Production and recycling cycles may have mixed, diluted or increased the amounts of indicative geo-markers (e.g., TiO_2 , Al_2O_3 , Zr and Hf). In this section, an attempt has been made to answer the provenance question and specify its reliability level. Table 2 summarises the results concisely, reporting key values. The compositional reference groups used for comparison are provided in Supplementary Tables S8a–b (Brill 1988; Freestone 1994; Freestone et al. 2000; Foy et al. 2003; Foster and Jackson 2009; Rosenow and Rehren 2014; Ceglia et al. 2015; Cholakova and Rehren 2018; Schibille et al. 2019; De Juan Ares et al. 2019; Schibille 2022). Compatibility with reference groups was tested based on all major elements and a selection of minor and trace elements, including Co , Cu , Sn , Sb , Sr , Zr , Hf , Pb , and REEs. Individual values that fell outside the compositional range of the reference group were noted in the text. Moreover, a reassessment of the provenance of the samples analysed in Bertini et al. (2020) has been performed and the results (which are quite similar) are compared in Supplementary Table S9. It may help the reader to consider that all samples from Bertini et al. (2020) are indicated with “Com” while those investigated in this study are indicated with “CO”. The sum of the samples analysed here with those previously investigated by Bertini et al. (2020) is equal to 123 vitreous findings. Among these, complete analyses (EMPA and LA-ICP-MS) are available for 94 samples.

Levantine glass The naturally coloured fluidity tests CO23B and the goblet CO368 present the typical composition of Levantine glass, characterised by low $\text{TiO}_2/\text{Al}_2\text{O}_3$ and high $\text{Al}_2\text{O}_3/\text{SiO}_2$ ratio, along with low amounts of FeO , MgO , K_2O and Zr . In particular, the very low levels of MnO (0.22 and 0.010 wt%) and the $\text{Na}_2\text{O}/\text{SiO}_2$ and $\text{CaO}/\text{Al}_2\text{O}_3$ ratios closely resemble the composition of the *Apollonia* products (Freestone et al. 2000, 2008; Tal et al. 2004; Phelps et al. 2016; Brems et al. 2018). Similarly, the moil CO230 and the waste CO365 can be associated with *Apollonia* products despite showing evident traces of recycling and lower Al_2O_3 amounts in CO230. The goblets CO94 and CO366 bears the same general characteristics of the previous samples but differs in relatively lower Al_2O_3 contents and, regarding CO94, higher CaO levels. These characteristics find comparison with Jalame products (4th c.; see Brill 1988 and Freestone et al. 2023); therefore, these two samples have been indicated as *Apollonia/Jalame*, meaning that both comparisons

Table 2 Main features of Connacchio glass, ordered by provenance assignment. Full EMPA and LA-ICP-MS data are provided in Supplementary Tables S1–S2 and S4–S5

Provenance	Publ.no.	Type	Colour	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	CaO	MgO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	Co	Cu	Sn	Sb	Pb	Sr	Zr		
<i>Apollonia</i>	CO23B	Fluidity test	aB	Nat. col.	71.98	0.06	3.20	0.43	0.02	6.24	0.43	15.77	0.55	0.04	0.21	0.98	1	5	2	1	6	324	39	
<i>Apollonia</i>	CO368	Goblet	laB	Nat. col.	72.21	0.06	3.13	0.37	0.01	6.96	0.48	15.18	0.51	0.04	0.12	0.86	1	3	1	0	5	369	32	
<i>Apollonia/Jalame</i>	CO366	Goblet	lab	Rec.	69.24	0.08	2.79	0.64	0.33	7.98	0.95	15.77	0.78	0.15	0.19	0.78	9	348	196	273	893	443	52	
<i>Apollonia-like</i>	CO230	Moil	G	Rec.	71.00	0.08	2.71	0.64	0.15	6.66	0.71	15.64	0.63	0.09	0.17	0.91	8	607	874	209	3504	405	50	
<i>Apollonia-like</i>	CO365	Waste	lab	Rec.	72.83	0.07	2.99	0.47	0.06	6.80	0.63	14.33	0.53	0.07	0.15	0.79	2	205	137	73	650	380	43	
<i>Jalame/Apollonia</i>	CO94	Goblet	IG	Nat. col.	71.64	0.06	2.82	0.39	0.02	9.51	0.62	13.28	0.97	0.06	0.22	0.38	1	12	2	0	13	353	38	
Levantine area	CO38C	Crucible g.	G	Rec.	72.63	0.08	2.75	0.75	0.05	3.94	4.33	13.55	0.83	0.07	0.12	0.79	15	105	183	42	295	268	50	
	CO23A	Fluidity test	G	Rec.	67.26	0.13	2.64	0.96	0.75	7.33	1.13	16.84	0.89	0.16	0.26	0.80	23	885	521	924	4076	536	88	
G2.1/G2.2	CO24	Block	dB	Int. col.	67.55	0.09	2.39	0.77	0.58	6.61	0.88	17.67	0.57	0.12	0.36	0.85	277	2133	178	6991	3381	501	61	
G2.1/G2.2	CO58B	Dripping	IG	Int. col.	66.80	0.13	2.52	1.05	0.68	6.63	0.98	15.98	2.72	0.15	0.23	0.82	37	1124	668	2645	6528	517	76	
G2.1/G2.2	CO92	Goblet	IG	Int. col.	64.95	0.16	2.56	1.01	0.87	7.25	0.99	17.07	0.73	0.20	0.30	0.85	71	3180	2875	3402	17683	605	100	
G2.1/G2.2	CO93	Goblet	IG	Int. col.	67.97	0.11	2.55	0.93	0.63	6.50	0.97	17.16	0.73	0.12	0.26	0.93	33	1742	706	1788	4578	498	69	
G2.1/G2.2	CO95	Goblet	IG	Int. col.	66.49	0.14	2.58	1.07	0.88	6.78	0.90	17.79	0.73	0.14	0.28	1.07	29	1805	381	1745	4603	500	93	
G2.1/G2.2	CO96	Goblet	IG	Int. col.	66.04	0.13	2.46	1.29	0.93	6.78	1.04	17.65	0.79	0.15	0.28	1.02	43	2579	896	1263	5929	528	83	
G2.1/G2.2	CO100A	Moil	IG(R)	Int. col.	68.72	0.13	2.81	0.93	0.34	5.94	0.90	16.63	0.83	0.13	0.21	0.91	29	2290	1801	1100	7719	435	72	
G2.1/G2.2	CO121A	Dripping	IG	Int. col.	67.80	0.13	2.49	1.06	0.86	6.55	1.14	17.07	0.76	0.08	0.26	0.93	26	1233	575	1189	3344	462	80	
G2.1/G2.2	CO121B	Dripping	IG	Int. col.	68.06	0.11	2.82	1.00	0.45	6.47	0.96	16.89	0.91	0.16	0.23	0.91	24	1882	444	1389	4083	443	66	
G2.1/G2.2	CO121D	Moil	IG	Int. col.	66.81	0.12	2.49	1.01	0.82	6.79	0.93	17.33	0.71	0.17	0.32	1.05	40	2550	417	2819	4635	482	74	
G2.1/G2.2	CO122	Block	B	Int. col.	67.58	0.09	2.32	0.90	0.61	6.78	0.90	17.42	0.70	0.11	0.34	0.69	275	2482	182	6345	2435	473	79	
G2.1/G2.2	CO184A	Cutting	G	Int. col.	67.25	0.13	2.62	1.02	0.68	6.80	1.07	17.29	0.82	0.14	0.26	0.69	41	1908	670	1906	5311	459	75	
G2.1/G2.2	CO184B	Block	G	Int. col.	67.29	0.10	2.45	0.89	0.73	6.60	0.89	17.82	0.57	0.11	0.31	1.11	24	2098	261	2196	4389	455	64	
G2.1/G2.2	CO184C	Wall	IG	Int. col.	66.90	0.12	2.44	0.98	0.75	6.52	1.04	17.93	0.69	0.14	0.29	1.01	47	2057	421	2343	4725	458	72	
G2.1/G2.2	CO233C	Window	dB	Int. col.	66.33	0.11	2.43	1.11	0.78	7.31	1.00	17.30	0.78	0.22	0.32	0.88	442	2099	523	3349	4264	543	72	
G2.1/G2.2	CO325	Goblet	IG	Int. col.	66.93	0.12	2.67	1.02	0.57	7.21	1.19	16.50	0.85	0.19	0.24	0.78	27	1986	1203	718	9245	513	72	
G2.1/G2.2	CO530	Lamp?	G(R)	Int. col.	65.67	0.12	2.78	1.33	0.59	7.56	1.00	14.82	0.85	0.18	0.19	0.73	72	7270	5277	301	23672	533	62	
G2.1/HFe	CO233B	Window	G	Rec.	68.50	0.12	2.56	1.75	1.15	6.74	1.01	16.19	0.61	0.13	0.28	0.83	8	48	5	101	80	612	82	
G3.2	CO25	Tessera	C	Rec.	70.38	0.07	1.95	0.42	0.60	5.98	0.62	17.95	0.42	0.02	0.24	1.29	5	24	2	228	16	423	42	
G3.2	G3.2-like (G2.1)	CO88	Wall	C	Int. col.	67.12	0.08	2.28	0.54	0.37	6.47	0.72	17.99	0.49	0.06	0.34	1.15	16	1561	2201	1608	14546	429	51
G3.2	G3.2-like (G2.1)	CO100B	Block	G	Int. col.	67.46	0.09	2.35	0.91	0.80	6.46	0.81	18.24	0.61	0.10	0.27	1.06	19	1548	192	1404	2700	428	56
HIMTa	CO99	Unknown	oG	+Fe+MnO	64.34	0.51	3.42	2.15	2.31	4.68	1.39	19.23	0.38	0.07	0.25	1.20	16	84	1	0	8	417	298	
Egypt 2 low Na ₂ O	CO233A	Window	G	Nat. col.	69.95	0.23	2.52	0.90	0.18	9.34	0.69	14.51	0.42	0.10	0.08	1.05	6	25	4	14	44	176	177	
Intermediate	CO58A	Block	ab	Rec.	69.97	0.10	2.93	0.82	0.28	6.44	0.75	16.23	0.70	0.11	0.21	0.88	17	797	343	797	1866	411	59	
Intermediate	CO121C	Moil	G	Int. col.	68.28	0.10	2.61	0.80	0.60	6.63	0.79	17.24	0.65	0.15	0.27	1.09	14	1491	305	1516	3395	436	58	

G2.1/G2.2 Foy series 2.1 and 2.2; *a* aqua; *l* light, *d* dark, *o*, olive; *B* blue; *G* green; *(R)* red stripes; *Rec.* recycled; *Int. col.* intentionally coloured; *Nat. col.* naturally coloured

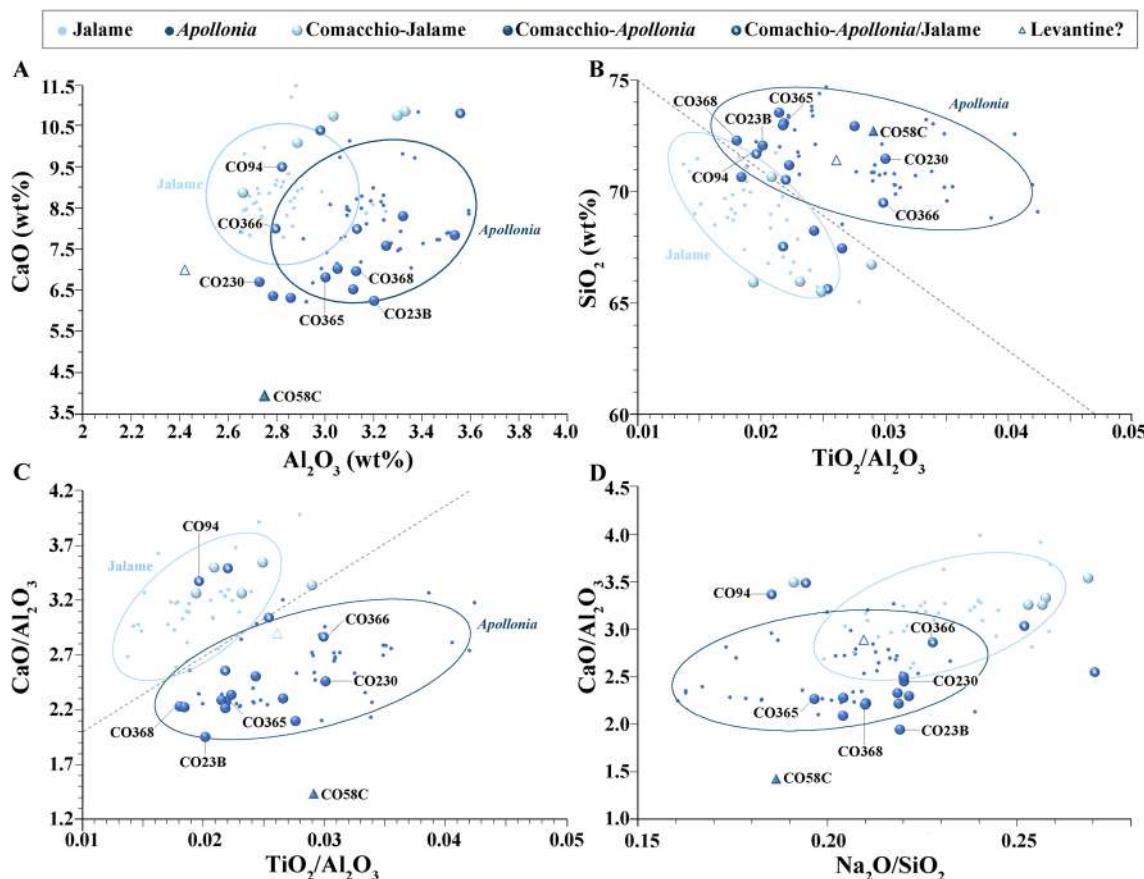


Fig. 6 Levantine glass. Both the reference samples from *Apollonia* and Jalame and the samples from Comacchio studied in and by Bertini et al. (2020) are represented. The confidence ellipses (90%) are drawn for the two reference groups. The dotted grey lines that sepa-

rate the distribution fields of *Apollonia* and Jalame are indicative only and correspond to the following functions: B) $y = -405x + 79.05$; C) $y = 68.75x + 1.3125$; D) $y = -22.143x + 7.6$

are reliable. This refers to the Jalame-type glass, not to the glass produced at Jalame many centuries earlier. It should also be noted that CO94 shows K₂O amounts relatively high compared to both *Apollonia* and Jalame products and could thus provide an indication of environmental contamination. Lastly, a Levantine provenance can be indicated for the glass from the crucible CO58C while explaining the anomalous CaO and Sr low levels due to the interaction with the crucible. Minor and trace elements are averagely low, as is typical of Levantine products.


Hence, 7 samples from this study are added to the 16 Levantine samples measured in Bertini et al. (2020) and all 23 are plotted in Fig. 6. In this figure, several diagrams are used for the same samples. Notably, the Na₂O/SiO₂-CaO/Al₂O₃ diagram introduced by Phelps et al. (2016) is no longer particularly effective for discriminating *Apollonia*'s products from those recently characterised from Jalame (Freestone et al. 2023). On the contrary, the Al₂O₃-CaO diagram and the Ti₂O/Al₂O₃-SiO₂ and Ti₂O/Al₂O₃-CaO/

Al₂O₃ diagrams present smaller overlaps of the confidence ellipses (90%). Similarly, Fig. 7A shows the compositional of Levantine glass alongside with that of the crucible glass CO58C (highlighted in red), showing a clear match with Levantine products.

Egyptian glass The poorly represented groups are the HIMT, the Egypt series and the séries 3.2:

- HIMTa glass is testified by the olive-green fragment CO99 thus bringing the total number of attested specimens to 3 (Com74 and Com75 in Bertini et al. 2020);
- the green window CO233A represents the first and only sample comparable to the poorly distributed group named “Egypt 2 (low Na₂O)” by Schibille et al. (2019);
- the colourless tessera CO25 fits well within the compositional range of the série 3.2 (henceforth G3.2), except for a slightly low Zr content (42 ppm) and an antimony level (228 ppm) higher than expected (< 30 ppm) in a practically uncontaminated com-

Fig. 7 The pattern of minor and trace elements contents in Levantine (A) and Egyptian glass (B–C). Values were normalised to the weathered continental crust, based on Kamber et al. (2005)

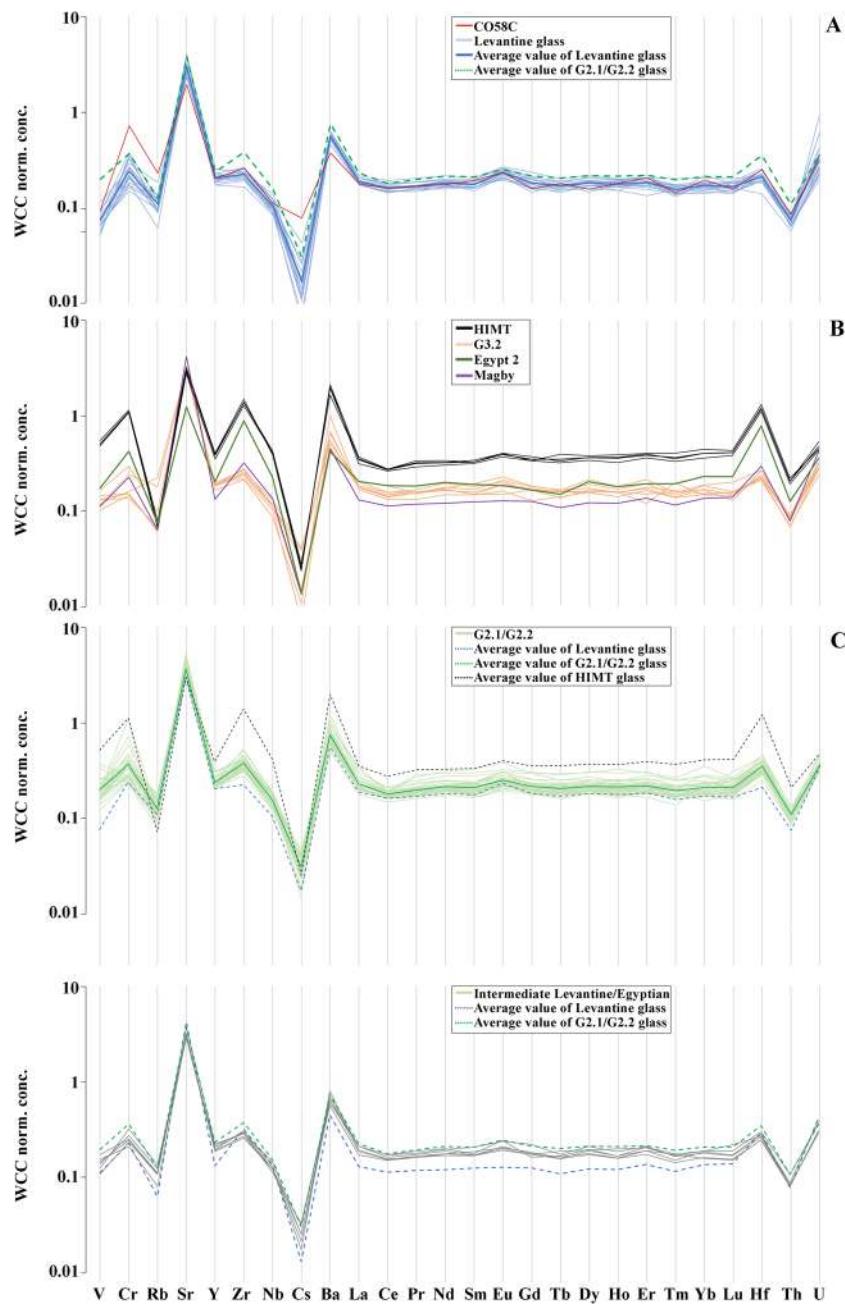

positional group such as the G3.2 (Schibille 2022). With less reliability, the wall CO88 and the blocks COO100B and CO121E could be assimilated to the G3.2 while taking into account lower MnO contents (CO88 and 121E) and admitting the later introduction of colourants (CO88, CO100B) or decolourant (CO121E). Among the materials previously investigated, only 4 other samples could be compared with this group (Com71, Com86, Com87 and Com91); however, only CO25 and Com87 show a trustable fit,

while the others present features comparable also with the séries 2.1 and 2.2.

- The green window CO233B and the yellow fragment Com85 represent the Fe-rich variant of the séries 2.1 (henceforth G2.1HFe) and other two samples can be added (Com38 and Com94) despite a weaker compatibility.
- To these scarcely attested groups, the sample Com14 in Bertini et al. (2020) may be added based on its attribution to the Magby-type glass defined by De Juan Ares et al. (2019).

In each case listed above, both the major and minor elements and traces are consistent with the proposed attributions. Among the overall collection, at least 60 samples are assigned to the série 2.1 and 2.2 (henceforth G2.1 and G2.2; Fig. 7C): 20 from this study and 47 from Bertini et al. (2020). These two groups -identified by Foy et al. (2003)- are distinguished essentially based on the contents of Mn (high in G2.1, low in G2.2) and colouring agents (variable in G2.1, constantly high in G2.2), although other distinctions may also be inconsistently observed (*e.g.*, Na₂O, CaO and Sr amounts). Since many of the samples considered in this study show greater affinity with G2.2 than with G2.1, both groups are recalled even if treated together. Among these samples, the provenance assignment is sometimes straightforward, other times less feasible due to the lack of measurement of key elements such as Zr and other minor and trace elements in reference data. It may be interesting to note that only a few samples present a composition perfectly comparable with G2.1 (*e.g.*, Com6, Com18 and Com29) and correspond to materials with slight traces of recycling. In contrast, all the others are more similar to G2.2 because they are heavily added. To provide some numbers, 53 samples contain Cu > 1000 ppm, 15 samples Sn > 1000 ppm, 43 samples Sb > 1000 ppm and 59 samples Pb > 1000 ppm. In the final section (“colouring coloured glass”), some food for thought is provided on these values.

Uncertain The list concludes with a small series of 4 samples (Com25, Com54, Com67, Com80) for which it is unrealistic to indicate a provenance. Additionally, there are 9 samples that show characteristics compatible with an Egyptian provenance but cannot be assigned to any known group (Com40, Com50, Com55, Com58, Com62, Com69, Com70, Com89, Com93). There are also 10 samples displaying intermediate values between Levantine and Egyptian products, possibly representing mixtures of both (CO58A, CO121C, Com1, Com4, Com27, Com48, Com63, Com92, Com96a). In Fig. 7, the trace and rare earth element pattern indicates that while the zirconium content is more compatible with Levantine glass, the REE profile aligns more closely with Egyptian glass. The isotopic analyses, primarily conducted to clarify the provenance of block CO58A, show that this sample also falls in the intermediate range between the Levantine materials from *Apollonia* and the Egyptian ones corresponding to G2.1 (Fig. 8). Given the similarly “intermediate” composition of G3.2, the hypothesis of an Egyptian origin seems more realistic but cannot be proven with certainty.

It should also be noted that the isotopic analyses conducted on samples from the mentioned groups are limited, and for Egyptian products in particular, they show wide

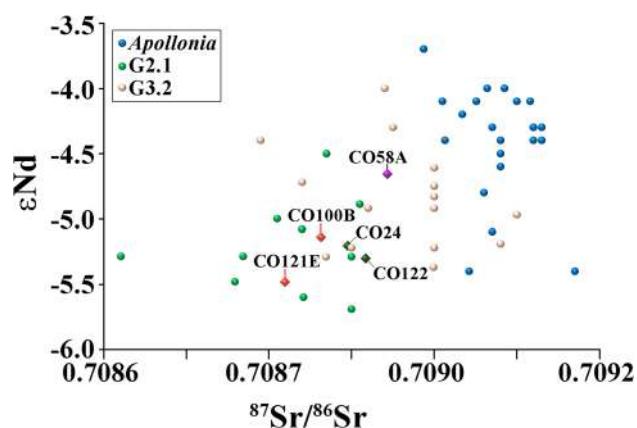


Fig. 8 $^{87}\text{Sr}/^{86}\text{Sr}$ ratio and ϵ_{Nd} values for Comacchio blocks compared to literature data available for the *Apollonia*, G2.1 and G3.2 glass groups. Selected data from Degryse et al. (2005), Degryse and Schneider (2008), Degryse et al. (2009), Ganio et al. (2012), Gallo et al. (2014), Maltoni et al. (2016), Brems et al. (2018), Gliozzo et al. (2019) and Barfod et al. (2022a)

distribution. However, while the attribution of samples CO24 and CO122 to G2.1/G2.2 appears to be confirmed, the non-unique classification of samples CO100B and CO121E as G3.2-like (/G2.1) remains unresolved.

To conclude this section and visualise the provenance assignments indicated above, Fig. 9 shows the $\text{Al}_2\text{O}_3/\text{SiO}_2$ - $\text{TiO}_2/\text{Al}_2\text{O}_3$ diagram proposed by Schibille et al. (2017) and the diagram $\text{TiO}_2/\text{Al}_2\text{O}_3$ -Zr in which the different Levantine and Egyptian products are discriminated based on elements representative of the sands used. Overall, Levantine glass was imported and worked at Comacchio but, following a trend that now seems consolidated for the Adriatic area (Gliozzo et al. 2023c), it does not represent a consistent supply, much less a priority one. Out of 116 for which provenance can be proposed, the materials investigated allowed only 20 samples to be identified as Levantine products. In contrast, Egyptian glass was particularly abundant based on at least 74 occurrences. The most attested type of glass is decidedly G2.1/G2.2, almost always heavily added, while Egypt 2 and HMT glass represent only 4% of total imports and are practically fresh. Glass type G3.2 is poorly represented and, like Jalame-type glass for Levantine products, can testify to the recovery of older materials as well as the presence of productions that inherited their characteristics.

Working glass at comacchio

The Comacchio excavations returned consistent evidence of the various processing phases and, among these, the crucible, the crucible-glass and the blocks deserve further discussion.

The crucible added valuable information on the production cycle. Unfortunately, the tiny dimensions of the fragment do not allow its shape to be reconstructed; however,

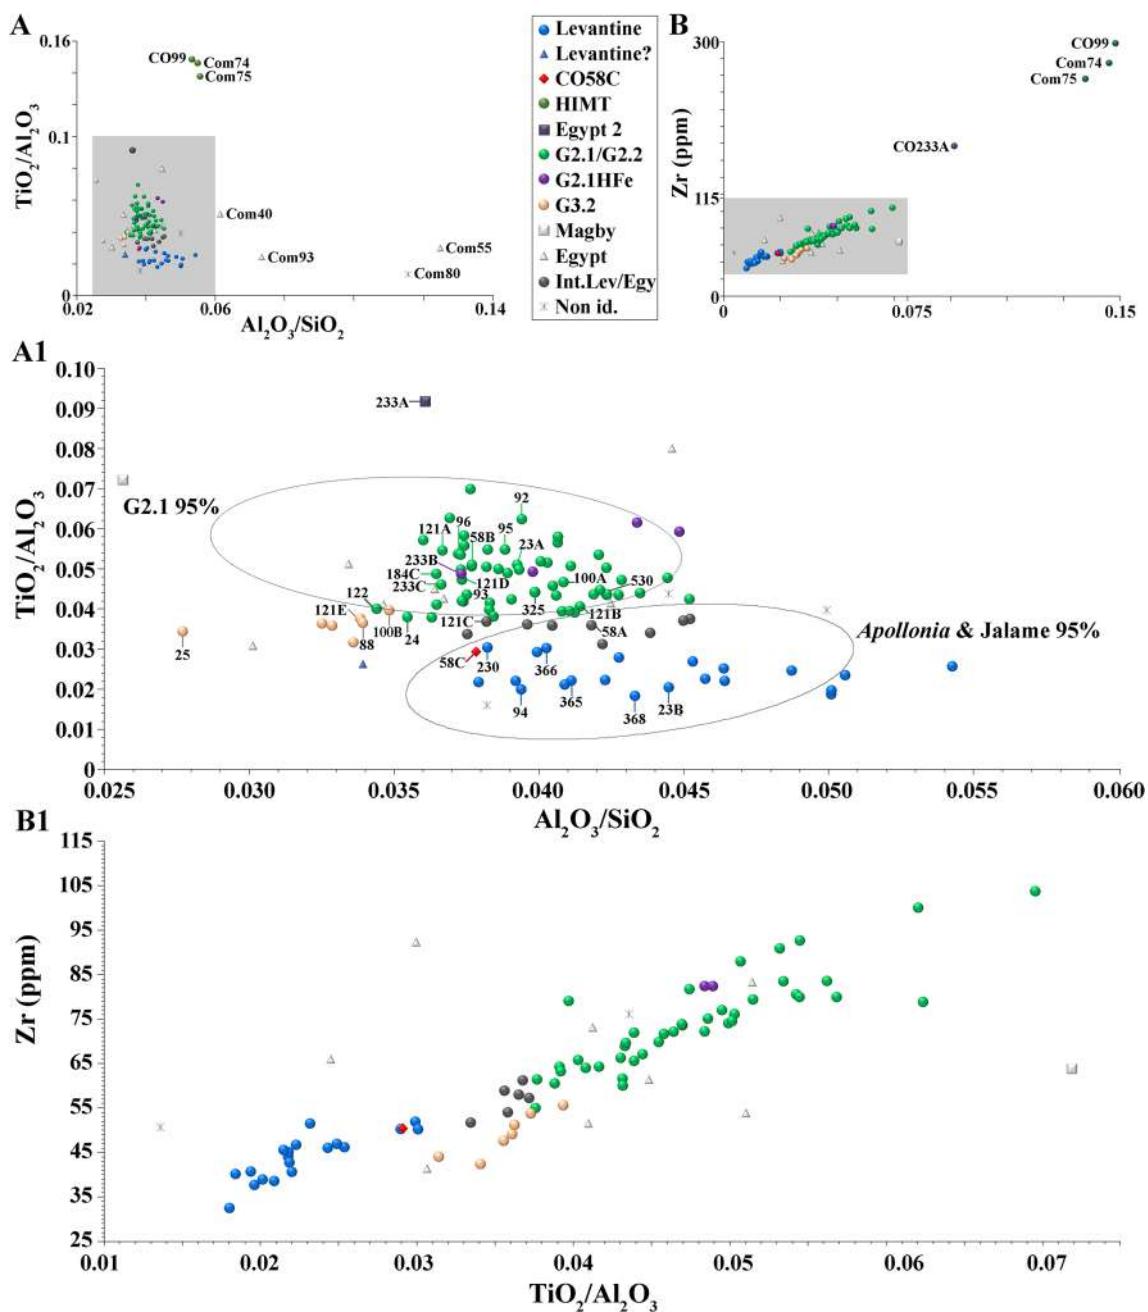


Fig. 9 Provenance assignment of Comacchio's glass. The diagrams A1 and B1 are inset of the smaller diagrams **A** and **B** on top

its flat profile may suggest a flat-bottomed crucible, thus perfectly comparable with the truncated cone shape of other crucibles found on the site (Alberti 2021). The effects of the pyrotechnological process hinder further insights into the provenance of steatite; however, it must be noted that in the western and central Alps, this type of rock is common and was exploited in ancient times (see, *e.g.*, Mannoni et al. 1987, Santi et al. 2005, Santi et al. 2009). For example, north of Comacchio, several occurrences of western and central “pietra ollare” were found at Nogara (Monaco et al. 2023)

and Aquileia (Antonelli and Lazzarini 2012); however, in both cases, their use was mainly related to food preparation, benefiting from the low porosity and very low hardness of this rock. Undoubtedly, these sites and Comacchio could take advantage of an easy communication route such as the Po River, which must have facilitated their transport.

Notably, the excavations at Comacchio brought to light numerous steatite artefacts. Indeed, they had various destinations and uses and were imported to Comacchio to be distributed along the southern Adriatic Sea (they were found as

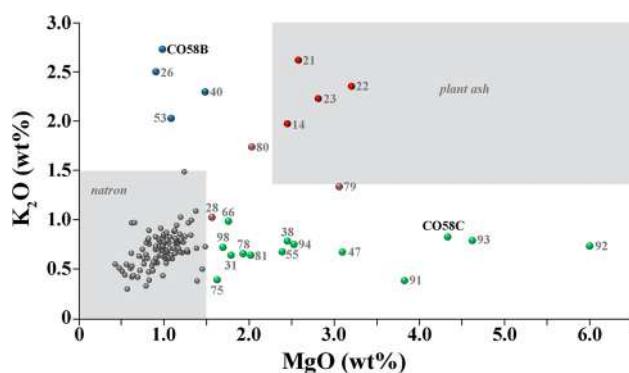


Fig. 10 MgO-K₂O binary diagram showing the use of different fluxes and the effects of different environmental or crucible contaminations. All numbers without label refer to Bertini et al. (2020). Coloured dots indicate natron-based glass (small grey), plant ash-based glass (red), environmental contamination (blue), crucible contamination (green), uncertain cases (pink)

far as Otranto; Alberti 2021). Some crucibles were analysed by Mini et al. (2016), who determined the provenance of most of those artefacts from Valchiavenna and Valmalenco (Central Alps). Further, they investigated four fired fragments (COM4, COM6, COM8 and COM10), which are perfectly comparable with the crucible investigated in this study. The fragments analysed by Mini et al. (2016) were not used in the glass workshop and bore no useful traces to understand what type of artisanal activity they had served.

A further consideration arising from the study of the crucible concerns the MgO contamination of the glass associated with it. The sample CO58C and the six crucible glasses from Bertini et al. (2020) show MgO contents between 2.0 to 4.6 wt% (Fig. 10). The common characteristic of this group of samples is the high levels of MgO and the contamination with the steatite crucible can now help explaining this evidence. This result is of particular interest even outside the context investigated here because it can clarify why some natron-based glass has high magnesium contents, especially if contents variations are observed along the thickness of the glass. Within the Comacchio materials, for example, other ten samples show this characteristic despite not being visibly associated with a crucible: 2 undiagnostic fragments (Com28 and Com75), 4 wasters (Com38, Com66, Com31 and Com55), 2 *tesserae* (Com91 and Com92) and 2 goblets (Com78 and Com98).

It follows, however, that the level of contamination can vary based on different factors such as the greater/lesser proximity of the steatite surface to the analysed glass, the thickness of the glass, the firing time and the temperature reached. Therefore, the canonical limit of 1.5 wt% MgO for natron-based glass can be decreased or increased depending on the amount of MgO present in the initial glass – which is, however, difficult to establish.

As a side effect, the increase in MgO, the decrease of CaO and the other possible contaminations less consistently observed (K₂O, FeO and Na₂O) can make the provenance study even more challenging and/or less reliable.

As a final note on this topic, it is important to consider that sample Com91, a white *tessera*, exhibits the highest Sb content in the entire collection. High MgO contents in opaque white glass have been attributed to the use of ankerite, based on comparisons with Roman enamels (Fiorentino et al. 2020, following Henderson 1991, on enamels). Alternatively, it has been proposed that an MgO-rich source for antimony (Fiorentino et al. 2020, following Wypyski & Becker 2004) or the introduction of dolomite (Wypyski & Becker 2004) into the mixture might be responsible. In the context of Comacchio, the introduction of magnesium via antimony can be excluded. Among the 17 samples with MgO content exceeding 1.6 wt%, five have Sb levels below 100 ppm, including those with the highest MgO values. Moreover, there are no correlations suggesting a link between these two elements. However, this hypothesis should remain open for the opaque white *tessera* Com91. Moving on to the blocks, they are all representative of Egyptian glass imports, except for CO58A. The intermediate composition of CO58A does not allow for a definitive determination of its provenance, although isotopic analyses suggest an Egyptian origin as well. The only block in which the decolouring purpose can be understood is CO121E. In this sample, the MnO level is higher than 0.025 wt% (0.39 wt%) and the antimony appears intentionally added (2019 ppm) but the final colour is light green. Since it is difficult to imagine that they were not capable of producing colourless glass, it will perhaps be more likely that the taste or market destination of this workshop favoured blue-green glass, as testified by production indicators (e.g. collars, cuts, drops and fluidity tests) and the entire collection of glass vessels found on the site (Ferri 2021a).

Colouring coloured glass

This section delves deeper into glass colouring techniques after observing interesting linear correlations between Sn and Pb, Cu and Sb and Sb and Pb contents in blue and green glass (n=82; Fig. 11).

The 76 samples for which both Sn and Pb values were provided show a strong Sn-Pb linear correlation with R²=0.751 (Fig. 9A). The Pb/Sn ratio cover a wide range from 1.61 to 110.79, corresponding to hypothetical alloys ranging from Sn₁Pb₉₉ to Sn₃₈Pb₆₂ (Supplementary Table S10) and the subset of 32 samples running along the correlation line has the strong R² value of 0.969 (Pb/Sn ratio from 4.55 to 8.82); however, most samples (n=73) would show Pb>75% in a hypothetical SnPb alloy. Despite the correlation, the use of lead stannates is possible but not directly demonstrable since crystals of lead

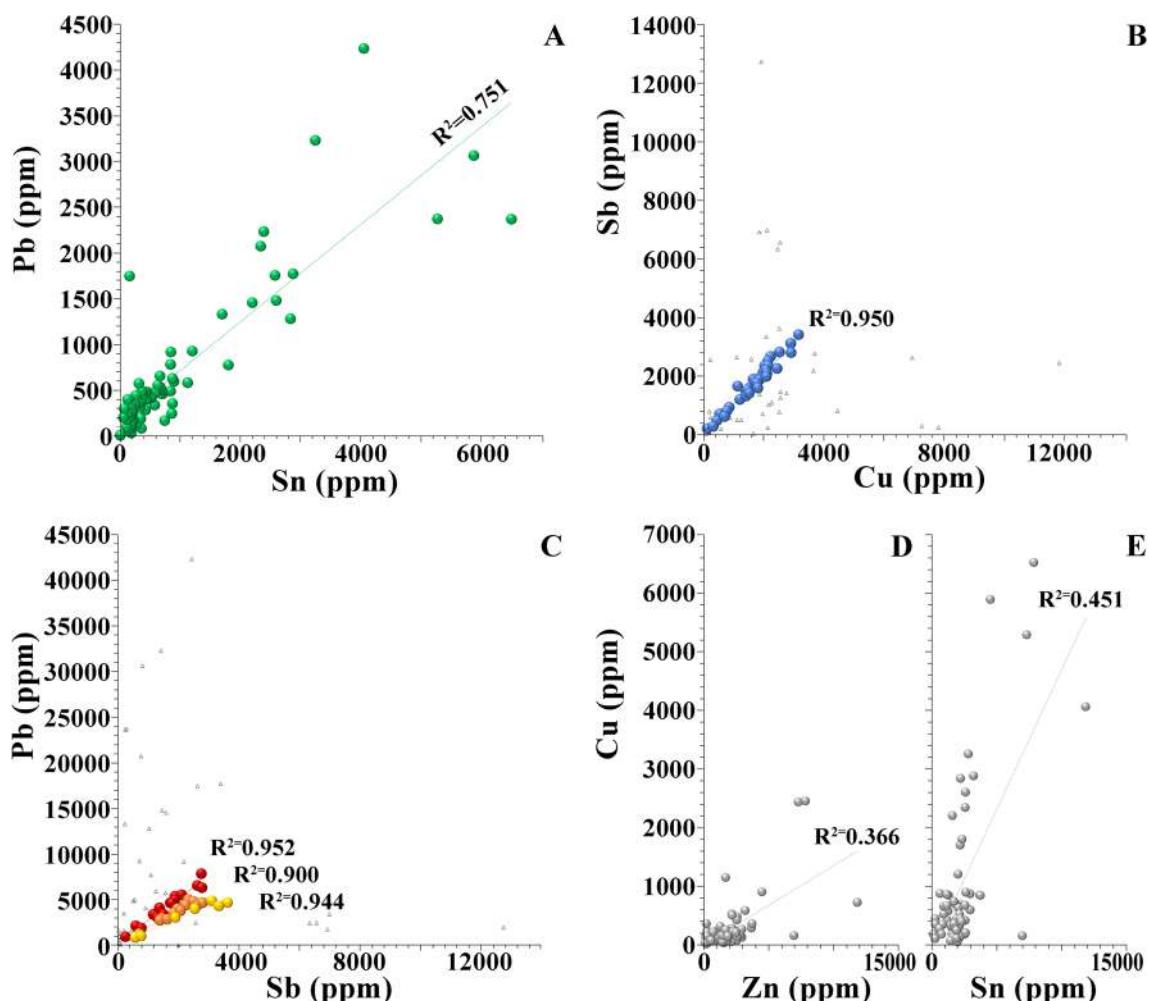


Fig. 11 The linear correlations between Sn and Pb, Cu and Sb, Sb and Pb, Cu and Zn/Sn

stannates -usually showing “30–35% tin oxide and 60–65% lead oxide” (Peake and Freestone 2014) – were not found. Hence, to further test this hypothesis, the PbO/SnO_2 ratio has been calculated and compared with the data reported by Tite et al. (2008, Table 1) for “lead stannate opacified glass and enamels”. In the latter, the PbO/SnO_2 ratio ranges from 2.8 to 12.2; within the Comacchio dataset, 58 samples fall within this range. It should be noted, however, that while in the (non-opaque) glass from Comacchio, the absolute values are mostly (PbO) or constantly (SnO_2) lower than 1 wt%, the beads, the *tesserae* and the enamels considered in the reference literature contain from 8.4 to 53.3 wt% PbO and from 1.2 to 9.2 wt% SnO_2 . Matin (2019) highlighted the importance of a Pb/Sn ratio equal to or above 3.5 for the formation of Pb_2SnO_4 and showed that in 80 green glasses collected from the literature, the average Pb/Sn ratio was 9.1 (s.d. 4.4), with minimum and maximum values ranging between 0.2 and 25.6, *i.e.* compatible with 73 of the 76 Comacchio samples.

Another possibility for explaining the Sn:Pb correlation is the use of soldering alloys. In this case, however, the alloys resulting from the recalculation (Supplementary Table S10) are Pb-richer than those we know from ancient sources such as Pliny (*e.g.*, *tertiarium* with $\text{Pb}:\text{Sn} = 2:1$ and *argentarium* with $\text{Pb}:\text{Sn} = 1:2$) and *Theophilus* (with $\text{Sn}/\text{Pb} = 2/1$) (see also Miśta-Jakubowska et al. 2022). Archaeometric investigation on SnPb solders is not frequent and the few examples available regard soft soldering for applying silver and gold foil. For example, the solders analysed in a 3rd-c. CE belt-fitting from Linowo in Poland (Kowalski et al. 2017) were made of a SnPb alloy with a ratio of 1:4, which is close to that of a small group of Comacchio samples.

The second correlation that deserves an additional note is the one observed between Cu and Sb (Supplementary Table S11; Fig. 9B). In the 78 samples where $\text{Cu} > 100 \text{ ppm}$ and/or $\text{Sb} > 25$ the correlation is very weak ($R^2 = 0.011$); conversely, a subgroup of 35 samples (*i.e.* just under half of the total) reaches an R^2 value of 0.959. These samples

are of great interest because the Cu/Sb ratio ranges between 0.75 and 1.27 and consequently implies that Cu:Sb ratio is approximately of 1:1. Indeed, the consistency of the group may suggest a voluntary action rather than randomness.

The third correlation between Sb and Pb (Supplementary Table S12) does not regards all 75 samples ($R^2=0.005$). Nevertheless, at least three different correlations can be identified within a subset of 37 samples. The first one includes 15 samples showing Pb/Sb ratio ranging from 3.42 to 2.24 (red dots with $R^2=0.952$ in Fig. 9C); the second one includes 14 samples showing Pb/Sb ratio between 2.12 and 1.64 (orange dots with $R^2=0.900$ in Fig. 9C) and the third one includes 8 samples with a Pb/Sb ratio (1.58/1.24; yellow dots with $R^2=0.944$ in Fig. 9C) which corresponds to the composition of the lead antimonate pigment with 58 wt% lead oxide and 42 wt% antimony oxide (Molina et al. 2014). As for lead stannates, however, also lead antimonates were sought but not found by SEM-EDS and it must be kept in mind that the production of pigments and 'animes' could vary on the Pb:Sb ratio to obtain different shades of yellow.

Finally, various recalculations on green and blue-green samples were carried out to verify the possibility of significant trends. Several combinations have been tested, assuming, for example, that copper had been introduced unalloyed or as bronze, brass or a ternary alloy such as gunmetal (Supplementary Table S13 and Appendix). Then, other constraints have been added, such as fixing the Sb and Pb contents to an Sb₄₂Pb₅₈ ratio (constraint 1), fixing the copper alloy to a Cu₉₀Sn₁₀ ratio (constraint 2) or fixing the gunmetal alloy to Sn=Zn (constraint 3 to lower the contents of Sn and be able to redistribute it). The results of these tests are provided in the Supplementary Appendix.

Calculations show that in samples with Cu:Sb~1:1, the most frequent combinations are:

1. 1 part Cu (unalloyed copper) + 1 part Sb;
2. 1 part Cu (unalloyed copper) + 2 – 3 parts Sb₄₂Pb₅₈;
3. 1 part Cu₉₀Sn₁₀(bronze) + 1 part Sb;
4. 1 part Cu₉₀Sn₁₀(bronze) + 2 – 3 parts Sb₄₂Pb₅₈;
5. 1 part Cu₇₅Zn₂₅/Cu₉₆Zn₄(brass) + 1 part Sb₄₂Pb₅₈;
6. 1 part Cu₇₅Zn₂₅/Cu₉₆Zn₄(brass) + 2 – 3 parts Sb₄₂Pb₅₈;
7. 1 part Cu₇₃Sn₁₄/Cu₉₂Sn₄Zn₄(ternary alloys) + 2 parts Sb₄₂Pb₅₈.

Of all the possible combinations, those that would have allowed better control of the colour are those with "pure" components. On the contrary, with the use of alloys, the procedure to obtain the 1:1 ratio seems more complicated except for the combinations no. 3 (bronze + Sb) and no. 5 (Zn-poor brass + Sb) in a 1:1 ratio and the combination no. 7 (ternary alloy + Sb₄₂Pb₅₈) in ratio 1:2. In all combinations, the resulting SnPb compound is rarely Sn-rich, while in most cases, Pb represents over 75% (on average ~ Sn₁₆Pb₈₄). Furthermore, there is no constant SnPb ratio in any of the hypothetical combinations.

In samples where the Cu/Sb correlation is not apparent, the most frequently observed combinations are:

1. Brass + SnPb + Sb;
2. Brass + Sb₄₂Pb₅₈ + SnPb;
3. Ternary alloy (constraint no.3) + Sb₄₂Pb₅₈ + SnPb.

The ratios between the various components are quite variable. Still, in the combination no. 2, it is interesting to note that while the Cu/Sb ratio varies from 1.27 to 4.83, the brass:Sb₄₂Pb₅₈ ratio ranges from 0.6 to 1.3, therefore returning to that 1:1 ratio observed in the samples of the previous group.

In both subgroups, the metal that has most frequently provided plausible combinations was brass and its (possible) use may have been varied depending on the Zn content of the alloy, *i.e.* a feature that could have been roughly determined by glassworkers since the higher the zinc, the more golden the colour, while the lower the zinc, the more silvery the colour. Hence, the process may have been practically simple, using Zn-poor brass alloys and two parts of Sb₄₂Pb₅₈ or Zn-richer brass alloys (or Zn and Sn in the case of gunmetals) and only one part of Sb₄₂Pb₅₈.

It is worth highlighting that these calculations are not intended to completely discard the recycling hypotheses -which in part will certainly have happened- but introduce the possibility that deliberate colouring procedures can be reconstructed based on the same values, when a series of correlations may suggest intentionality (intentional colouring) rather than controlled randomness (recycling).

Upon comparing our findings with other published research, such as the study conducted on the San Vincenzo al Volturro workshop by Schibille and Freestone (2013), notable differences and similarities emerge. Unlike the study in Comacchio, their investigation reveals the absence or very weak presence of Sn–Pb and Sb–Pb correlations. Additionally, they report a Cu-Sb correlation in clear and colourless glasses, with copper values averaging 3198 ppm (ranging from 719 to 9586 ppm), which they attribute to recycling.

While attributing strong correlations solely to recycling may pose challenges due to the possible mixing of materials from different epochs and provenances, the introduction of "pure" components or those with a predictable composition, such as metals, might offer greater control over the final product. For instance, the introduction of antimony (Sb) might have aided in maintaining copper in its oxidised state, thus reducing the risk of alloy formation. Conversely, the presence of copper could have facilitated the reduction of antimony from (V) to (III) oxidation states, necessary for Sb to decolourise glass ($2\text{Cu}^+ + \text{Sb}^{5+} \rightleftharpoons 2\text{Cu}^{2+} + \text{Sb}^{3+}$). This mechanism could potentially explain the high copper content in colourless glass. Nevertheless, at Comacchio, a consistent correlation where Cu and Sb are present in approximately

equal ratios is challenging to attribute solely to the reuse of older *tesserae*. Moreover, the coexistence of the glass workshop and the metallurgical workshop encourages exploring alternative explanations alongside recycling, within the frame of cross-crafts interactions.

These considerations suggest the possibility of a technology less reliant on recycling, akin to that reconstructed for San Vincenzo al Volturno. Consequently, each case should be evaluated individually.

Additionally, it is noteworthy that high lead (Pb) contents have often been interpreted as indicative of continuous recycling when comparing different contexts from various periods (Rehren and Freestone 2015, Fig. 6). While recycling certainly contributed to increased average Pb levels, could we exclude the possibility that lead's properties, such as lowering the melting temperature and viscosity of glass and improving workability, have been increasingly exploited over the centuries by intentionally increasing its content?

The Comacchio samples, all from a single, restricted chronological period, exhibit Pb values ranging from 5 ppm to 23672 ppm. Is it plausible that lead was intentionally added for technological reasons when levels exceed 1000 ppm, rather than solely relying on recycling?

We do not claim to have definitive answers to propose. Presumably, there may not be a rigid model in the context of pre-industrial production, but all various options should be considered in the current state of research; however keeping in mind that the intentional colouration does not exclude previous recycling cycles.

Conclusions

The study of representative 34 samples, combined with the data already available, made it possible to frame Comacchio's glass production within the trade routes of Levantine and Egyptian products and obtain original production technology data.

Comacchio's imports fit perfectly into an increasingly consistent and significant picture, showing the priority of imports from Egypt over those from the primary glass-making kilns on the Levantine coast. In this framework, Comacchio data are even more important because they offer a glimpse of the glass trade in the second half of the seventh century, corresponding to or immediately following the activity of the *Apollonia* furnaces. However, despite the revitalization of Levantine production testified by the *Apollonia* products, the relationship between Levantine and Egyptian imports is 22% to 78%. Undoubtedly, the greater manufacturing difficulty imposed by Levantine glass and an increasing trend of imports from Egypt may have both played an important role.

Regarding production technology, the most interesting result certainly concerns the use of steatite crucibles and the relative increase in MgO in the glass. This result, supported by archaeological and archaeometric evidence, can be used as a valid argument to explain high MgO contents in the absence of a corresponding increase in K₂O and can therefore be applied to the study of many other finds beyond this case study. On the other hand, this aspect seems to invalidate the reconstruction of mixing between natron-based and plant ash-based glass proposed in the previous literature. Furthermore, the discovery of only three samples of plant ash glass among the 123 investigated suggests a randomness that tends to exclude the import and processing of plant ash-based glass at Comacchio.

Finally, the presence of evident correlations (*e.g.*, Sn–Pb and Cu–Sb) led to a series of calculations to understand which compounds could have been used as an alternative to the hypothesis of a random introduction due to recycling. The calculations highlighted that the colour could be obtained by introducing appropriate compounds including metals and, among these, brass returned the greatest compatibility. Furthermore, the SnPb correlation may indicate the use of lead stannates or soldering alloys, although they have not been directly observed.

Ultimately, the purpose of the calculations was not to discard the recycling hypothesis but rather to not give in to a hypothesis invoked perhaps too often, even when not necessarily the only one. In this regard, it is worth remembering that glassworking was closely connected with metalworking at the production site of Comacchio. While recycling can account for part of the evidence, the rest could be attributed to the expertise of Comacchio artisans. They aimed to produce green–blue glass and knew how to control both the glass and metal production processes to achieve it.

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1007/s12520-024-02017-1>.

Acknowledgements The authors express their sincere gratitude to Dr. Laura Chiarantini (M.E.M.A) for her invaluable guidance and constructive suggestions during SEM-EDS investigation. E.G. acknowledges the National Recovery and Resilience Plan (PNRR) funds – Call PE – Project PE5 – CHANGES, “Cultural Heritage. Active Innovation for Next-Gen Sustainable Society” - Code PE_00000020. E.G. and M.F. acknowledge Ministero dell’Istruzione, dell’Università e della Ricerca, Grant/Award Number FOOD & S.T.O.N.E.S. PRIN2017, CUP H74I17000170003.

Authors contribution Introduction: MF, EG; Materials: MF; Experimental: EG, EB; Results: EG, EB (isotopic investigations); Discussion: EG; Conclusions: EG, MF, EB.

Funding Open access funding provided by Università degli Studi di Firenze within the CRUI-CARE Agreement.

Data availability The authors confirm that the data supporting the findings of this study are available within the article and its supplementary materials.

Declarations

Competing interest The authors declare no competing interests.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

References

- Alberti A (2021) 12. La Pietra Ollare E i traffici commerciali dei comacchiesi. In: Gelichi S, Negrelli C, Grandi E (eds) Un Emporio E La Sua cattedrale. Gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, Firenze, pp 333–343
- Antonelli F, Lazzarini L (2012) The first archaeometric characterization of roman millstones found in the Aquileia archaeological site (Udine, Italy). *Archaeometry* 54(1):1–17. <https://doi.org/10.1111/j.1475-4754.2011.00615.x>
- Antonelli F, Santi P, Renzulli A, Bonazza A (2006) Petrographic features and thermal behaviour of the historically known ‘pietra ollare’ from the Italian Central Alps (Valchiavenna and Valsesia). In: Maggetti M, Messiga B (eds) Geomaterials in cultural heritage. The Geological Society, London, pp 229–239
- Avanzinelli R, Boari E, Conticelli S, Frascalanci L, Guarnieri L, Perini G, Petrone CM, Tommasini S, Ulivi U (2005) High precision Sr, Nd, and Pb isotopic analyses and reproducibility using new generation thermal ionisation Mass Spectrometer: aims and perspective for Isotope Geology Applications. *Periodico Di Mineralogia* 74(3):147–166
- Baehre O, Kloess G, Raue D, Muenster T, Franz A (2019) From talc to enstatite: archaeometric investigations on an ancient Egyptian whitish bead. *Archaeol Anthropol Sci* 11:1621–1629. <https://doi.org/10.1007/s12520-019-00785-9>
- Banner JL (2004) Radiogenic isotopes: systematics and applications to earth surface processes and chemical stratigraphy. *Earth Sci Rev* 65(3–4):141–194. [https://doi.org/10.1016/S0012-8252\(03\)00086-2](https://doi.org/10.1016/S0012-8252(03)00086-2)
- Barfod GH, Freestone IC, Jackson-Tal RE, Lichtenberger A, Raja R (2022a) Exotic glass types and the intensity of recycling in the northwest quarter of Gerasa (Jerash, Jordan). *J Archaeol Sci* 140:105546. <https://doi.org/10.1016/j.jas.2022.105546>
- Bayley J, Rehren T (2007) Towards a functional and typological classification of crucibles. In: La Niece S, Hook D, Craddock PT (eds) Metals and Mines – Studies in Archaeometallurgy. Archetype, London, pp 46–55
- Bertini C, Henderson J, Chinery S (2020) Seventh to eleventh century CE glass from Northern Italy: between continuity and innovation. *Archaeol Anthropol Sci* 12:120. <https://doi.org/10.1007/s12520-020-01048-8>
- Brems D, Freestone IC, Gorin-Rosen Y, Scott R, Devulder V, Vanhaecke F, Degryse P (2018) Characterisation of byzantine and early islamic primary tank furnace glass. *J Archaeol Science: Rep* 20:722–735. <https://doi.org/10.1016/j.jasrep.2018.06.014>
- Brill RH (1988) Scientific investigations of the Jalame glass and related finds. In: Davidson Weinberg G (ed) Excavations at Jalame: site of a glass factory in late roman Palestine. University of Missouri, Columbia, pp 257–294
- Cable M, Smedley JW (1987) The replication of an opaque red glass from Nimrud. In: Bimson M, Freestone IC (eds) *Early vitreous materials*. British Museum Occasional paper, 56. British Museum Research Laboratory, London, UK, pp 151–163
- Ceglia A, Cosyns P, Nys K, Terryn H, Thienpont H, Meulebroeck W (2015) Late antique glass distribution and consumption in Cyprus: a chemical study. *J Archaeol Sci* 61:213–222. <https://doi.org/10.1016/j.jas.2015.06.009>
- Cholakova A, Rehren T (2018) A late antique manganese-decolourised glass composition: interpreting patterns and mechanisms of distribution. In: Rosenow D, Phelps M, Meek A, Freestone IC (eds) *Things that travelled: Mediterranean glass in the first millennium AD*. UCL, London, pp 46–71. <https://doi.org/10.2307/j.ctt21c4tb3.9>
- De Juan Ares J, Vigil-Escalera Guirado A, Cáceres Gutiérrez Y, Schibille N (2019) Changes in the supply of eastern Mediterranean glasses to Visigothic Spain. *J Archaeol Sci* 107:23–31. <https://doi.org/10.1016/j.jas.2019.04.006>
- Degryse P (ed) (2014) Glass making in the Greco-Roman World, results of the ARCHGLASS Project. University, Leuven
- Degryse P, Schneider J (2008) Pliny the Elder and Sr-Nd isotopes: tracing the provenance of raw materials for roman glass production. *J Archaeol Sci* 35:1993–2000. <https://doi.org/10.1016/j.jas.2008.01.002>
- Degryse P, Schneider J, Poblome J, Waelkens M, Haack U, Muchez P (2005) A geochemical study of roman to early byzantine glass from Sagalassos, South-West Turkey. *J Archaeol Sci* 32(2):287–299. <https://doi.org/10.1016/j.jas.2004.09.006>
- Degryse P, Schneider J, Lauwers V, Henderson J, Van Daele B, Martens M, Huisman HDJ, De Muynck D, Muchez P (2009) Neodymium and strontium isotopes in the provenance determination of primary natron glass production. In: Degryse P, Henderson J, Hodgins G (eds) Isotopes in vitreous materials. Studies in Archaeological sciences. University, Leuven, pp 53–72
- Ferri M (2021a) I vetri Dallo Scavo Di Piazza XX Settembre. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 403–417
- Ferri M (2021b) Le Officine produttive. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 463–475
- Fiorentino S, Chinni T, Vandini M (2020) Ravenna, its mosaics and the contribution of archaeometry. A systematic reassessment on literature data related to glass tesserae and new considerations. *J Cult Herit* 46:335–349. <https://doi.org/10.1016/j.culher.2020.06.003>
- Foster HE, Jackson CM (2009) The composition of ‘naturally coloured’ late roman vessel glass from Britain and the implications for models of glass production and supply. *J Archaeol Sci* 36(2):189–204. <https://doi.org/10.1016/j.jas.2008.08.008>
- Foy D, Picon M, Vichy M, Thirion-Merle V (2003) Caractérisation des verres de la fin de l’Antiquité en Méditerranée occidentale: l’émergence de nouveaux courants commerciaux. In: Foy D, Nenna M-D (eds) Échanges et commerce du verre dans le monde antique. Actes du Colloque de l’AFAV (Aix-en-Provence et Marseille, 7–9 Juin 2001). Monographies Instrumentum, 24. Drémil-Lafage: Éditions Mergoil, pp 41–85

- Freestone IC (1994) Chemical analysis of “raw” glass fragments. In: Hurst H (ed) Excavations at Carthage, Vol II, 1 The Circular Harbour, North Side. Oxford University Press for British Academy, p 290
- Freestone IC, Gorin-Rosen Y, Hughes MJ (2000) Primary glass from Israel and the production of glass in late antiquity and the early Islamic period. In: Nenna M-D (ed) La route Du Verre. Ateliers Primaires et secondaires du second millénaire av. J.-C. Au Moyen Âge, vol 33. Maison de l’Orient Méditerranéen, Lyon, pp 65–83
- Freestone IC, Leslie KA, Thirlwall M, Gorin-Rosen Y (2003) Strontium isotopes in the investigation of early glass production: byzantine and early Islamic glass from the Near East. Archaeometry 45(1):19–32. <https://doi.org/10.1111/1475-4754.00094>
- Freestone IC, Jackson-Tal RE, Tal O (2008) Raw glass and the production of glass vessels at late byzantine Apollonia-Arsuf, Israel. J Glass Stud 50:67–80
- Freestone IC, Barfod GH, Chen C, Larson KA, Gorin-Rosen Y (2023) Glass production at Jalame, Israel: process, composition and relationship to Roman glass in Europe. J Archaeol Science: Rep 51:104179. <https://doi.org/10.1016/j.jasrep.2023.104179>
- Gagetti E (2021) Magistra Romanitas? La Matrice Di Comacchio E La Produzione Di cammei vitrei a due strati a imitazione dell’antico. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 429–440
- Galli A, Bonizzoni L (2021) Dallo Stampo ai cammei in pasta vitrea: analisi non invasive sui materiali. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 441–446
- Gallo F, Marcante A, Silvestri A, Molin G (2014) The glass of the Casa Delle Bestie Ferite: a first systematic archaeometric study on late Roman vessels from Aquileia. J Archaeol Sci 41:7–20. <https://doi.org/10.1016/j.jas.2013.07.028>
- Ganio M, Boyen S, Fenn T, Scott R, Vanhoutte S, Gimeno D, Degryse P (2012) Roman glass across the empire: an elemental and isotopic characterization. J Anal At Spectrom 27:743–753. <https://doi.org/10.1039/C2JA10355A>
- Garavello S (2021) Manufatti in materia dura animale. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 365–376
- Gelichi S, Grandi E, Negrelli C (eds) (2021) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino
- Gliozzo E (2017) The composition of colourless glass: a review. Archaeol Anthropol Sci 9:455–483. <https://doi.org/10.1007/s12520-016-0388-y>
- Gliozzo E, Braschi E, Giannetti F, Langone A, Turchiano M (2019) New Geochemical and isotopic insights into the late Antiquity Apulian glass and the HIMT1 and HIMT2 glass productions - the glass vessels from San Giusto (Foggia, Italy) and the diagrams for provenance studies. Archaeol Anthropol Sci 11:141–170. <https://doi.org/10.1007/s12520-017-0531-4>
- Gliozzo E, Giannetti F, Goffredo R, Totten DM (2023a) Late antique glass from Salapia: tracking production and trading networks. Archaeometry 65(1):118–135. <https://doi.org/10.1111/arcm.12804>
- Gliozzo E, Ferri M, Braschi E, Cadamuro S, Cianciosi A (2023b) Late antique and early medieval glass from the northern Venetian lagoon: new data from the archaeological site of Jesolo. Microchim J 189:108511. <https://doi.org/10.1016/j.microc.2023.108511>
- Gliozzo E, Ferri M, Giannetti F, Turchiano M (2023c) Glass trade through the Adriatic Sea: preliminary report of an ongoing project. J Archaeol Science: Rep 51:104180. <https://doi.org/10.1016/j.jasrep.2023.104180>
- Gratuze B, Pactat I, Schibille N (2018) Changes in the signature of cobalt colorants in late antique and early Islamic glass production. Minerals 8(6):225. <https://doi.org/10.3390/min8060225>
- Henderson J (1991) Technological characteristics of Roman enamels. Jewellery Stud 5:65–76
- Henderson J, McLoughlin SD, McPhal DS (2004) Radical changes in Islamic glass technology: evidence for conservatism and experimentation with new glass recipes from early and middle Islamic Raqqā, Syria. Archaeometry 46(3):439–468. <https://doi.org/10.1111/j.1475-4754.2004.00167.x>
- Isings C (1957) Roman glass from dated finds. Archaeologica Traiectina 2. Groningen and Djakarta: J. B. Wolters, p 185
- Jackson C (1996) From Roman to early medieval glasses. Many happy returns or a new birth? Annals du 13^e Congrès de l’Association Internationale pour l’Histoire du Verre. AIHV, Lochem, pp 289–302. Pays Bas, 28 August–1 September 1995
- Kamber BS, Greig A, Collerson KD (2005) A new estimate for the composition of weathered young upper continental crust from alluvial sediments, Queensland, Australia. Geochim Cosmochim Acta 69:1041–1058. <https://doi.org/10.1016/j.gca.2004.08.020>
- Kowalski Ł, Strobin J, Garbacz-Klempka A, Perek-Nowak M (2017) Towards manufacturing technology: Balteus belt-fittings from the Wielbark culture cemetery in Linowo (Poland). J Archaeol Science: Rep 15:370–380. <https://doi.org/10.1016/j.jasrep.2017.09.006>
- Lilyquist C, Brill RH (1993) Studies in early Egyptian glass. The Metropolitan Museum of Art, New York, p 80
- Maltoni S, Silvestri A, Marcante A, Molin G (2016) The transition from Roman to late antique glass: new insights from the *Domus of Tito Macro in Aquileia* (Italy). J Archaeol Sci 73:1–16. <https://doi.org/10.1016/j.jas.2016.07.002>
- Mannoni T, Pfeifer HR, Serneels V (1987) Giacimenti e cave di pietra ollare nelle Alpi. In: La pietra ollare: della preistoria all’età moderna. Atti della Giornata di Studio (Como, Museo Civico Archeologico Giovo 16–17 ottobre 1982). Como: Edizioni New Press, pp 7–45
- Matin M (2019) Tin-based opacifiers in archaeological glass and ceramic glazes: a review and new perspectives. Archaeol Anthropol Sci 11:1155–1167. <https://doi.org/10.1007/s12520-018-0735-2>
- Mini FM, Santi P, Renzulli A, Riccardi MP, Antonelli F, Alberti A (2016) Representative archaeological finds of pietra ollare from Comacchio (Italy): identifying provenance and high-T mineral breakdown reactions hindering lithotype classification. Archaeol Anthropol Sci 8:135–148. <https://doi.org/10.1007/s12520-014-0220-5>
- Miśta-Jakubowska E, Czech Błońska R, Duczko W, Gójska A, Żabiński G, Ciepielewski P, Diduszko R, Kosińska A, Brojanowska A (2022) Research on chemical soldering in early medieval jewellery: the case of lunula-type Viking age ornaments. Archaeometry 64(3):698–713. <https://doi.org/10.1111/arcm.12730>
- Mitchell J (2021) An Eighth-Century Matrix for a bronze letter from Comacchio. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 425–428
- Molina G, Odin GP, Pradell T, Shortland AJ, Tite MS (2014) Production technology and replication of lead antimonate yellow glass from New Kingdom Egypt and the Roman Empire. J Archaeol Sci 41:171–184. <https://doi.org/10.1016/j.jas.2013.07.030>
- Monaco D, Saggioro F, Marrocchino E, Vaccaro C, Marchesini M (2023) Archaeometric analysis of encrustations adhering to pietra ollare fragments from the medieval village of Nogara. Heritage 6(4):3365–3384. <https://doi.org/10.3390/heritage6040178>

- Olszak-Humienik M, Jablonski M (2015) Thermal behavior of natural dolomite. *J Therm Anal Calorim* 119:2238–2248. <https://doi.org/10.1007/s10973-014-4301-6>
- Peake JRN, Freestone IC (2012) Cross-craft interactions between metal and glass working: slag additions to early Anglo-Saxon red glass. In: Meulebroeck W, Nys K, Vanclooster D, Thienpont H (eds) Integrated Approaches to the Study of Historical Glass (September 21, 2012) IAS, 12, pp 8422048–1/12. <https://doi.org/10.1111/12.973765>
- Phelps M, Freestone IC, Gorin-Rosen Y, Gratuze B (2016) Natron glass production and supply in the late antique and early medieval Near East: the effect of the byzantine-islamic transition. *J Archaeol Sci* 75:57–71. <https://doi.org/10.1016/j.jas.2016.08.006>
- Pouchou J-L, Pichoir F (1991) Quantitative analysis of homogeneous or stratified microvolumes applying the model PAP. In: Heinrich KFJ, Newbury DE (eds) Electron probe quantitation. Springer, New York, NY, pp 31–75. <https://doi.org/10.1007/978-1-4899-2617-3>
- Rapone F (2021) I reperti metallici. In: Gelichi S, Grandi E, Negrelli C (eds) Un Emporio E La Sua cattedrale: gli scavi di piazza XX Settembre E Villaggio San Francesco a Comacchio. All’Insegna del Giglio, Sesto Fiorentino, pp 353–364
- Rehren T, Freestone IC (2015) Ancient glass: from kaleidoscope to crystal ball. *J Archaeol Sci* 56:233–241. <https://doi.org/10.1016/j.jas.2015.02.021>
- Rosenow D, Rehren T (2014) Herding cats - roman to late antique glass groups from Bubastis, northern Egypt. *J Archaeol Sci* 49:170–184. <https://doi.org/10.1016/j.jas.2014.04.025>
- Santi P, Antonelli F, Renzulli A (2005) Provenance of medieval pietra ollare artefacts found in archaeological sites of central-eastern Italy: insights into the Alpine soapstone trade. *Archaeometry* 47(2):253–264. <https://doi.org/10.1111/j.1475-4754.2005.00200.x>
- Santi P, Renzulli A, Antonelli F, Alberti A (2009) Classification and provenance of soapstones and garnet chlorite schist artifacts from medieval sites of Tuscany (Central Italy): insights into the Tyrrhenian and Adriatic trade. *J Archaeol Sci* 36(11):2493–2501. <https://doi.org/10.1016/j.jas.2009.05.006>
- Schibille N (2022) Islamic glass in the making. Leuven University, Leuven, p 270. <https://doi.org/10.11116/9789461664419>
- Schibille N, Freestone IC (2013) Composition, production and procurement of glass at San Vincenzo al Volturno: an early medieval monastic complex in Southern Italy. *PLOS ONE* 8(10):e76479. <https://doi.org/10.1371/journal.pone.0076479>
- Schibille N, Meek A, Tobias B, Entwistle C, Avisseau-Broustet M, Da Mota H, Gratuze B (2016) Comprehensive chemical characterisation of byzantine glass weights. *PLoS ONE* 11(12):e0168289. <https://doi.org/10.1371/journal.pone.0168289>
- Schibille N, Sterrett-Krause AE, Freestone IC (2017) Glass groups, glass supply and recycling in late roman Carthage. *Archaeol Anthropol Sci* 9:1223–1241. <https://doi.org/10.1007/s12520-016-0316-1>
- Schibille N, Gratuze B, Ollivier E, Blondeau É (2019) Chronology of early islamic glass compositions from Egypt. *J Archaeol Sci* 104:10–18. <https://doi.org/10.1016/j.jas.2019.02.001>
- Silva Torres HS, Chicarino Varajão AFD, Soares Sabioni AC (2015) Technological properties of ceramic produced from steatite (soapstone) residues–kaolinite clay ceramic composites. *Appl Clay Sci* 112–113:53–61. <https://doi.org/10.1016/j.clay.2015.04.016>
- Stiaffini D (1985) Contributo ad una prima sistemazione tipologica dei materiali vitrei altomedievali. *Archeologia Medievale* 12:667–687
- Stille P, Shields G (1997) Radiogenic isotope geochemistry of sedimentary and aquatic systems. Springer
- Tal O, Jackson-Tal RE, Freestone IC (2004) New evidence of the production of raw glass at late byzantine Apollonia-Arsuf, Israel. *J Glass Stud* 46:51–66
- Thirlwall MF (1991) Long-term reproducibility of Multicollector Sr and Nd isotope ratio analysis. *Chem Geol* 94(2):85–104. [https://doi.org/10.1016/S0009-2541\(10\)80021-X](https://doi.org/10.1016/S0009-2541(10)80021-X)
- Thornton CP, Rehren Th (2009) A truly refractory crucible from fourth millennium Tepe Hissar, Northeast Iran. *J Archaeol Sci* 36(12):2700–2712. <https://doi.org/10.1016/j.jas.2009.08.008>
- Tian L, Tahmasebi A, Yu J (2014) An experimental study on thermal decomposition behavior of magnesite. *J Therm Anal Calorim* 118:1577–1584. <https://doi.org/10.1007/s10973-014-4068-9>
- Tiepolo M, Bottazzi P, Palenzona M, Vannucci R (2003) A laser probe coupled with ICP – double-focusing sector-field mass spectrometer for in situ analysis of geological samples and U–Pb dating of zircon. *Can Mineral* 41(2):259–272. <https://doi.org/10.2113/gscanmin.41.2.259>
- Tite MS, Pradell T, Shortland A (2008) Discovery, production and use of tin-based opacifiers in glasses, enamels and glazes from the Late Iron Age onwards: a reassessment. *Archaeometry* 50(1):67–84. <https://doi.org/10.1111/j.1475-4754.2007.00339.x>
- Van Achterbergh E, Ryan CG, Jackson SE, Griffin WL (2001) Data reduction software for LA-ICP-MS: appendix. In: Sylvester PJ (ed) Laser ablation –ICP-mass spectrometry in the Earth sciences: principles and applications, vol 29. Mineralogical Association of Canada, Ottawa, Ontario, Canada, pp 239–243
- Vicenzi EP, Egging S, Logan A, Wysoczanski R (2002) Archeological reference glasses: new additions to the Smithsonian. *J Res Natl Inst Stand Technol* 107(6):719–727. <https://doi.org/10.6028/jres.107.058>
- Weis D, Kieffer B, Maerschalk C, Barling J, de Jong J, Williams GA, Hanano D, Pretorius W, Mattielli N, Scoates JS, Goolaerts A (2006) High-precision isotopic characterization of USGS reference materials by TIMS and MC-ICP-MS. *Geochem Geophys Geosyst* 7(8):Q08006. <https://doi.org/10.1029/2006GC001283>
- Weldeab S, Emeis K-C, Hemleben C, Siebel W (2002) Provenance of lithogenic surface sediments and pathways of riverine suspended matter in the Eastern Mediterranean Sea: evidence from $^{143}\text{Nd}/^{144}\text{Nd}$ and $^{87}\text{Sr}/^{86}\text{Sr}$ ratios. *Chem Geol* 186:139–149. [https://doi.org/10.1016/S0009-2541\(01\)00415-6](https://doi.org/10.1016/S0009-2541(01)00415-6)
- Wypyski MT, Becker L (2004) Glassmaking technology at Antioch: evidence from the Atrium House triclinium and later mosaics. In: Becker L, Kondoleon C (eds) The arts of Antioch: art historical and scientific approaches to roman mosaics and a catalogue of the Worcester Art Museum Antioch Collection. Princeton University Press, Worcester, pp 115–175

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Gliozzo, E., Braschi, E., Ferri, M. 2024. New data and insights on the secondary glass workshop of Comacchio (Italy): MgO contents, steatite crucibles and alternatives to recycling. *Archaeological and Anthropological Sciences*. DOI: 10.1007/s12520-024-02017-1

List of Supplementary materials

- Table S1. Results obtained by EMPA. Dark grey bands (db), medium grey bands (mb), light grey bands (lb) and white bands (wb) are indicated. Average data of “n=” measurements are expressed as wt% [sd=standard deviation].
- Table S2. The results achieved by LA-ICP-MS on the glass collection from Comacchio. All values are provided as ppm. Abbreviations: db=dark grey bands; mb=medium grey bands; lb=light grey bands; n=number of measurements.
- Table S3. Sr, Nd isotopic results on Comacchio blocks.
- Table S4. EMPA full dataset. All values in wt%.
- Table S5. LA-ICP-MS: full data set. All values in ppm.
- Table S6. The composition of wollastonite crystals measured by EMPA.
- Table S7. The composition of clinopyroxenes measured by EMPA.
- Table S8. The overall collection from Comacchio and the results of the provenance investigation.
- Table S9a. The reference and compositional groups used for comparison.
- Table S9b. The composition of reference and compositional groups listed in Tables S9a.
- Table S10. Discussion of the Sn-Pb correlation. For converting elements to oxides, the following factors have been used: 1.07722 for Pb to PbO and 1.1347999 for Sn to SnO₂. The lines filled in grey are those corresponding to R²=0.969.
- Table S11. Discussion of the Cu-Sb correlation.
- Table S12. Discussion of the Sb-Pb correlation.
- Table S13. Calculation of bronze and brass hypothetical alloys.

- Figure S1. Banded samples CO23A, 92, 100A, 121A, 230, 325, 365 and 530. The spot analyses are reported in Supplementary Table S4.
- Figure S2. The sample CO23. Spot analyses are provided in Tables S7 and S7.
- Figure S3-S7. SEM-EDS transects made along the glass section of sample CO58C.

- Appendix
- Excel Table (uploaded separately)

Table S1. Results obtained by EMPA Dark grey bands (db), medium grey bands (mb), light grey bands (lb) and white bands (wb) are indicated. Average data of “n=” measurements are expressed as wt% [sd=standard deviation].

		SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO100A db	n=9	68.96	0.13	2.84	0.90	0.34	0.92	6.09	16.73	0.85	0.14	0.20	0.88	0.25	0.52	0.14	0.09	99.97
	sd	0.3	-	-	-	-	-	0.2	0.2	-	-	-	-	-	0.1	-	-	
CO100A lb	n=9	68.49	0.14	2.77	0.97	0.35	0.88	5.80	16.53	0.81	0.13	0.21	0.93	0.32	1.14	0.15	0.37	99.99
	sd	0.1	-	-	-	-	-	-	0.1	-	-	-	-	-	0.1	-	-	
*CO100A (av.)	n=18	68.72	0.13	2.81	0.93	0.34	0.90	5.94	16.63	0.83	0.13	0.21	0.91	0.29	0.83	0.15	0.23	99.98
	sd	0.3	-	-	-	-	-	0.2	0.2	-	-	-	-	-	0.3	-	0.1	
CO100B	n=7	67.46	0.11	2.35	0.91	0.80	0.81	6.46	18.24	0.61	0.10	0.27	1.06	0.20	0.32	0.20	0.03	99.94
	sd	0.1	-	-	-	-	-	-	0.1	-	-	-	-	-	-	-	-	
CO121A db	n=5	68.06	0.15	2.57	1.02	0.83	1.01	6.67	17.00	0.79	0.13	0.27	0.86	0.15	0.21	0.19	0.04	99.96
	sd	0.2	-	-	0.1	-	0.1	0.1	0.3	-	-	-	-	0.1	-	-	-	
CO121A lb	n=6	67.58	0.16	2.54	1.04	0.87	1.10	6.62	17.13	0.77	0.10	0.28	0.94	0.17	0.51	0.13	0.06	99.99
	sd	0.5	-	0.1	0.1	-	0.3	0.2	0.1	-	-	-	-	0.1	-	-	-	
*CO121A (av.)	n=11	67.80	0.16	2.49	1.06	0.86	1.14	6.55	17.07	0.76	0.08	0.26	0.93	0.17	0.48	0.13	0.05	99.99
	sd	0.40	-	0.10	0.10	-	0.30	0.20	-	-	-	-	-	0.10	-	-	-	
CO121B db	n=3	69.37	0.23	3.32	0.90	0.25	0.88	5.13	17.21	0.99	0.11	0.17	0.77	0.22	0.25	0.09	0.05	99.94
	sd	0.2	-	0.1	-	-	-	0.3	0.3	0.1	-	-	-	0.2	-	-	-	
CO121B mb	n=6	68.06	0.13	2.67	0.85	0.49	0.94	6.85	16.82	0.89	0.17	0.24	0.95	0.24	0.46	0.19	0.03	99.96
	sd	-	-	-	-	-	-	-	0.1	0.1	-	-	-	-	-	-	-	
CO121B lb	n=4	67.08	0.12	2.67	1.31	0.56	1.06	6.92	16.77	0.90	0.18	0.26	0.95	0.26	0.62	0.28	0.03	99.96
	sd	0.6	-	0.1	0.7	-	0.1	0.1	-	-	-	-	-	-	-	-	-	
*CO121B	n=13	68.06	0.15	2.82	1.00	0.45	0.96	6.47	16.89	0.91	0.16	0.23	0.91	0.24	0.46	0.19	0.04	99.95
	sd	0.9	-	0.3	0.4	0.1	0.1	0.7	0.2	-	-	-	-	0.1	-	0.1	-	
CO121C	n=8	68.28	0.10	2.61	0.80	0.60	0.79	6.63	17.24	0.65	0.15	0.27	1.09	0.19	0.36	0.21	0.05	99.99
	sd	0.2	-	-	-	-	-	-	0.1	0.2	-	-	-	-	-	-	-	
CO121D	n=7	66.81	0.13	2.49	1.01	0.82	0.93	6.79	17.33	0.71	0.17	0.32	1.05	0.35	0.58	0.42	0.04	99.96
	sd	0.1	-	-	-	-	-	-	0.1	0.2	-	-	-	-	-	-	-	
CO121E	n=5	67.48	0.11	2.28	0.65	0.38	0.99	6.16	19.45	0.43	0.04	0.34	1.34	bdl	bdl	0.29	bdl	99.95
	sd	0.2	-	-	-	-	-	-	0.2	-	-	-	-	-	-	-	-	
CO122	n=5	67.58	0.08	2.32	0.90	0.61	0.90	6.78	17.42	0.70	0.11	0.34	0.69	0.33	0.28	0.88	0.01	99.93
	sd	0.1	-	-	-	-	-	-	0.1	0.2	-	-	-	0.1	-	-	-	
CO184A	n=5	67.25	0.13	2.62	1.02	0.68	1.07	6.80	17.29	0.82	0.14	0.26	0.69	0.25	0.60	0.28	0.08	99.98
	sd	0.2	-	-	-	-	-	-	-	-	-	-	-	0.1	-	-	-	
CO184B	n=7	67.29	0.11	2.45	0.89	0.73	0.89	6.60	17.82	0.57	0.11	0.31	1.11	0.28	0.49	0.31	0.02	99.97
	sd	0.1	-	-	-	-	-	-	0.1	0.1	-	-	-	-	-	-	-	
CO184C	n=6	66.90	0.13	2.44	0.98	0.75	1.04	6.52	17.93	0.69	0.14	0.29	1.01	0.28	0.53	0.33	0.04	100.00
	sd	0.3	-	-	0.1	-	0.1	0.2	0.1	-	-	-	-	0.1	-	-	-	
CO230 db	n=10	71.49	0.09	2.75	0.65	0.11	0.74	6.67	15.41	0.62	0.09	0.15	0.90	0.05	0.13	0.08	0.03	99.95
	sd	0.2	-	-	-	-	-	-	0.1	-	-	-	-	-	-	-	-	
CO230 lb	n=10	70.51	0.09	2.67	0.62	0.18	0.68	6.66	15.86	0.64	0.10	0.19	0.93	0.09	0.52	0.09	0.14	99.97
	sd	0.5	-	-	-	-	-	-	0.2	0.2	-	-	-	0.1	-	-	-	
*CO230 (av.)	n=20	71.00	0.09	2.71	0.64	0.15	0.71	6.66	15.64	0.63	0.09	0.17	0.91	0.07	0.33	0.08	0.09	99.96
	sd	0.6	-	-	-	-	-	-	0.1	0.3	-	-	-	0.2	-	-	-	

		SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO233A	n=7	69.95	0.27	2.52	0.90	0.18	0.69	9.34	14.51	0.42	0.10	0.08	1.05	bdl	bdl	bdl	bdl	100.01
	sd	0.1	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
CO233B	n=17	68.50	0.15	2.56	1.75	1.15	1.01	6.74	16.19	0.61	0.13	0.28	0.83	0.01	0.02	0.02	bdl	99.95
	sd	0.1	-	-	-	-	-	-	0.1	-	-	-	-	-	-	-	-	-
CO233C	n=16	66.33	0.12	2.43	1.11	0.78	1.00	7.31	17.30	0.78	0.22	0.32	0.88	0.30	0.52	0.47	0.08	99.94
	sd	0.2	-	-	-	-	-	0.1	0.1	-	-	-	-	-	-	-	-	-
CO325 db	n=4	67.10	0.16	2.80	1.10	0.57	1.26	7.09	16.48	0.88	0.17	0.22	0.70	0.28	0.92	0.16	0.09	99.97
	sd	0.1	-	0.3	0.1	-	0.2	0.2	0.2	-	-	-	0.1	-	-	-	-	-
CO325 lb	n=11	66.87	0.14	2.62	0.99	0.56	1.16	7.25	16.51	0.84	0.19	0.25	0.81	0.27	1.14	0.15	0.20	99.97
	sd	0.3	-	-	0.1	-	0.2	0.2	0.1	-	-	-	-	-	0.1	-	0.1	-
*CO325 (av.)	n=15	66.93	0.15	2.67	1.02	0.57	1.19	7.21	16.50	0.85	0.19	0.24	0.78	0.27	1.08	0.15	0.17	99.97
	sd	0.3	-	0.1	0.1	-	0.2	0.2	0.1	-	-	-	-	-	0.1	-	0.1	-
CO365 db	n=7	73.26	0.07	2.98	0.41	0.03	0.56	6.79	14.22	0.54	0.06	0.14	0.78	0.04	0.05	0.02	0.01	99.98
	sd	-	-	-	-	-	-	-	0.1	-	-	-	-	-	-	-	-	-
CO365 lb	n=6	72.33	0.09	3.02	0.54	0.09	0.70	6.80	14.46	0.52	0.07	0.15	0.80	0.05	0.27	0.05	0.08	100.00
	sd	0.4	-	0.1	0.1	-	-	0.1	0.1	-	-	-	-	-	-	-	-	-
*CO365 (av.)	n=13	72.83	0.08	2.99	0.47	0.06	0.63	6.80	14.33	0.53	0.07	0.15	0.79	0.04	0.15	0.03	0.04	99.99
	sd	0.5	-	0.1	0.1	-	-	-	0.1	-	-	-	-	-	0.1	-	-	-
CO366	n=8	69.24	0.11	2.79	0.64	0.33	0.95	7.98	15.77	0.78	0.15	0.19	0.78	0.06	0.12	0.05	0.02	99.96
	sd	0.4	-	-	-	-	-	-	0.4	0.2	-	-	-	-	-	-	-	-
CO368	n=7	72.21	0.07	3.13	0.37	0.01	0.48	6.96	15.18	0.51	0.04	0.12	0.86	bdl	bdl	bdl	bdl	99.94
	sd	0.2	-	-	-	-	-	-	0.1	-	-	-	-	-	-	-	-	-
CO530 db	n=3	68.20	0.09	2.99	0.80	0.31	0.80	7.63	14.79	0.89	0.11	0.12	0.76	0.83	1.37	0.06	0.19	99.93
	sd	0.9	-	-	0.1	0.1	-	0.3	-	-	-	-	-	-	0.4	-	-	-
→CO530 mb	n=7	65.83	0.12	2.77	1.33	0.59	1.00	7.56	14.75	0.85	0.16	0.19	0.73	0.88	2.46	0.05	0.69	99.96
	sd	0.2	-	-	-	-	-	-	0.2	-	-	-	-	-	0.1	-	0.2	-
→ CO530 lb	n=11	65.50	0.12	2.78	1.34	0.60	0.99	7.55	14.90	0.84	0.19	0.19	0.73	0.94	2.64	0.04	0.65	100.02
	sd	0.4	-	-	-	-	-	-	0.1	0.2	-	-	-	-	-	0.2	-	-
CO530 wb	n=5	62.42	0.14	2.70	1.93	0.60	1.00	7.37	14.84	0.80	0.26	0.22	0.72	1.19	4.31	0.03	1.40	99.93
	sd	0.1	-	-	0.4	-	-	0.2	0.2	-	-	-	-	0.2	0.5	-	0.3	-
*CO530 (av.)	n=26	65.67	0.12	2.78	1.33	0.59	1.00	7.56	14.82	0.85	0.18	0.19	0.73	0.91	2.55	0.04	0.67	99.99
	sd	0.2	-	-	-	-	-	-	0.1	-	-	-	-	-	0.1	-	-	-

* Average values must be taken with caution since the volume of each kind of band is not known. For sample CO530 only the bands indicated with the arrows have been used to calculate the average composition since the other types of bands are infrequent.

Table S2. The results achieved by LA-ICP-MS on the glass collection from Comacchio. All values are provided as ppm. Abbreviations: db=dark grey bands; mb=medium grey bands; lb=light grey bands; n=number of measurements.

	CO23A n=4		CO23B n=4		CO24 n=4		CO25 n=5		CO58A n=4		CO58B n=4		CO58C n=6		CO88 n=4	
	av.	s.d.	av.	s.d.	av.	s.d.	av.	av.	av.	s.d.	av.	s.d.	av.	s.d.	av.	s.d.
Li	7.8	1.4	5.3	1.3	6.1	1.7	4.3	1.1	6.1	1.1	5.9	1.8	4.9	0.8	6.1	1.8
Be	4.4	1.1	4.4	1.7	3.6	0.9	3.4	-	1.7	-	-	-	4.2	1.9	1.7	-
B	120	8	55	5	135	14	168	22	104	10	144	10	59	10	104	15
Sc	4.2	0.3	2.6	0.3	3.2	0.1	2.5	0.1	2.5	0.4	3.7	0.3	3.7	0.4	2.5	0.3
Ti	891	21.1	430	28.3	601	48.9	442	21.3	550	44.8	843	74.0	532	32	550	26.3
V	23	1	8	1	18	1	17	1	14	1	24	2	11	1	14	2
Cr	38	4	11	2	24	6	10	1	16	3	22	5	45	7	16	3
Co	23	1	1	-	277	39	5	1	16	2	37	-	15	2	16	1
Ni	30	3	3	1	29	4	6	1	11	-	18	1	123	18	11	1
Cu	885	21	5	1	2133	324	24	6	1561	13	1124	26	105	12	1561	147
Zn	102	3	5	1	59	2	9	1	186	41	142	12	37	5	186	23
Ga	3.4	0.4	3.0	0.2	3.4	0.2	1.9	0.1	2.4	0.3	2.9	0.1	3.2	0.3	2.4	0.4
Ge	1.0	-	0.7	0.2	1.5	0.3	1.1	0.5	0.8	0.2	1.3	0.3	1.4	0.8	0.8	0.1
As	11.9	0.6	1.0	0.4	31.0	6.2	6.5	0.3	19.3	2.0	25.6	3.7	2.3	0.5	19.3	3.0
Rb	10.7	0.4	9.2	0.3	8.7	0.9	4.8	0.3	14.3	0.3	12.5	0.2	17.9	1.1	14.3	4.5
Sr	536	9	324	12	501	14	423	6	429	12	517	7	268	26	429	16
Y	8.3	0.5	5.8	0.3	7.7	0.4	5.3	0.3	6.1	0.5	7.5	0.3	6.4	0.3	6.1	0.4
Zr	87.9	3.7	38.8	1.8	61.4	3.9	42.3	1.2	51.2	3.9	76.1	6.8	50.4	2.5	51.2	2.9
Nb	2.48	0.30	1.51	0.18	1.93	0.22	1.34	0.08	2.02	0.19	2.60	0.55	1.69	0.20	2.02	0.84
Mo	1.80	0.41	0.35	0.06	2.00	0.43	0.45	0.24	0.84	0.26	1.91	0.24	0.32	0.05	0.84	0.18
Ag	1.46	0.27	1.91	2.65	1.69	0.19	0.15	0.10	4.48	0.07	0.05	0.03	0.45	0.12	4.48	0.79
Cd	-	-	-	-	0.48	0.1	0.39	0.1	0.36	-	0.65	0.1	0.22	0.08	0.36	-
In	2.00	0.09	0.04	-	0.90	0.22	0.02	-	8.69	0.22	2.55	0.23	0.69	0.09	8.69	0.70
Sn	521	46	2	-	178	51	2	-	2201	42	668	33	183	27	2201	168
Sb	924	69	1	-	6991	354	228	2	1608	121	2645	553	42	7	1608	220
Cs	0.165	0.045	0.092	0.014	0.168	0.032	0.057	0.01	0.219	0.023	0.209	0.016	0.417	0.066	0.219	0.032
Ba	313	5	206	7	259	14	400	5	204	3	294	6	145	11	204	10
La	8.043	0.260	5.702	0.234	7.357	0.261	5.448	0.13	6.622	0.242	7.998	0.391	5.670	0.309	6.622	0.506
Ce	13.669	0.433	11.112	0.392	12.861	0.189	9.462	0.436	13.171	0.190	13.551	0.325	11.212	0.652	13.171	5.129
Pr	1.778	0.075	1.341	0.022	1.542	0.098	1.126	0.011	1.291	0.126	1.697	0.096	1.391	0.117	1.291	0.100
Nd	8.119	0.950	5.887	0.350	7.035	0.413	4.886	0.095	5.806	0.294	7.063	0.225	5.663	0.427	5.806	0.545
Sm	1.617	0.337	1.164	0.155	1.551	0.537	1.019	0.160	1.334	0.260	1.582	0.277	1.310	0.325	1.334	0.242
Eu	0.484	0.080	0.398	0.061	0.351	0.071	0.254	0.085	0.357	0.102	0.484	0.063	0.360	0.061	0.357	0.043
Gd	1.310	0.294	0.992	0.065	1.390	0.155	0.818	0.132	1.173	0.353	1.329	0.177	0.990	0.177	1.173	0.139
Tb	0.232	0.027	0.169	0.026	0.209	0.021	0.140	0.028	0.163	0.043	0.210	0.023	0.176	0.035	0.163	0.030
Dy	1.300	0.368	0.906	0.149	1.375	0.236	0.927	0.107	1.265	0.308	1.301	0.132	0.906	0.083	1.265	0.168
Ho	0.305	0.032	0.183	0.023	0.276	0.025	0.193	0.041	0.221	0.025	0.268	0.044	0.217	0.042	0.221	0.030
Er	0.709	0.095	0.445	0.067	0.724	0.071	0.405	0.075	0.721	0.159	0.723	0.116	0.684	0.045	0.721	0.107
Tm	0.096	0.019	0.078	0.025	0.105	0.030	0.101	0.022	0.079	0.029	0.110	0.028	0.072	0.016	0.079	0.026
Yb	0.658	0.208	0.500	0.179	0.920	0.122	0.481	0.187	0.611	0.066	0.714	0.240	0.625	0.084	0.611	0.103
Lu	0.149	0.018	0.071	0.035	0.085	0.026	0.071	0.018	0.099	0.020	0.122	0.033	0.075	0.021	0.099	0.031
Hf	2.350	0.216	0.999	0.255	1.548	0.201	1.192	0.200	1.417	0.373	1.810	0.227	1.313	0.259	1.417	0.273
Ta	0.141	0.042	0.076	0.017	0.137	0.024	0.066	0.020	0.100	0.033	0.117	0.020	0.104	0.024	0.100	0.047
W	0.442	0.092	0.131	-	0.514	0.104	0.136	0.103	0.372	0.090	0.745	0.136	0.131	0.083	0.372	0.098
Au	0.425	0.097	0.029	0.016	0.987	0.482	0.039	0.001	6.675	0.088	0.680	0.166	0.313	0.183	6.675	0.752
Tl	0.064	0.022	0.024	-	0.089	0.054	0.020	0.014	0.196	0.004	0.081	0.035	-	-	0.196	0.034
Pb	4076	83	6	-	3381	1193	16	2	14546	117	6528	630	295	41	14546	1818
Bi	0.417	0.154	0.044	0.014	0.308	0.123	0.035	-	4.616	0.028	0.619	0.116	0.139	0.058	4.616	1.343
Th	1.446	0.093	0.737	0.082	1.220	0.145	0.760	0.132	1.008	0.107	1.311	0.028	0.948	0.094	1.008	0.074
U	1.100	0.060	0.671	0.131	1.062	0.052	0.780	0.047	0.907	0.171	1.118	0.037	0.868	0.105	0.907	0.076

(continued)

	CO92		CO93		CO94		CO95		CO96		CO99		CO100A db		CO100A lb	
	n=5		n=4		n=3		n=4		n=4		n=4		n=4		n=3	
	av.	s.d.	av.	s.d.	av.	s.d.										
Li	6.0	1.1	5.5	0.7	4.8	1.4	3.6	0.9	6.8	1.9	4.0	2.3	7.0	1.3	5.7	1.6
Be	3.5	1.2	3.0	-	-	-	1.7	0.1	-	-	2.5	1.4	1.9	1.3	-	-
B	148	13	138	19	79	8	155	12	144	11	225	7	92	13	98	7
Sc	4.2	0.4	4.4	0.5	2.3	0.3	3.5	0.4	3.1	0.2	7.1	0.3	4.6	0.3	4.9	0.4
Ti	1058	20	735	33.5	369	15	937	10.0	875	27.3	3383	59.8	828	58.0	884	16
V	29	-	20	-	7	1	25	1	24	-	59	1	19	1	19	-
Cr	24	3	24	1	14	2	22	1	23	3	70	2	24	4	26	5
Co	71	2	33	3	1	-	29	4	43	2	16	-	24	4	35	8
Ni	28	1	16	1	5	1	15	0	23	3	17	1	48	56	27	7
Cu	3180	46	1742	56	12	1	1805	33	2579	100	84	2	1950	413	2663	150
Zn	589	33	78	9	6	2	73	5	187	41	30	1	170	76	341	178
Ga	3.6	0.2	3.2	0.2	2.7	0.1	3.0	0.3	3.2	0.1	4.5	0.4	3.4	0.5	3.2	0.4
Ge	1.6	0.3	1.9	-	1.1	-	1.4	0.5	1.3	0.1	1.9	0.2	1.2	0.3	1.5	-
As	40.5	1.8	21.4	0.7	1.0	-	20.1	0.9	22.9	3.6	11.5	0.7	17.1	8.7	43.7	26.6
Rb	10.8	0.4	13.3	0.7	7.9	0.2	9.4	0.3	12.6	1.1	5.4	0.3	15.1	1.4	12.5	0.2
Sr	605	5	498	7	353	8	500	2	528	8	417	6	438	10	432	9
Y	8.5	0.4	6.6	0.5	5.4	0.2	8.0	0.2	7.8	0.3	12.9	0.5	7.7	0.2	7.5	-
Zr	100.0	8.8	68.9	3.4	37.6	1.4	92.6	1.5	83.4	2.4	297.7	1.2	70.3	3.4	74.0	2.2
Nb	2.85	0.06	2.15	0.08	1.32	0.1	2.30	0.11	2.45	0.08	5.99	0.25	2.29	0.25	2.36	0.1
Mo	2.25	0.28	1.62	0.26	0.23	0.03	1.96	0.29	2.44	0.37	3.70	0.63	1.15	0.26	1.17	0.04
Ag	9.24	0.37	2.01	0.20	-	-	1.95	0.18	2.87	0.16	0.06	-	1.71	0.51	2.37	0.26
Cd	-	-	-	-	0.92	-	0.54	0.3	0.10	-	0.36	-	0.12	-	0.96	0.26
In	9.13	0.38	2.72	0.14	0.03	0.01	1.45	0.10	3.49	0.57	0.04	0.02	3.37	1.97	10.85	7.19
Sn	2875	26	706	30	2	-	381	23	896	156	1	-	862	509	2855	1956
Sb	3402	127	1788	144	0.5	-	1745	27	1263	43	0.5	-	961	149.5	976	18.7
Cs	0.200	0.035	0.214	0.047	0.076	0.027	0.146	0.029	0.119	0.013	0.126	0.006	0.213	0.061	0.188	0.041
Ba	330	5	264	10	178	2.823	321	4	305	9	842	3	261	8	257	1.934
La	8.651	0.254	6.738	0.462	5.573	0.228	7.916	0.165	8.050	0.097	12.039	0.426	7.375	0.282	7.427	0.297
Ce	14.659	0.217	11.675	0.580	10.433	0.523	13.122	0.390	13.404	0.269	19.656	0.524	13.585	0.688	13.242	0.469
Pr	1.894	0.086	1.451	0.068	1.236	0.035	1.614	0.054	1.732	0.139	2.730	0.102	1.637	0.095	1.796	0.061
Nd	7.979	0.346	6.096	0.679	5.368	0.210	7.363	0.117	7.580	0.478	10.666	0.331	6.916	0.553	7.011	0.327
Sm	1.601	0.102	1.222	0.235	1.119	0.044	1.751	0.134	1.559	0.350	2.352	0.331	1.418	0.411	1.552	0.392
Eu	0.433	0.051	0.315	0.063	0.316	0.030	0.391	0.040	0.411	0.093	0.634	0.065	0.355	0.073	0.441	0.022
Gd	1.599	0.265	1.166	0.175	0.981	0.146	1.426	0.301	1.401	0.245	2.148	0.217	1.067	0.136	1.411	0.205
Tb	0.248	0.029	0.174	0.040	0.148	0.033	0.228	0.028	0.202	0.032	0.391	0.038	0.220	0.037	0.200	0.057
Dy	1.442	0.241	1.116	0.051	0.981	0.091	1.152	0.263	1.436	0.238	2.251	0.151	1.313	0.096	1.364	0.035
Ho	0.302	0.018	0.215	0.041	0.209	0.050	0.312	0.033	0.310	0.054	0.475	0.038	0.279	0.043	0.281	0.053
Er	0.844	0.156	0.551	0.116	0.542	0.098	0.749	0.138	0.777	0.060	1.360	0.209	0.584	0.094	0.739	0.063
Tm	0.130	0.020	0.069	0.023	0.077	0.012	0.104	0.032	0.109	0.013	0.206	0.023	0.102	0.021	0.102	0.017
Yb	0.764	0.159	0.798	0.234	0.482	0.305	0.771	0.157	0.698	0.168	1.450	0.090	0.681	0.140	0.594	0.217
Lu	0.101	0.021	0.094	0.010	0.088	0.023	0.103	0.018	0.132	0.023	0.213	0.014	0.091	0.018	0.091	0.011
Hf	2.425	0.254	1.763	0.359	0.957	0.076	2.202	0.447	2.336	0.108	7.013	0.357	1.725	0.073	2.061	0.086
Ta	0.177	0.027	0.153	0.035	0.082	0.018	0.184	0.018	0.137	0.027	0.389	0.038	0.101	0.030	0.145	0.012
W	0.441	0.106	0.586	0.188	0.087	0.055	0.864	0.136	0.765	0.259	1.102	0.062	0.347	0.107	0.324	0.105
Au	2.754	0.277	0.879	0.258	-	-	0.398	0.067	1.139	0.418	0.045	0.014	0.734	0.127	0.804	0.143
Tl	0.248	0.054	0.072	0.027	0.062	-	0.084	0.036	0.086	0.036	-	-	0.076	0.028	0.133	0.011
Pb	17683	383	4578	303	13	1	4603	58	5929	1217	8	1	4949	2031	10160	5040
Bi	3.413	0.320	0.441	0.109	-	-	0.338	0.027	0.625	0.039	0.074	0.047	0.509	0.101	0.707	0.313
Th	1.434	0.081	1.133	0.111	0.728	0.010	1.411	0.117	1.393	0.029	2.465	0.049	1.171	0.088	1.181	0.127
U	1.246	0.058	0.980	0.110	0.602	0.092	1.007	0.019	1.011	0.043	1.270	0.032	1.094	0.078	1.113	0.082

(continued)

	CO100B n=4		CO121A n=4		CO121B n=3		CO121C n=4		CO121D n=4		CO121E n=4		CO122 n=3		CO184A n=3	
	av.	s.d.	av.	s.d.	av.	s.d.										
Li	3.6	1.4	8.1	1.2	7.1	3.2	5.1	2.1	6.2	2.3	4.1	0.2	4.9	2.4	5.2	1.1
Be	3.6	3.2	1.3	-	-	-	-	-	4.6	-	2.7	1.4	-	-	-	-
B	129	10	141	7	147	10	141	14	168	16	166	12	152	19	143	4
Sc	2.6	0.4	3.0	0.3	3.0	0.3	2.7	0.4	3.1	0.4	2.6	0.4	2.6	0.4	3.3	0.1
Ti	616	11.6	899	43	757	65	634	18	781	34	567	5	615	91	847	13
V	20	1	24	-	19	3	17	1	23	1	16	-	18	2	23	1
Cr	19	1	25	3	25	5	16	2	20	4	10	2	22	5	30	2
Co	19	1	26	2	24	4	14	1	40	1	4	-	275	11	41	1
Ni	20	2	19	2	16	3	11	1	16	2	8	1	27	4	23	2
Cu	1548	57	1233	27	1882	105	1491	34	2550	55	15	-	2482	167	1908	49
Zn	33	1	72	9	81	14	57	6	92	5	20	3	71	7	166	9
Ga	2.5	0.3	2.9	0.3	3.0	0.1	2.6	0.2	2.8	0.1	2.6	0.3	3.4	0.1	3.3	0.5
Ge	1.2	0.4	1.4	0.8	1.2	0.4	1.2	0.3	1.1	0.5	1.2	0.2	1.7	0.2	1.5	1.0
As	18.1	0.6	15.7	0.5	15.5	1.0	15.4	1.8	24.7	1.8	23.1	1.6	24.2	5.8	22.0	1.2
Rb	7.8	0.2	9.0	0.3	11.7	2.4	8.8	0.4	9.2	0.2	5.0	0.5	11.0	0.3	12.1	0.5
Sr	428	3	462	7	443	13	436	13	482	3	424	3	473	20	459	1
Y	6.0	0.1	7.2	0.4	7.3	0.6	6.6	0.6	7.2	0.4	6.3	-	6.9	0.3	7.3	0.4
Zr	55.6	2.1	80.5	5.8	65.7	3.5	57.9	1.5	73.5	2.0	53.7	1.0	79.0	41.5	75.0	1.0
Nb	1.76	0.10	2.22	0.12	2.14	0.25	1.74	0.08	2.14	0.16	1.79	0.08	1.76	0.17	2.29	0.17
Mo	1.63	0.30	2.11	0.38	1.31	0.30	1.45	0.13	2.00	0.31	0.46	0.06	2.02	0.16	1.51	0.18
Ag	2.05	0.32	1.27	0.10	1.77	0.44	1.18	0.23	6.62	0.29	0.06	-	1.26	0.18	1.82	0.20
Cd	-	-	-	-	0.46	-	0.34	0.09	0.26	-	-	-	0.14	-	-	-
In	0.75	0.05	2.28	0.63	1.71	0.15	1.16	0.34	1.64	0.17	0.04	-	0.92	0.19	2.67	0.01
Sn	192	17	575	180	444	35	305	83	417	34	2	-	182	46	670	39
Sb	1404	42.8	1189	84	1389	76	1516	108	2819	69	2019	28	6345	1382	1906	26
Cs	0.168	0.019	0.165	0.048	0.208	0.065	0.178	0.053	0.178	0.043	0.072	0.022	0.152	0.051	0.213	0.039
Ba	260	6	312	2	253	7	278	15	288	5	177	3	226	5	278	5
La	6.011	0.123	7.141	0.324	7.181	0.804	6.896	0.158	7.259	0.323	6.623	0.129	6.684	0.087	7.273	0.137
Ce	11.069	0.285	12.424	0.175	12.849	0.929	11.596	0.579	11.986	0.370	11.188	0.186	11.486	0.257	12.542	0.328
Pr	1.350	0.129	1.646	0.037	1.562	0.144	1.465	0.034	1.546	0.094	1.419	0.063	1.481	0.118	1.679	0.105
Nd	5.625	0.657	7.217	0.609	7.114	0.381	6.240	0.273	6.156	0.171	6.455	0.547	6.313	0.493	6.988	0.659
Sm	1.034	0.101	1.621	0.220	1.459	0.214	1.184	0.196	1.259	0.141	1.250	0.289	1.204	0.318	1.123	0.055
Eu	0.236	0.034	0.438	0.053	0.396	0.038	0.315	0.062	0.363	0.048	0.318	0.067	0.349	0.057	0.313	0.037
Gd	1.061	0.122	1.456	0.356	1.192	0.070	1.106	0.239	1.209	0.162	1.045	0.246	1.092	0.211	1.425	0.258
Tb	0.136	0.007	0.208	0.057	0.173	0.037	0.187	0.029	0.185	0.037	0.156	0.019	0.189	0.046	0.222	0.016
Dy	0.983	0.143	1.295	0.181	1.198	0.137	1.142	0.407	1.246	0.247	1.132	0.015	1.173	0.071	1.197	0.063
Ho	0.195	0.015	0.285	0.049	0.240	0.005	0.243	0.031	0.226	0.052	0.207	0.030	0.274	0.014	0.280	0.049
Er	0.510	0.110	0.699	0.154	0.818	0.146	0.689	0.081	0.657	0.063	0.657	0.055	0.613	0.203	0.726	0.003
Tm	0.081	0.024	0.110	0.025	0.110	0.020	0.086	0.023	0.095	0.008	0.074	0.022	0.089	0.019	0.109	0.024
Yb	0.543	0.121	0.736	0.147	0.568	0.285	0.617	0.107	0.574	0.221	0.601	0.297	0.640	0.174	0.753	0.279
Lu	0.063	0.015	0.110	0.017	0.083	0.056	0.093	0.016	0.098	0.009	0.078	0.033	0.124	0.006	0.109	0.050
Hf	1.413	0.162	1.878	0.086	1.629	0.525	1.596	0.055	1.710	0.280	1.170	0.441	2.139	1.170	2.092	0.156
Ta	0.116	0.020	0.117	0.004	0.150	0.036	0.124	0.051	0.127	0.032	0.087	0.011	0.094	0.005	0.121	0.024
W	0.605	0.111	0.568	0.105	0.758	0.098	0.802	0.262	0.929	0.265	0.152	0.054	0.394	0.032	0.737	0.010
Au	1.518	0.154	0.525	0.073	1.046	0.182	0.693	0.176	0.981	0.132	0.301	-	0.477	0.147	1.287	0.188
Tl	0.055	0.005	0.071	0.024	0.054	0.029	0.076	0.022	0.075	0.017	0.030	0.019	0.049	0.027	0.054	0.032
Pb	2700	262	3344	241	4083	530	3395	334	4635	176	22	1	2435	320	5311	106
Bi	0.231	0.015	0.193	0.029	0.278	0.089	1.254	1.508	0.338	0.069	0.080	0.014	0.317	0.052	0.556	0.025
Th	0.868	0.100	1.204	0.059	1.318	0.097	1.194	0.041	1.232	0.133	0.970	0.065	1.153	0.058	1.248	0.054
U	0.916	0.105	0.972	0.170	0.966	0.067	1.050	0.047	0.967	0.098	0.810	0.068	0.942	0.018	0.922	0.094

(continued)

	CO184B		CO184C		CO230		CO233A		CO233B		CO233C		CO325		CO365	
	n=4		n=4		n=4		n=4		n=3		n=4		n=4		n=5	
	av.	s.d.														
Li	4.2	1.2	4.8	2.0	4.7	2.5	3.9	1.0	7.6	1.6	6.2	0.7	6.3	2.6	5.1	1.7
Be	-	-	3.1	-	4.8	-	3.5	-	-	-	4.7	4.3	-	-	-	-
B	156	8	158	17	96	16	99	11	172	16	179	9	129	13	195	330
Sc	2.7	0.4	2.9	0.3	2.7	0.2	3.7	0.4	3.3	0.2	3.2	0.2	3.0	0.3	3.0	0.3
Ti	667	82	786	19	544	19	1536	24	824	16	741	43	780	50	436	17
V	19	3	22	1	11	1	21	-	31	2	22	1	21	1	9	1
Cr	18	1	23	4	24	6	27	4	15	2	21	2	23	7	17	4
Co	24	4	47	4	8	1	6	-	8	-	442	15	27	9	2	1
Ni	12	1	18	3	14	4	7	-	18	3	64	1	25	7	5	1
Cu	2098	272	2057	41	607	39	25	1	48	3	2099	61	1986	104	205	91
Zn	58	9	114	19	194	121	29	4	25	2	87	4	267	84	19	2
Ga	2.7	0.3	3.0	0.3	2.7	0.4	3.1	0.1	3.0	0.2	4.0	0.2	2.9	0.4	2.9	0.3
Ge	1.5	0.6	0.8	0.1	1.6	0.5	1.9	0.3	0.9	0.4	2.7	0.9	1.2	0.5	1.1	0.2
As	21.9	2.7	26.7	3.0	10.7	6.0	1.0	0.2	14.8	0.8	25.0	3.4	15.6	5.1	2.3	0.6
Rb	11.5	5.4	8.3	0.3	9.2	0.5	5.9	0.6	7.4	0.3	9.0	0.5	10.1	1.4	9.2	0.2
Sr	455	16	458	2	405	10	176	5	612	0	543	18	513	18	380	10
Y	6.4	1.0	7.1	0.1	6.4	0.2	6.4	0.2	9.7	0.4	7.2	0.4	7.1	0.1	6.3	0.2
Zr	64.0	2.1	72.1	1.3	50.1	0.7	176.7	3.7	82.4	0.8	71.6	2.5	71.9	3.4	42.7	1.6
Nb	1.93	0.19	2.06	0.09	1.64	0.20	3.46	0.18	2.51	0.04	2.01	0.16	2.20	0.22	1.41	0.19
Mo	1.57	0.25	1.95	0.23	0.59	0.31	0.38	0.15	1.79	0.22	3.27	0.30	1.45	0.19	0.34	0.10
Ag	1.66	0.39	2.17	0.15	1.00	0.31	0.15	0.04	0.08	0.04	1.16	0.16	3.07	0.38	0.48	0.11
Cd	0.59	0.22	0.37	0.11	0.61	0.07	0.44	-	-	-	0.62	-	0.55	-	-	-
In	1.08	0.09	1.75	0.48	3.35	1.20	0.04	0.01	0.03	0.01	2.60	0.18	4.61	0.91	0.50	0.25
Sn	261	13	421	82	874	286	4	1	5	-	523	43	1203	250	137	75
Sb	2196	249	2343	293	209	78	14	4	101	1	3349	67	718	210	73	47
Cs	0.221	0.040	0.129	0.011	0.138	0.031	0.074	0.015	0.092	0.035	0.158	0.028	0.133	0.051	0.115	0.041
Ba	273	22	289	2	202	4	167	5	369	10	244	7	249	6	219	4
La	6.364	1.041	6.778	0.079	6.047	0.183	6.664	0.218	11.056	0.107	7.230	0.212	7.005	0.187	6.173	0.133
Ce	11.311	0.872	11.733	0.275	10.920	0.447	13.193	0.196	13.459	0.371	12.796	0.502	12.273	0.374	11.228	0.212
Pr	1.483	0.113	1.533	0.077	1.385	0.144	1.549	0.061	2.263	0.102	1.474	0.056	1.473	0.072	1.418	0.045
Nd	6.133	1.361	6.392	0.239	6.278	1.048	6.581	0.339	10.089	0.148	6.658	0.176	6.719	0.463	5.593	0.345
Sm	1.199	0.420	1.302	0.181	1.199	0.103	1.311	0.177	2.203	0.215	1.254	0.311	1.522	0.337	1.188	0.337
Eu	0.341	0.058	0.344	0.083	0.382	0.089	0.291	0.054	0.593	0.034	0.413	0.031	0.373	0.076	0.382	0.059
Gd	1.129	0.165	1.237	0.152	1.227	0.308	1.062	0.128	1.842	0.180	1.270	0.215	1.243	0.226	1.043	0.231
Tb	0.181	0.079	0.185	0.036	0.161	0.015	0.149	0.051	0.286	0.025	0.199	0.015	0.193	0.038	0.168	0.037
Dy	1.139	0.134	1.101	0.136	1.096	0.291	1.200	0.026	1.752	0.262	1.184	0.147	1.174	0.181	1.113	0.175
Ho	0.224	0.058	0.236	0.040	0.208	0.036	0.220	0.030	0.394	0.068	0.234	0.040	0.248	0.015	0.226	0.022
Er	0.708	0.195	0.655	0.233	0.587	0.148	0.652	0.090	0.993	0.154	0.604	0.148	0.787	0.181	0.728	0.174
Tm	0.094	0.022	0.082	0.033	0.082	0.015	0.099	0.026	0.134	0.011	0.090	0.011	0.099	0.022	0.073	0.002
Yb	0.489	0.235	0.704	0.103	0.580	0.220	0.750	0.255	1.123	0.044	0.589	0.270	0.653	0.232	0.694	0.070
Lu	0.085	0.019	0.124	0.025	0.090	0.014	0.112	0.017	0.127	0.030	0.099	0.041	0.113	0.030	0.086	0.031
Hf	1.895	0.301	1.661	0.186	1.139	0.261	4.169	0.542	1.815	0.020	1.714	0.127	1.675	0.188	1.113	0.107
Ta	0.152	0.062	0.142	0.030	0.112	0.011	0.230	0.034	0.125	0.021	0.136	0.031	0.126	0.021	0.086	0.025
W	0.674	0.100	0.675	0.084	0.192	0.115	0.139	0.058	0.381	0.058	0.216	0.095	0.292	0.050	0.140	0.016
Au	1.254	0.289	0.884	0.274	0.332	0.243	0.061	-	0.014	-	0.148	0.050	0.673	0.057	0.111	0.053
Tl	0.092	0.028	0.065	0.038	0.087	0.035	0.036	0.006	0.059	0.033	0.079	0.011	0.113	0.071	0.027	0.004
Pb	4389	415	4725	748	3504	493	44	6	80	1	4264	220	9245	580	650	177
Bi	0.289	0.082	0.416	0.024	0.820	0.250	0.038	0.005	0.058	0.018	0.512	0.057	1.682	0.318	0.175	0.173
Th	1.054	0.154	1.169	0.105	0.962	0.070	1.405	0.146	1.311	0.053	1.294	0.108	1.208	0.098	0.861	0.074
U	0.922	0.012	0.961	0.145	0.894	0.081	1.011	0.023	1.330	0.065	1.053	0.120	0.916	0.052	0.831	0.100

(continued)

	CO366		CO368		CO530 db		CO530 lb	
	n=4		n=3		n=3		n=3	
	av.	s.d.	av.	s.d.	av.	s.d.	av.	s.d.
Li	3.9	1.3	3.3	1.4	4.6	1.8	5.4	2.4
Be	3.2	-	1.9	0.8	4.0	-	-	-
B	99	8	44	13	109	20	100	5
Sc	2.6	0.3	2.8	0.1	3.0	0.2	3.2	0.2
Ti	555	24	376	17	721	15	717	53
V	14	1	8	1	21	-	21	1
Cr	17	3	10	4	17	1	18	-
Co	9	-	1	-	70	1	73	10
Ni	9	1	3	-	155	3	170	32
Cu	348	47	3	-	7185	60	8093	739
Zn	43	3	3	-	2319	2	2566	533
Ga	2.9	0.3	3.1	0.3	3.5	0.3	2.9	0.1
Ge	0.7	-	1.2	0.5	1.3	0.4	1.3	0.4
As	4.0	0.6	1.2	0.2	115.1	3.6	141.9	53.3
Rb	8.6	0.3	8.8	0.5	9.0	0.3	8.8	0.3
Sr	443	8	369	6	538	1	527	9
Y	5.9	0.1	5.4	0.5	7.4	0.2	7.6	0.3
Zr	51.8	1.2	32.4	0.8	61.0	1.3	62.1	3.0
Nb	1.66	0.15	1.27	0.08	2.18	0.13	2.14	0.13
Mo	0.86	0.15	0.42	0.18	1.84	0.46	1.80	0.15
Ag	0.70	0.14	0.03	-	2.45	0.15	3.97	2.62
Cd	0.28	-	0.41	-	0.70	0.31	0.39	0.20
In	0.70	0.07	0.02	0.01	22.60	0.17	24.34	4.91
Sn	196	9	1	-	5882	48	9527	1841
Sb	273	5	0.3	-	238	2	258	37
Cs	0.147	0.039	0.101	0.016	0.176	0.008	0.164	0.020
Ba	217	3	218	8	249	2	244	3
La	5.930	0.329	5.563	0.166	7.187	0.264	6.975	0.208
Ce	11.024	0.189	11.261	0.592	12.720	0.256	12.142	0.598
Pr	1.376	0.163	1.374	0.111	1.622	0.033	1.550	0.077
Nd	5.754	0.542	5.258	0.387	7.462	0.447	6.857	0.336
Sm	1.022	0.171	1.227	0.359	1.485	0.191	1.546	0.060
Eu	0.326	0.126	0.299	0.018	0.424	0.038	0.459	0.023
Gd	0.911	0.184	1.029	0.275	1.482	0.232	1.298	0.141
Tb	0.172	0.027	0.141	0.027	0.234	0.003	0.200	0.044
Dy	0.850	0.081	0.998	0.203	1.552	0.058	1.416	0.086
Ho	0.212	0.016	0.183	0.027	0.277	0.075	0.245	0.019
Er	0.591	0.161	0.640	0.104	0.653	0.043	0.833	0.135
Tm	0.066	0.033	0.069	0.024	0.109	0.030	0.087	0.024
Yb	0.564	0.130	0.571	0.132	0.698	0.020	0.652	0.045
Lu	0.091	0.027	0.078	0.033	0.115	0.018	0.098	0.013
Hf	1.346	0.117	0.734	0.119	1.626	0.236	1.537	0.497
Ta	0.109	0.014	0.088	0.024	0.122	0.022	0.149	0.014
W	0.133	0.043	0.132	0.075	0.408	0.123	1.184	1.091
Au	0.196	0.039	0.052	-	0.074	0.017	0.071	-
Tl	0.028	0.001	0.014	-	0.284	0.037	0.289	0.022
Pb	893	21	5	-	23916	109	39421	6628
Bi	0.180	0.012	0.025	-	1.888	0.064	2.167	0.423
Th	0.882	0.094	0.631	0.148	1.059	0.089	1.069	0.042
U	0.911	0.069	0.736	0.075	0.938	0.082	0.929	0.047

Table S3. Sr, Nd isotopic results on Comacchio blocks.

Sample	Rb ppm	Sr ppm	Nd ppm	Sm ppm	CaO/Sr	$^{87}\text{Sr}/^{86}\text{Sr}$	2se	$^{143}\text{Nd}/^{144}\text{Nd}$	2se	ϵNd	2se
CO24	8.7	501	7.04	1.55	132	0.708895	± 0.000005	0.512371	± 0.000005	-5.204	± 0.09
CO121E	5.0	424	6.46	1.25	145	0.708819	± 0.000005	0.512357	± 0.000006	-5.482	± 0.11
CO122	11	473	6.31	1.20	143	0.708917	± 0.000004	0.512366	± 0.000006	-5.301	± 0.11
CO100B	7.8	428	5.63	1.03	151	0.708863	± 0.000005	0.512375	± 0.000006	-5.137	± 0.11
CO58A	10.8	411	6.58	1.22	157	0.708943	± 0.000005	0.512399	± 0.000004	-4.655	± 0.08
Standard						$^{87}\text{Sr}/^{86}\text{Sr}$	2se	$^{143}\text{Nd}/^{144}\text{Nd}$	2se		
G2	<i>Within-run standard</i>					0.709777	± 0.000006	0.512219	± 0.000007		
Weiss et al. 2008						$^{87}\text{Sr}/^{86}\text{Sr}$	2sd	$^{143}\text{Nd}/^{144}\text{Nd}$	2sd	n	
						0.709770	± 0.000014	0.512222	± 0.000006	7	
SRM987	<i>Within-run international and internal standard</i>					$^{87}\text{Sr}/^{86}\text{Sr}$	2se				
SRM987	<i>Within-run international and internal standard</i>					0.710264	± 0.000006				
<i>average value</i>						0.710261	± 0.000005				
<i>Reference value</i>	Thilwall 1989					$^{87}\text{Sr}/^{86}\text{Sr}$	2sd			n	
						0.710263	± 0.000004			2	
						0.710248	± 0.000011			428	
NdFi	<i>Within-run international and internal standard</i>							$^{143}\text{Nd}/^{144}\text{Nd}$	2se		
NdFi	<i>Within-run international and internal standard</i>							0.511462	± 0.000006		
<i>average value</i>								0.511465	± 0.000004		
Avanzinelli et al. 2004	<i>Long term reproducibility</i>							$^{143}\text{Nd}/^{144}\text{Nd}$	2sd	n	
								0.511463	± 0.000005	2	
								0.511468	± 0.000009	58	

Samples preparation and isotopic measurements have been performed at the DST-UNIFI laboratory of Geochemistry of Radiogenic Isotopes . 2se= two standard error of the mean; 2sd= two standard deviation; n= number of analysis. ϵNd is calculated as $^{143}\text{Nd}/^{144}\text{Nd}$ of the sample/0.512638 -1 *10000, where the value 0.512638 is the CHUR ‘chondritic uniform reservoir’ of Jacobson and Wasserburg (1980).

Table S4. EMPA full dataset. All values in wt%.

	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO23A-db1	67.75	0.15	2.68	0.91	0.85	1.17	7.40	16.45	0.84	0.16	0.26	0.83	0.12	0.40	0.13	0.00	100.09
CO23A-db2	67.62	0.13	2.69	0.98	0.73	1.10	7.19	16.81	0.91	0.13	0.24	0.82	0.10	0.40	0.13	0.00	99.98
CO23A-db3	67.49	0.14	2.69	0.98	0.70	1.20	7.48	16.49	0.88	0.19	0.27	0.81	0.12	0.41	0.15	0.00	100.00
CO23A-db4	67.57	0.15	2.71	0.87	0.72	1.10	7.48	16.67	0.87	0.18	0.25	0.80	0.11	0.43	0.10	0.00	100.01
CO23A-mb1	67.41	0.10	2.69	1.06	0.68	1.24	7.18	16.71	0.88	0.19	0.25	0.77	0.16	0.43	0.13	0.05	99.92
CO23A-mb2	67.43	0.11	2.55	0.99	0.76	1.21	7.46	16.57	0.90	0.15	0.28	0.75	0.12	0.50	0.13	0.09	100.01
CO23A-mb3	67.46	0.17	2.69	0.86	0.69	1.04	7.27	16.86	0.95	0.18	0.24	0.79	0.11	0.43	0.15	0.07	99.97
CO23A-mb4	67.47	0.08	2.58	0.87	0.70	1.11	7.26	16.98	0.96	0.18	0.27	0.75	0.12	0.44	0.14	0.00	99.91
CO23A-mb5	67.70	0.16	2.78	0.94	0.70	1.14	7.34	16.43	0.95	0.11	0.24	0.82	0.14	0.45	0.08	0.00	99.98
CO23A-mb6	67.60	0.15	2.58	1.00	0.69	1.03	7.15	16.88	0.91	0.14	0.25	0.83	0.10	0.45	0.16	0.04	99.96
CO23A-mb7	67.04	0.15	2.63	1.04	0.86	1.10	7.67	16.56	0.91	0.20	0.26	0.77	0.11	0.50	0.12	0.15	100.05
CO23A-mb8	67.52	0.15	2.66	0.99	0.71	1.20	7.28	16.58	0.89	0.14	0.26	0.78	0.09	0.51	0.12	0.12	99.98
CO23A-mb9	67.57	0.14	2.46	0.93	0.78	0.87	6.59	17.12	0.68	0.16	0.26	1.07	0.34	0.53	0.47	0.07	100.03
CO23A-lb1	66.29	0.12	2.60	0.96	0.91	1.13	7.57	17.35	0.84	0.23	0.29	0.81	0.14	0.59	0.16	0.00	99.98
CO23A-lb2	66.87	0.13	2.63	1.02	0.67	1.34	7.25	17.04	0.88	0.17	0.23	0.76	0.12	0.63	0.17	0.15	100.05
CO23A-lb3	66.36	0.10	2.59	0.95	0.79	1.15	7.63	17.29	0.93	0.16	0.30	0.76	0.13	0.53	0.15	0.14	99.96
CO23A-lb4	66.68	0.11	2.58	0.97	0.89	1.06	7.48	17.06	0.89	0.19	0.23	0.77	0.13	0.62	0.12	0.14	99.92
CO23A-lb5	66.80	0.14	2.73	1.02	0.70	1.16	7.21	17.31	0.93	0.12	0.22	0.76	0.12	0.59	0.15	0.10	100.04
CO23B	72.27	0.09	3.22	0.40	0.03	0.44	6.23	15.58	0.55	0.06	0.21	0.98	0.00	0.00	0.00	0.00	100.06
CO23B	71.96	0.06	3.26	0.42	0.01	0.45	6.20	15.84	0.55	0.04	0.20	0.98	0.00	0.00	0.00	0.00	99.97
CO23B	72.20	0.07	3.23	0.45	0.02	0.41	6.14	15.63	0.53	0.06	0.20	0.98	0.00	0.00	0.00	0.00	99.91
CO23B	71.91	0.09	3.21	0.47	0.02	0.44	6.27	15.73	0.55	0.03	0.19	0.97	0.00	0.00	0.00	0.00	99.88
CO23B	71.61	0.09	3.12	0.41	0.02	0.41	6.53	15.89	0.55	0.06	0.25	1.00	0.00	0.00	0.00	0.00	99.92
CO23B	71.93	0.06	3.17	0.42	0.04	0.43	6.06	15.98	0.55	0.02	0.20	0.98	0.00	0.00	0.00	0.00	99.83
CO24	67.34	0.08	2.44	0.85	0.60	0.98	6.37	17.80	0.57	0.12	0.34	0.86	0.29	0.35	0.83	0.02	99.83
CO24	67.79	0.05	2.41	0.79	0.59	0.96	6.56	17.47	0.56	0.12	0.37	0.78	0.26	0.37	0.92	0.01	99.99
CO24	67.29	0.06	2.36	0.76	0.57	0.81	6.82	17.85	0.58	0.11	0.36	0.99	0.25	0.29	0.97	0.01	100.07
CO24	67.61	0.09	2.35	0.73	0.60	0.74	6.55	17.61	0.59	0.12	0.38	1.00	0.31	0.34	0.94	0.02	99.98
CO24	67.74	0.11	2.42	0.74	0.57	0.91	6.74	17.60	0.56	0.12	0.35	0.64	0.28	0.35	0.92	0.02	100.07
CO25	70.51	0.11	1.96	0.37	0.58	0.62	5.86	17.84	0.43	0.05	0.22	1.28	0.00	0.00	0.03	0.00	99.86
CO25	69.99	0.09	1.94	0.45	0.61	0.64	6.11	18.26	0.41	0.00	0.24	1.29	0.02	0.00	0.03	0.00	100.08
CO25	70.43	0.10	1.87	0.43	0.56	0.64	5.96	17.92	0.40	0.00	0.25	1.30	0.00	0.01	0.02	0.00	99.88
CO25	70.38	0.09	1.99	0.41	0.60	0.59	6.00	17.97	0.41	0.03	0.24	1.29	0.00	0.00	0.03	0.00	100.03
CO25	70.63	0.05	1.95	0.40	0.63	0.61	5.97	17.79	0.44	0.03	0.23	1.26	0.00	0.00	0.02	0.00	100.01
CO25	70.33	0.09	2.00	0.43	0.66	0.64	5.98	17.90	0.42	0.00	0.26	1.30	0.00	0.01	0.01	0.00	100.03
CO58A	69.94	0.18	2.91	0.86	0.29	0.78	6.42	16.13	0.73	0.10	0.18	0.89	0.12	0.22	0.19	0.03	99.96
CO58A	69.87	0.14	2.93	0.84	0.29	0.79	6.37	16.29	0.64	0.13	0.23	0.92	0.11	0.24	0.14	0.04	99.97
CO58A	70.05	0.11	2.92	0.76	0.28	0.77	6.40	16.27	0.66	0.13	0.20	0.87	0.11	0.22	0.19	0.02	99.97
CO58A	69.94	0.15	2.87	0.78	0.29	0.77	6.52	16.14	0.71	0.16	0.20	0.87	0.12	0.21	0.17	0.02	99.93
CO58A	69.91	0.08	2.91	0.78	0.26	0.73	6.52	16.28	0.73	0.11	0.22	0.88	0.15	0.22	0.15	0.03	99.96
CO58A	69.97	0.14	2.92	0.87	0.30	0.76	6.36	16.15	0.67	0.10	0.24	0.88	0.14	0.20	0.19	0.05	99.95
CO58A	69.81	0.14	2.97	0.83	0.31	0.73	6.47	16.42	0.71	0.13	0.17	0.89	0.12	0.20	0.09	0.04	100.04
CO58A	70.27	0.12	2.96	0.89	0.20	0.73	6.27	16.35	0.71	0.08	0.15	0.85	0.10	0.16	0.07	0.03	99.92
CO58A	70.13	0.11	2.89	0.79	0.29	0.69	6.53	16.10	0.72	0.11	0.26	0.88	0.10	0.22	0.16	0.06	100.04
CO58A	69.84	0.18	2.98	0.84	0.26	0.75	6.57	16.18	0.70	0.08	0.22	0.90	0.07	0.23	0.17	0.11	100.05
CO58B	66.63	0.16	2.65	1.10	0.69	1.00	6.56	15.94	2.74	0.15	0.22	0.84	0.11	0.65	0.42	0.06	99.92
CO58B	66.84	0.13	2.45	1.07	0.67	1.03	6.79	15.93	2.67	0.13	0.21	0.79	0.11	0.69	0.37	0.07	99.96
CO58B	66.85	0.15	2.60	1.07	0.68	0.98	6.55	16.09	2.60	0.14	0.20	0.81	0.16	0.68	0.41	0.07	100.02
CO58B	66.41	0.16	2.47	1.05	0.72	1.00	6.71	16.06	2.69	0.18	0.24	0.82	0.17	0.79	0.39	0.08	99.95
CO58B	66.85	0.10	2.46	0.99	0.70	0.92	6.62	15.98	2.72	0.14	0.27	0.85	0.20	0.69	0.40	0.11	100.01
CO58B	66.86	0.14	2.52	0.97	0.66	0.99	6.60	15.97	2.79	0.17	0.25	0.85	0.12	0.70	0.31	0.07	99.97
CO58B	66.93	0.12	2.53	1.02	0.69	0.95	6.57	16.05	2.69	0.15	0.23	0.84	0.15	0.67	0.37	0.08	100.06
CO58B	67.03	0.17	2.42	1.03	0.68	0.98	6.79	15.79	2.60	0.19	0.23	0.78	0.12	0.71	0.36	0.12	99.98
CO58B	66.75	0.12	2.51	1.19	0.66	1.00	6.62	16.04	2.82	0.14	0.24	0.82	0.10	0.64	0.32	0.07	100.04
CO58B	66.81	0.15	2.54	1.02	0.68	0.96	6.51	15.99	2.93	0.15	0.23	0.85	0.10	0.56	0.34	0.12	99.95
CO58C	72.99	0.08	2.76	0.55	0.09	2.98	5.08	13.66	0.81	0.04	0.13	0.82	0.03	0.02	0.02	0.01	100.05
CO58C	72.93	0.09	2.69	0.59	0.06	3.33	4.62	13.64	0.78	0.08	0.13	0.79	0.02	0.05	0.03	0.02	99.86
CO58C	72.74	0.11	2.77	0.76	0.04	5.23	3.34	13.32	0.79	0.07	0.10	0.77	0.00	0.03	0.02	0.01	100.09
CO58C	71.84	0.05	2.69	1.43	0.02	5.34	3.17	13.65	0.85	0.09	0.11	0.70	0.02	0.02	0.01	0.02	100.01
CO58C	72.30	0.08	2.77	0.66	0.03	5.39	3.33	13.37	0.84	0.06	0.13	0.75	0.03	0.08	0.00	0.02	99.84
CO58C	72.87	0.05	2.76	0.60	0.06	3.13	4.73	13.73	0.81	0.02	0.12	0.89	0.02	0.06	0.00	0.03	99.87
CO58C	72.73	0.06	2.79	0.67	0.07	4.94	3.31	13.48	0.89	0.09	0.13	0.78	0.03	0.02	0.01	0.01	

	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO92 lb1	64.48	0.14	2.49	1.10	0.91	0.95	7.48	17.01	0.69	0.17	0.29	0.84	0.47	2.06	0.59	0.39	100.05
CO92 lb2	64.36	0.15	2.38	0.94	0.96	0.98	7.12	17.29	0.77	0.16	0.36	0.78	0.46	2.27	0.49	0.50	99.96
CO92 lb3	64.68	0.13	2.44	1.02	0.90	0.96	7.17	16.95	0.75	0.21	0.35	0.87	0.44	2.28	0.43	0.44	100.00
CO92 lb4	64.71	0.14	2.44	1.02	0.86	0.98	7.20	16.82	0.72	0.20	0.33	0.79	0.45	2.36	0.52	0.44	99.98
CO93	68.18	0.13	2.58	0.87	0.55	0.92	6.52	17.18	0.68	0.13	0.24	0.94	0.24	0.46	0.30	0.10	100.03
CO93	68.23	0.07	2.53	0.92	0.64	0.96	6.40	17.08	0.73	0.11	0.27	0.90	0.21	0.57	0.27	0.09	99.98
CO93	67.82	0.14	2.54	0.84	0.67	0.97	6.56	17.33	0.77	0.09	0.25	0.93	0.23	0.47	0.26	0.10	99.96
CO93	68.08	0.14	2.55	0.99	0.60	0.90	6.45	17.16	0.71	0.15	0.28	0.94	0.20	0.51	0.24	0.10	100.00
CO93	67.78	0.10	2.60	1.00	0.66	0.93	6.67	17.08	0.68	0.18	0.26	0.92	0.25	0.51	0.25	0.11	99.99
CO93	68.10	0.13	2.57	0.91	0.60	0.93	6.54	17.12	0.68	0.12	0.26	0.92	0.20	0.51	0.23	0.08	99.89
CO93	67.85	0.15	2.52	0.94	0.65	1.05	6.40	17.23	0.79	0.12	0.29	0.89	0.25	0.55	0.22	0.11	100.01
CO93	67.90	0.12	2.50	0.98	0.68	0.87	6.66	17.02	0.74	0.09	0.28	0.97	0.21	0.46	0.24	0.11	99.84
CO93	67.75	0.12	2.55	0.97	0.63	1.18	6.31	17.22	0.78	0.14	0.26	0.93	0.29	0.53	0.24	0.10	99.98
CO94	71.46	0.11	2.84	0.36	0.02	0.60	9.64	13.31	0.92	0.06	0.23	0.38	0.00	0.00	0.00	0.00	99.92
CO94	71.58	0.09	2.86	0.40	0.03	0.64	9.51	13.27	1.00	0.05	0.22	0.38	0.00	0.00	0.00	0.00	100.03
CO94	71.74	0.09	2.83	0.41	0.01	0.63	9.53	13.23	0.92	0.04	0.21	0.38	0.00	0.00	0.00	0.00	100.01
CO94	71.58	0.09	2.83	0.39	0.03	0.64	9.45	13.40	1.00	0.06	0.20	0.38	0.00	0.00	0.00	0.00	100.04
CO94	71.63	0.05	2.78	0.38	0.02	0.61	9.50	13.19	1.00	0.09	0.23	0.39	0.00	0.00	0.00	0.00	99.87
CO94	71.84	0.05	2.78	0.39	0.02	0.63	9.43	13.28	0.96	0.05	0.21	0.38	0.00	0.00	0.00	0.00	100.03
CO95	66.32	0.13	2.58	0.93	0.84	0.91	6.82	17.96	0.73	0.16	0.29	1.05	0.24	0.61	0.28	0.03	99.87
CO95	66.67	0.15	2.53	1.00	0.87	0.93	6.75	17.66	0.75	0.13	0.28	1.09	0.25	0.55	0.28	0.04	99.92
CO95	66.50	0.17	2.61	1.34	0.90	0.89	6.67	17.85	0.72	0.12	0.29	1.07	0.23	0.36	0.23	0.07	100.01
CO95	66.34	0.18	2.63	1.14	0.92	0.89	6.77	17.73	0.74	0.16	0.28	1.08	0.26	0.49	0.19	0.03	99.82
CO95	66.65	0.14	2.57	0.92	0.89	0.90	6.88	17.76	0.70	0.14	0.24	1.06	0.29	0.61	0.23	0.05	100.04
CO96	66.03	0.13	2.45	1.17	0.97	0.97	6.84	18.02	0.79	0.16	0.29	1.04	0.34	0.59	0.21	0.09	100.06
CO96	66.17	0.15	2.48	1.23	0.92	0.89	6.97	17.71	0.78	0.12	0.28	1.03	0.32	0.70	0.20	0.11	100.05
CO96	65.65	0.16	2.47	1.48	0.96	1.24	6.66	17.72	0.80	0.15	0.27	0.99	0.36	0.66	0.18	0.15	99.88
CO96	66.27	0.17	2.50	1.13	0.93	0.94	6.88	17.97	0.82	0.13	0.32	1.05	0.32	0.44	0.15	0.13	100.13
CO96	65.58	0.10	2.40	1.43	0.90	1.23	6.82	17.74	0.76	0.18	0.28	1.00	0.37	0.96	0.24	0.17	100.14
CO96	66.18	0.14	2.46	1.15	0.91	0.98	6.78	17.82	0.78	0.15	0.30	1.02	0.38	0.68	0.26	0.14	100.11
CO96	66.19	0.16	2.48	1.36	0.87	1.10	6.49	17.50	0.81	0.18	0.28	1.01	0.35	0.74	0.17	0.08	99.79
CO96	66.25	0.13	2.43	1.35	1.02	0.97	6.77	16.76	0.79	0.12	0.26	1.03	0.38	0.86	0.26	0.16	99.53
CO99	64.07	0.56	3.48	2.24	2.33	1.39	4.76	19.22	0.39	0.07	0.25	1.19	0.01	0.00	0.00	0.00	99.96
CO99	64.41	0.51	3.40	2.08	2.32	1.34	4.79	19.24	0.36	0.08	0.26	1.20	0.02	0.00	0.00	0.00	100.02
CO99	64.37	0.55	3.48	2.20	2.33	1.41	4.68	19.10	0.38	0.06	0.24	1.18	0.00	0.00	0.00	0.00	99.97
CO99	64.44	0.54	3.44	2.09	2.32	1.40	4.66	19.26	0.38	0.03	0.25	1.20	0.01	0.00	0.00	0.00	100.01
CO99	64.49	0.54	3.37	2.16	2.30	1.39	4.60	19.20	0.36	0.05	0.26	1.22	0.01	0.00	0.00	0.00	99.94
CO99	64.10	0.57	3.42	2.13	2.34	1.40	4.66	19.45	0.37	0.10	0.26	1.20	0.00	0.00	0.00	0.00	99.99
CO99	64.47	0.56	3.37	2.17	2.26	1.44	4.59	19.18	0.40	0.06	0.24	1.19	0.02	0.00	0.00	0.00	99.95
CO100A db1	68.63	0.14	2.74	0.95	0.34	0.95	5.69	17.30	0.89	0.14	0.24	0.92	0.22	0.55	0.20	0.10	100.00
CO100A db2	68.84	0.13	2.84	0.85	0.39	0.93	6.36	16.65	0.83	0.16	0.20	0.89	0.23	0.52	0.18	0.08	100.05
CO100A db3	69.21	0.14	2.79	0.88	0.34	0.87	5.98	16.74	0.86	0.10	0.22	0.97	0.21	0.41	0.12	0.12	99.97
CO100A db4	69.44	0.13	2.94	0.80	0.27	0.83	6.21	16.54	0.87	0.12	0.18	0.84	0.22	0.42	0.13	0.06	99.98
CO100A db5	68.70	0.11	2.83	0.89	0.35	0.86	6.15	16.70	0.80	0.13	0.19	0.90	0.33	0.74	0.14	0.05	99.85
CO100A db6	68.35	0.11	2.90	1.04	0.39	1.01	6.33	16.77	0.88	0.13	0.18	0.85	0.30	0.56	0.18	0.09	100.06
CO100A db7	68.80	0.15	2.77	0.86	0.38	0.89	6.17	16.72	0.79	0.14	0.20	0.91	0.29	0.58	0.11	0.11	99.88
CO100A db8	69.21	0.09	2.93	0.93	0.30	0.85	6.09	16.46	0.81	0.16	0.18	0.84	0.22	0.54	0.13	0.11	99.87
CO100A db9	69.44	0.13	2.85	0.87	0.30	1.12	5.78	16.65	0.88	0.16	0.23	0.85	0.23	0.38	0.11	0.09	100.07
CO100A lb1	68.39	0.16	2.78	1.10	0.35	0.93	5.85	16.49	0.86	0.17	0.21	0.94	0.30	1.00	0.12	0.37	100.01
CO100A lb2	68.28	0.12	2.74	0.92	0.35	0.86	5.90	16.94	0.80	0.10	0.20	0.95	0.27	1.04	0.18	0.32	99.96
CO100A lb3	68.20	0.14	2.77	0.97	0.33	0.93	5.72	16.57	0.79	0.13	0.23	0.93	0.37	1.48	0.16	0.36	100.07
CO100A lb4	68.38	0.14	2.78	0.97	0.38	0.86	5.79	16.52	0.81	0.12	0.21	0.93	0.43	1.16	0.14	0.44	100.04
CO100A lb5	68.49	0.15	2.76	1.00	0.37	0.88	5.85	16.49	0.78	0.15	0.19	0.94	0.41	1.14	0.18	0.33	100.09
CO100A lb6	68.71	0.12	2.78	0.90	0.31	0.89	5.73	16.34	0.78	0.14	0.20	0.96	0.31	1.09	0.17	0.38	99.81
CO100A lb7	68.52	0.14	2.79	0.94	0.37	0.87	5.85	16.58	0.83	0.15	0.25	0.92	0.24	1.09	0.10	0.36	99.98
CO100A lb8	68.78	0.15	2.74	0.98	0.33	0.88	5.80	16.30	0.83	0.11	0.20	0.91	0.36	1.10	0.14	0.37	99.96
CO100A lb9	68.63	0.11	2.79	0.98	0.33	0.86	5.77	16.60	0.79	0.10	0.22	0.88	0.23	1.17	0.14	0.38	99.99
CO100B	67.36	0.15	2.34	0.91	0.79	0.79	6.55	18.18	0.56	0.11	0.29	1.05	0.24	0.33	0.28	0.02	99.93
CO100B	67.46	0.13	2.39	0.78	0.84	0.79	6.33	18.50	0.58	0.10	0.25	1.05	0.20	0.30	0.20	0.01	99.91
CO100B	67.51	0.07	2.35	0.93	0.78	0.82	6.51	18.23	0.60	0.07	0.23	1.07	0.24	0.33	0.19	0.04	99.97
CO100B	67.61	0.12	2.35	0.92	0.81	0.86	6.44	18.21	0.55	0.09	0.28	1.05	0.20	0.33	0.18	0.03	100.04
CO100B	67.32	0.11	2.33	1.05	0.80	0.81	6.54	18.01	0.71	0.11	0.32	1.06	0.18	0.38	0.24	0.03	99.99
CO100B	67.53	0.09	2.														

	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO121B lb1	66.48	0.12	2.55	2.41	0.51	1.01	6.69	16.67	0.90	0.23	0.26	0.92	0.27	0.60	0.26	0.06	99.92
CO121B lb2	67.92	0.13	2.63	0.77	0.55	0.90	7.10	16.71	0.84	0.18	0.23	1.01	0.22	0.55	0.23	0.00	99.97
CO121B lb3	66.94	0.10	2.77	1.02	0.59	1.17	7.02	16.84	0.89	0.18	0.26	0.93	0.28	0.66	0.29	0.06	99.98
CO121B lb4	66.99	0.15	2.73	1.05	0.60	1.16	6.86	16.86	0.96	0.13	0.29	0.93	0.29	0.65	0.34	0.00	99.97
CO121C	68.55	0.12	2.56	0.84	0.65	0.83	6.64	16.80	0.66	0.12	0.28	1.16	0.21	0.30	0.21	0.03	99.95
CO121C	68.38	0.08	2.62	0.82	0.59	0.80	6.77	16.87	0.64	0.18	0.26	1.13	0.22	0.40	0.25	0.04	100.04
CO121C	68.26	0.12	2.69	0.78	0.51	0.78	6.62	17.32	0.59	0.13	0.28	1.09	0.15	0.41	0.22	0.06	99.99
CO121C	68.19	0.10	2.67	0.73	0.54	0.81	6.80	17.26	0.65	0.17	0.27	1.08	0.18	0.33	0.25	0.03	100.07
CO121C	67.90	0.08	2.56	0.85	0.59	0.81	6.71	17.40	0.72	0.17	0.27	1.06	0.20	0.42	0.21	0.05	99.99
CO121C	68.62	0.10	2.53	0.75	0.67	0.77	6.38	17.44	0.62	0.13	0.26	1.04	0.19	0.32	0.17	0.01	99.99
CO121C	68.14	0.09	2.63	0.87	0.68	0.79	6.43	17.42	0.63	0.13	0.24	1.10	0.20	0.34	0.19	0.10	99.97
CO121C	68.17	0.11	2.60	0.79	0.58	0.75	6.68	17.46	0.65	0.15	0.27	1.05	0.15	0.35	0.18	0.05	99.96
CO121D	66.57	0.13	2.40	0.92	0.81	0.94	6.70	17.76	0.72	0.18	0.33	1.06	0.34	0.62	0.39	0.07	99.93
CO121D	67.02	0.12	2.48	1.02	0.79	0.90	6.64	17.39	0.72	0.14	0.33	1.02	0.34	0.56	0.39	0.04	99.89
CO121D	66.83	0.13	2.49	1.00	0.76	0.93	6.73	17.37	0.67	0.16	0.35	1.06	0.31	0.66	0.48	0.02	99.95
CO121D	66.77	0.14	2.53	0.98	0.85	0.95	6.71	17.33	0.69	0.18	0.31	1.04	0.40	0.52	0.40	0.03	99.93
CO121D	66.99	0.14	2.43	0.96	0.85	0.90	6.86	17.24	0.76	0.19	0.28	1.05	0.32	0.48	0.42	0.03	99.91
CO121D	66.91	0.14	2.52	1.03	0.82	0.95	6.86	17.16	0.72	0.15	0.33	1.05	0.36	0.57	0.43	0.06	100.06
CO121D	66.58	0.14	2.62	1.09	0.84	0.97	7.03	17.06	0.66	0.17	0.29	1.10	0.37	0.64	0.44	0.05	100.04
CO121E	67.20	0.10	2.25	0.67	0.39	0.94	6.13	19.72	0.45	0.00	0.35	1.39	0.00	0.01	0.28	0.00	99.87
CO121E	67.26	0.08	2.27	0.71	0.38	1.02	6.13	19.64	0.43	0.03	0.32	1.33	0.01	0.00	0.33	0.00	99.95
CO121E	67.69	0.13	2.37	0.61	0.39	0.99	6.21	19.16	0.43	0.05	0.35	1.32	0.00	0.00	0.28	0.00	99.98
CO121E	67.49	0.12	2.26	0.68	0.38	1.01	6.13	19.53	0.41	0.07	0.35	1.33	0.00	0.01	0.27	0.00	100.05
CO121E	67.76	0.11	2.26	0.60	0.37	0.98	6.23	19.22	0.43	0.03	0.34	1.34	0.00	0.00	0.27	0.00	99.95
CO122	67.57	0.09	2.29	0.92	0.63	0.87	6.98	17.28	0.68	0.11	0.35	0.65	0.31	0.29	0.90	0.00	99.92
CO122	67.63	0.08	2.32	0.90	0.62	0.77	6.88	17.39	0.66	0.13	0.33	0.59	0.34	0.28	0.95	0.03	99.89
CO122	67.56	0.06	2.42	0.98	0.57	1.15	6.38	17.41	0.73	0.12	0.32	0.86	0.34	0.29	0.82	0.01	100.03
CO122	67.79	0.06	2.32	0.80	0.61	0.83	6.90	17.53	0.68	0.10	0.33	0.57	0.32	0.28	0.87	0.00	99.98
CO122	67.36	0.10	2.26	0.90	0.65	0.90	6.77	17.47	0.74	0.11	0.36	0.77	0.32	0.26	0.84	0.02	99.83
CO184A	67.46	0.12	2.57	1.00	0.66	1.03	6.84	17.35	0.83	0.13	0.26	0.39	0.35	0.61	0.33	0.10	100.01
CO184A	66.94	0.10	2.64	1.05	0.72	1.04	6.79	17.31	0.84	0.18	0.26	0.92	0.17	0.64	0.27	0.07	99.93
CO184A	67.22	0.12	2.62	0.98	0.69	1.12	6.78	17.30	0.80	0.15	0.27	0.71	0.29	0.57	0.30	0.08	99.99
CO184A	67.54	0.12	2.63	1.02	0.65	1.06	6.85	17.20	0.79	0.14	0.22	0.78	0.20	0.61	0.24	0.05	100.09
CO184A	67.08	0.17	2.62	1.05	0.69	1.11	6.77	17.28	0.86	0.13	0.29	0.64	0.26	0.56	0.27	0.09	99.87
CO184B	67.29	0.09	2.39	0.87	0.76	0.91	6.89	17.63	0.56	0.14	0.29	1.10	0.29	0.57	0.29	0.00	100.05
CO184B	67.19	0.06	2.43	0.80	0.74	0.95	6.72	17.96	0.56	0.08	0.33	1.08	0.31	0.47	0.28	0.04	99.98
CO184B	67.09	0.14	2.46	0.92	0.70	0.95	6.68	17.89	0.60	0.12	0.31	1.02	0.28	0.52	0.33	0.03	100.01
CO184B	67.49	0.12	2.48	0.96	0.72	0.86	6.47	17.89	0.56	0.07	0.30	1.11	0.27	0.48	0.28	0.00	100.05
CO184B	67.24	0.12	2.48	0.94	0.71	0.82	6.43	18.01	0.55	0.15	0.32	1.19	0.23	0.44	0.33	0.00	99.95
CO184B	67.37	0.09	2.44	0.82	0.74	0.86	6.39	17.89	0.63	0.09	0.29	1.19	0.30	0.44	0.32	0.02	99.89
CO184B	67.36	0.13	2.49	0.90	0.72	0.92	6.67	17.46	0.54	0.10	0.33	1.10	0.28	0.49	0.35	0.02	99.85
CO184C	66.46	0.16	2.52	1.11	0.76	1.25	6.25	17.90	0.69	0.18	0.27	1.00	0.30	0.65	0.35	0.06	99.88
CO184C	66.73	0.12	2.46	1.10	0.80	1.16	6.41	17.83	0.67	0.12	0.27	1.00	0.27	0.67	0.41	0.03	100.03
CO184C	66.87	0.12	2.49	1.05	0.79	1.09	6.57	17.69	0.65	0.17	0.28	1.01	0.25	0.54	0.32	0.04	99.93
CO184C	67.51	0.12	2.37	0.81	0.71	0.83	6.36	18.25	0.68	0.08	0.32	1.14	0.25	0.37	0.22	0.05	100.06
CO184C	67.14	0.11	2.28	0.89	0.67	0.93	6.92	18.00	0.74	0.17	0.29	0.89	0.31	0.39	0.34	0.03	100.10
CO184C	66.67	0.16	2.51	0.91	0.78	0.99	6.59	17.91	0.69	0.14	0.31	1.02	0.30	0.59	0.35	0.04	99.96
CO230 db1	71.64	0.08	2.80	0.68	0.04	0.72	6.69	15.20	0.65	0.08	0.16	0.96	0.06	0.00	0.08	0.05	99.88
CO230 db2	71.77	0.09	2.80	0.53	0.15	0.86	6.67	15.31	0.59	0.10	0.14	0.84	0.03	0.10	0.08	0.03	100.08
CO230 db3	71.09	0.08	2.72	0.62	0.14	0.66	6.86	15.73	0.59	0.10	0.15	0.90	0.10	0.12	0.10	0.01	99.96
CO230 db4	71.46	0.08	2.72	0.60	0.13	0.81	6.66	15.36	0.66	0.08	0.14	0.88	0.05	0.18	0.04	0.05	99.88
CO230 db5	71.32	0.10	2.67	0.70	0.17	0.77	6.68	15.54	0.60	0.09	0.17	0.88	0.01	0.16	0.08	0.01	99.98
CO230 db6	71.35	0.10	2.85	0.84	0.06	0.65	6.50	15.45	0.66	0.09	0.14	0.90	0.04	0.17	0.10	0.03	99.91
CO230 db7	71.54	0.10	2.70	0.65	0.14	0.76	6.61	15.43	0.61	0.11	0.15	0.89	0.02	0.18	0.10	0.04	100.01
CO230 db8	71.79	0.08	2.80	0.56	0.08	0.73	6.69	15.36	0.65	0.07	0.14	0.90	0.03	0.09	0.08	0.01	100.06
CO230 db9	71.38	0.10	2.74	0.75	0.13	0.78	6.63	15.34	0.61	0.06	0.19	0.87	0.08	0.21	0.05	0.06	99.96
CO230 db10	71.56	0.11	2.75	0.60	0.08	0.64	6.69	15.42	0.58	0.08	0.11	0.94	0.07	0.14	0.06	0.02	99.83
CO230 lb1	71.34	0.07	2.67	0.51	0.17	0.65	6.47	15.52	0.69	0.11	0.17	0.94	0.15	0.34	0.05	0.09	99.95
CO230 lb2	70.99	0.05	2.69	0.58	0.12	0.63	6.58	15.88	0.63	0.09	0.15	0.92	0.09	0.34	0.05	0.10	99.90
CO230 lb3	70.93	0.11	2.63	0.60	0.15	0.65	6.70	15.70	0.62	0.11	0.19	0.86	0.08	0.47	0.05	0.09	99.95
CO230 lb4	70.97	0.09	2.69	0.61	0.17	0.67	6.46	15.57	0.68	0.07	0.17	0.98	0.13	0.52	0.12	0.12	100.01
CO230 lb5	70.52	0.09	2.63	0.60	0.26	0.73	6.81	15.53	0.63	0.07	0.20	0.93	0.09	0.54	0.15	0.17	9

	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO233B	68.33	0.21	2.51	1.73	1.11	0.97	6.90	16.31	0.66	0.12	0.25	0.84	0.01	0.03	0.00	0.00	99.98
CO233B	68.46	0.13	2.51	1.78	1.25	1.00	6.79	16.21	0.64	0.16	0.27	0.82	0.00	0.03	0.05	0.00	100.09
CO233B	68.56	0.13	2.56	1.89	1.14	0.96	6.73	16.11	0.61	0.10	0.28	0.82	0.03	0.03	0.00	0.00	99.94
CO233B	68.39	0.13	2.52	1.80	1.28	0.95	6.63	16.14	0.64	0.16	0.30	0.99	0.00	0.04	0.03	0.03	100.02
CO233B	68.63	0.17	2.54	1.76	1.06	0.99	6.78	16.21	0.59	0.09	0.26	0.80	0.01	0.04	0.02	0.00	99.94
CO233B	68.47	0.17	2.54	1.84	1.22	1.08	6.72	15.91	0.59	0.12	0.27	0.84	0.05	0.04	0.03	0.00	99.89
CO233B	68.20	0.17	2.64	1.66	1.05	1.13	6.90	16.24	0.63	0.14	0.27	0.83	0.04	0.05	0.05	0.02	100.03
CO233C	66.06	0.10	2.44	1.13	0.85	1.05	7.40	17.49	0.81	0.21	0.34	0.92	0.29	0.39	0.51	0.06	100.04
CO233C	66.12	0.12	2.43	1.09	0.79	0.98	7.22	17.60	0.77	0.21	0.29	0.84	0.29	0.55	0.52	0.06	99.88
CO233C	66.33	0.12	2.39	1.17	0.78	0.93	7.35	17.34	0.82	0.20	0.31	0.89	0.29	0.48	0.36	0.08	99.83
CO233C	66.26	0.13	2.40	1.09	0.80	1.02	7.36	17.37	0.80	0.20	0.29	0.87	0.31	0.49	0.51	0.05	99.92
CO233C	66.31	0.14	2.36	1.17	0.83	0.93	7.30	17.38	0.79	0.23	0.32	0.89	0.29	0.50	0.41	0.07	99.90
CO233C	66.40	0.14	2.37	1.05	0.77	1.05	7.25	17.28	0.75	0.20	0.31	0.87	0.32	0.53	0.50	0.06	99.85
CO233C	66.13	0.14	2.50	1.19	0.78	1.00	7.30	17.30	0.76	0.25	0.31	0.90	0.28	0.53	0.49	0.08	99.94
CO233C	66.55	0.08	2.41	1.02	0.66	0.92	7.34	17.36	0.79	0.18	0.31	0.82	0.29	0.55	0.54	0.05	99.85
CO233C	67.07	0.13	2.43	1.04	0.75	1.00	7.10	17.09	0.80	0.20	0.26	0.85	0.33	0.46	0.47	0.07	100.04
CO233C	66.21	0.14	2.46	1.11	0.82	1.09	7.51	17.01	0.76	0.31	0.36	0.83	0.35	0.58	0.41	0.12	100.08
CO233C	66.16	0.15	2.39	1.11	0.83	1.01	7.59	17.31	0.78	0.26	0.33	0.92	0.29	0.57	0.27	0.08	100.04
CO233C	66.44	0.14	2.36	1.06	0.77	1.01	7.41	17.12	0.76	0.18	0.32	0.89	0.33	0.57	0.51	0.14	100.00
CO233C	66.55	0.09	2.49	1.08	0.79	0.97	7.09	17.41	0.74	0.21	0.33	0.90	0.26	0.46	0.46	0.05	99.88
CO233C	66.26	0.17	2.48	1.13	0.77	1.01	7.20	17.29	0.78	0.25	0.36	0.90	0.28	0.58	0.49	0.09	100.04
CO233C	66.10	0.08	2.50	1.12	0.75	1.09	7.26	17.20	0.78	0.26	0.32	0.92	0.32	0.59	0.52	0.07	99.89
CO233C	66.29	0.12	2.47	1.14	0.78	0.99	7.29	17.21	0.74	0.24	0.34	0.86	0.26	0.55	0.50	0.07	99.86
CO325 db1	66.94	0.23	3.33	1.25	0.55	1.28	6.89	16.17	0.91	0.18	0.17	0.63	0.34	0.81	0.11	0.11	99.90
CO325 db2	67.03	0.12	2.68	1.07	0.58	1.07	7.30	16.45	0.89	0.17	0.27	0.82	0.25	0.94	0.22	0.08	99.94
CO325 db3	67.14	0.12	2.61	0.92	0.56	1.03	7.32	16.86	0.84	0.16	0.24	0.79	0.28	0.96	0.14	0.09	100.03
CO325 db4	67.29	0.17	2.59	1.16	0.59	1.67	6.85	16.43	0.88	0.17	0.20	0.57	0.24	0.98	0.17	0.07	100.00
CO325 lb1	67.25	0.18	2.57	0.88	0.59	1.01	7.41	16.41	0.85	0.20	0.25	0.78	0.27	1.01	0.12	0.24	99.98
CO325 lb2	67.23	0.13	2.64	0.95	0.57	1.08	7.43	16.40	0.83	0.19	0.23	0.83	0.26	1.03	0.17	0.00	99.95
CO325 lb3	66.86	0.14	2.64	1.39	0.53	1.94	6.63	16.54	0.86	0.18	0.22	0.68	0.23	1.09	0.10	0.00	100.04
CO325 lb4	66.88	0.12	2.69	0.90	0.58	1.22	7.44	16.55	0.83	0.20	0.23	0.80	0.24	1.07	0.19	0.00	99.94
CO325 lb5	66.30	0.13	2.46	0.95	0.65	1.01	7.27	16.85	0.82	0.18	0.28	0.86	0.26	1.37	0.13	0.34	99.87
CO325 lb6	67.02	0.14	2.60	1.00	0.58	1.12	7.31	16.43	0.80	0.23	0.24	0.81	0.28	1.06	0.10	0.20	99.93
CO325 lb7	66.56	0.12	2.63	0.94	0.58	1.29	7.30	16.68	0.93	0.17	0.22	0.79	0.25	1.12	0.19	0.21	99.97
CO325 lb8	67.29	0.16	2.66	0.99	0.52	1.00	7.25	16.22	0.82	0.19	0.25	0.86	0.30	1.06	0.20	0.24	100.00
CO325 lb9	66.94	0.15	2.58	0.92	0.51	1.01	7.22	16.50	0.87	0.19	0.26	0.84	0.27	1.15	0.20	0.26	99.86
CO325 lb10	67.13	0.15	2.76	0.90	0.55	1.12	7.15	16.47	0.85	0.19	0.27	0.80	0.26	1.15	0.11	0.23	100.08
CO325 lb11	66.12	0.15	2.59	1.06	0.56	0.98	7.37	16.58	0.82	0.22	0.33	0.89	0.31	1.49	0.13	0.43	100.03
CO365 db1	73.29	0.08	3.04	0.41	0.02	0.56	6.82	14.08	0.55	0.07	0.15	0.81	0.08	0.08	0.01	0.00	100.05
CO365 db2	73.27	0.07	2.86	0.44	0.07	0.60	6.86	14.04	0.58	0.08	0.14	0.78	0.04	0.08	0.01	0.07	99.98
CO365 db3	73.25	0.05	2.95	0.39	0.01	0.58	6.85	14.40	0.53	0.03	0.16	0.77	0.04	0.01	0.05	0.02	100.09
CO365 db4	73.34	0.08	2.99	0.46	0.05	0.56	6.65	14.24	0.53	0.05	0.16	0.76	0.04	0.08	0.02	0.00	100.01
CO365 db5	73.14	0.07	3.10	0.36	0.00	0.55	6.74	14.26	0.58	0.04	0.14	0.81	0.02	0.04	0.00	0.01	99.84
CO365 db6	73.31	0.09	3.02	0.39	0.02	0.52	6.78	14.33	0.49	0.07	0.12	0.76	0.00	0.05	0.00	0.00	99.96
CO365 db7	73.22	0.05	2.88	0.45	0.05	0.58	6.87	14.18	0.54	0.08	0.13	0.79	0.06	0.03	0.06	0.00	99.95
CO365 lb1	72.60	0.08	2.92	0.50	0.12	0.68	6.84	14.25	0.53	0.07	0.17	0.82	0.08	0.21	0.07	0.05	99.97
CO365 lb2	72.86	0.06	2.89	0.46	0.06	0.73	6.62	14.44	0.53	0.06	0.12	0.79	0.05	0.24	0.01	0.02	99.94
CO365 lb3	71.95	0.11	3.32	0.75	0.10	0.72	6.84	14.25	0.47	0.09	0.16	0.73	0.05	0.39	0.00	0.15	100.07
CO365 lb4	72.61	0.09	2.97	0.46	0.04	0.66	6.82	14.50	0.56	0.07	0.13	0.81	0.04	0.19	0.07	0.02	100.02
CO365 lb5	72.21	0.06	2.90	0.50	0.07	0.63	6.76	14.75	0.52	0.05	0.15	0.87	0.04	0.28	0.08	0.08	99.95
CO365 lb6	71.74	0.13	3.10	0.61	0.14	0.77	6.92	14.54	0.48	0.10	0.17	0.75	0.05	0.31	0.07	0.16	100.04
CO366	69.12	0.13	2.79	0.60	0.34	0.93	7.95	15.99	0.77	0.13	0.18	0.80	0.06	0.14	0.07	0.06	100.04
CO366	69.71	0.08	2.85	0.59	0.31	0.91	7.88	15.70	0.75	0.16	0.18	0.77	0.00	0.17	0.05	0.00	100.09
CO366	68.88	0.12	2.82	0.71	0.39	0.96	7.95	15.91	0.77	0.15	0.20	0.81	0.07	0.10	0.05	0.00	99.88
CO366	69.68	0.12	2.83	0.57	0.26	0.92	7.99	15.37	0.75	0.12	0.18	0.80	0.11	0.12	0.02	0.02	99.87
CO366	68.42	0.11	2.75	0.56	0.27	0.96	8.97	16.03	0.73	0.18	0.16	0.71	0.05	0.12	0.06	0.00	100.07
CO366	69.14	0.10	2.63	0.75	0.38	1.05	7.67	15.82	0.84	0.20	0.23	0.80	0.07	0.09	0.05	0.00	99.80
CO366	69.78	0.09	2.79	0.62	0.29	0.97	7.80	15.61	0.76	0.10	0.20	0.78	0.04	0.13	0.03	0.00	99.98
CO366	69.17	0.14	2.84	0.70	0.42	0.89	7.65	15.74	0.86	0.18	0.20	0.80	0.12	0.11	0.06	0.08	99.94
CO368	72.57	0.09	3.07	0.38	0.00	0.49	6.80	15.09	0.54	0.06	0.12	0.76	0.00	0.00	0.00	0.00	99.96
CO368	72.02	0.09	3.18	0.32	0.01	0.49	6.99	15.39	0.50	0.05	0.15	0.83	0.00	0.00	0.02	0.00	100.03
CO368	72.10	0.06	3.15	0.40	0.00	0.46	7.04	15.16	0.52	0.01	0.11	0.87	0.00	0.00	0.00	0.0	

	SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MnO	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃	Cl	CuO	PbO	Sb ₂ O ₅	SnO ₂	Total
CO530 lb1	64.80	0.14	2.84	1.24	0.62	0.98	7.72	15.33	0.84	0.16	0.18	0.76	0.94	2.62	0.02	0.77	99.96
CO530 lb2	65.85	0.13	2.82	1.30	0.60	1.06	7.53	14.50	0.83	0.18	0.21	0.73	0.93	2.61	0.07	0.74	100.08
CO530 lb3	66.02	0.14	2.75	1.36	0.59	0.93	7.42	14.98	0.87	0.19	0.17	0.74	0.94	2.62	0.04	0.33	100.09
CO530 lb4	65.08	0.12	2.77	1.46	0.60	1.04	7.68	15.14	0.83	0.18	0.21	0.74	0.94	2.64	0.03	0.45	99.89
CO530 lb5	65.65	0.14	2.73	1.27	0.58	0.95	7.56	14.60	0.90	0.21	0.21	0.72	0.94	2.63	0.01	0.99	100.07
CO530 lb6	65.15	0.09	2.74	1.42	0.62	0.97	7.48	14.96	0.86	0.21	0.18	0.75	0.97	2.71	0.03	0.78	99.92
CO530 lb7	65.98	0.09	2.78	1.22	0.59	1.03	7.50	14.84	0.84	0.23	0.16	0.72	0.93	2.56	0.09	0.48	100.03
CO530 lb8	65.86	0.11	2.77	1.27	0.57	1.05	7.49	14.79	0.86	0.19	0.20	0.72	0.91	2.50	0.02	0.65	99.95
CO530 lb9	64.69	0.12	2.73	1.43	0.60	0.98	7.73	14.97	0.81	0.20	0.21	0.71	0.95	2.86	0.00	1.04	100.02
CO530 lb10	65.66	0.14	2.85	1.32	0.65	0.97	7.46	14.91	0.83	0.18	0.19	0.75	0.97	2.60	0.05	0.55	100.08
CO530 lb11	65.78	0.14	2.81	1.39	0.56	0.99	7.52	14.88	0.79	0.22	0.20	0.74	0.96	2.68	0.08	0.37	100.09
CO530 wb1	62.47	0.15	2.75	1.58	0.66	1.04	7.55	15.22	0.81	0.28	0.22	0.71	1.59	3.62	0.04	1.19	99.89
CO530 wb2	62.37	0.15	2.68	1.87	0.61	0.99	7.56	14.83	0.80	0.31	0.23	0.73	1.04	4.62	0.03	1.11	99.91
CO530 wb3	62.22	0.16	2.78	2.72	0.57	1.12	7.36	14.93	0.79	0.23	0.21	0.71	1.04	3.96	0.02	1.08	99.89
CO530 wb4	62.39	0.11	2.65	1.74	0.57	0.91	7.01	14.69	0.85	0.23	0.20	0.71	1.28	4.92	0.04	1.76	100.04
CO530 wb5	62.66	0.14	2.67	1.75	0.57	0.94	7.36	14.55	0.74	0.26	0.23	0.74	1.02	4.41	0.02	1.88	99.93

Table S5. LA-ICP-MS: full data set. All values in ppm.

	CO23A				CO23B				CO25				
Li	9.2	<2.30	7.7	6.5	4.7	6.8	3.7	5.7	5.1	4.5	2.4	4.2	5.2
Be	3.9	5.6	3.6	<0.00	6.3	3.1	3.7	<2.90	3.4	<2.56	<0.00	<3.05	<3.11
B	127	126	119	109	60	58	50	53	164	143	195	185	154
Sc	4.3	4.4	3.9	4.0	2.5	2.6	3.0	2.3	2.6	2.6	2.4	2.5	2.3
Ti	874	922	884	885	468	409	434	407	422	455	417	454	464
V	23	25	23	23	8	8	8	7	17	18	17	18	16
Cr	35	42	33	41	9	9	13	12	11	9	9	9	12
Co	24	23	21	24	1	1	1	1	6	6	5	6	5
Ni	26	32	29	33	3	3	3	4	6	5	6	5	6
Cu	876	872	875	917	5	5	5	7	21	22	22	21	34
Zn	103	98	104	103	6	6	5	5	10	9	9	8	10
Ga	3.9	3.0	3.1	3.6	2.7	3.1	3.3	2.9	1.8	2.0	1.8	2.0	2.0
Ge	<0.91	<1.07	1.0	<0.91	<0.61	<0.61	0.8	0.5	1.0	1.1	<0.46	1.8	0.7
As	11.5	12.0	11.3	12.7	1.6	0.9	0.8	0.8	6.1	6.6	7.0	6.3	6.6
Rb	10.5	10.8	10.2	11.2	9.3	9.0	9.5	8.9	4.5	4.9	4.7	5.2	4.8
Sr	529	544	526	543	330	315	338	312	423	427	413	426	425
Y	8.2	9.1	7.9	8.2	6.2	5.7	5.6	5.5	5.2	5.2	4.9	5.6	5.5
Zr	87.1	92.9	84.1	87.5	40.4	38.2	40.1	36.6	42.3	42.0	41.1	44.2	41.9
Nb	2.35	2.91	2.44	2.22	1.48	1.38	1.77	1.41	1.45	1.30	1.23	1.37	1.34
Mo	1.70	1.89	1.31	2.29	0.41	0.28	0.36	0.34	0.50	0.51	0.78	0.12	0.35
Ag	1.41	1.13	1.78	1.51	0.04	<0.089	<0.065	3.79	0.08	0.22	<0.051	<0.033	<0.059
Cd	<0.60	<0.60	<0.45	<0.47	<0.34	<0.31	<0.39	<0.190	<0.163	<0.34	0.28	0.45	0.42
In	1.96	2.01	1.92	2.13	<0.0170	<0.0152	0.04	<0.0163	<0.0140	<0.0084	0.02	<0.0141	<0.0143
Sn	514	572	462	535	1	2	2	2	2	2	2	2	2
Sb	861	968	869	998	1	<0.28	<0.32	<0.224	228	226	228	229	231
Cs	0.224	0.175	0.123	0.139	0.096	0.080	0.110	0.081	0.060	0.067	0.040	0.060	0.057
Ba	313	319	308	310	214	200	209	199	403	407	394	398	398
La	8.162	8.344	7.898	7.766	5.984	5.435	5.774	5.615	5.597	5.336	5.386	5.336	5.587
Ce	13.241	13.951	14.123	13.363	11.499	10.670	11.379	10.899	9.345	10.199	9.044	9.295	9.426
Pr	1.888	1.729	1.732	1.762	1.372	1.341	1.321	1.333	1.123	1.118	1.145	1.122	1.120
Nd	8.679	8.881	6.773	8.141	5.684	6.304	6.034	5.525	4.833	4.934	5.024	4.853	4.783
Sm	1.328	1.338	1.997	1.805	1.229	1.109	1.339	0.979	1.005	0.794	1.015	1.246	1.035
Eu	0.458	0.550	0.547	0.382	0.387	0.420	0.466	0.320	0.254	0.304	0.257	0.340	0.116
Gd	1.237	1.744	1.156	1.105	0.999	0.899	1.019	1.049	0.894	0.773	0.645	0.995	0.784
Tb	0.251	0.259	0.208	0.211	0.140	0.154	0.189	0.194	0.165	0.149	0.167	0.116	0.105
Dy	1.490	1.724	1.024	0.963	0.803	0.803	1.119	0.900	0.916	1.045	1.024	0.796	0.855
Ho	0.259	0.330	0.323	0.308	0.183	0.216	0.163	0.170	0.177	0.141	0.244	0.181	0.224
Er	0.740	0.824	0.670	0.602	0.440	0.353	0.480	0.507	0.361	0.384	0.389	0.537	0.353
Tm	0.085	0.076	0.119	0.103	0.098	0.054	0.101	0.058	0.107	0.064	0.101	0.112	0.121
Yb	0.649	0.923	0.413	0.649	0.265	0.468	0.679	0.587	0.424	0.525	0.440	0.251	0.764
Lu	0.157	0.134	0.134	0.169	0.034	<0.025	0.075	0.103	0.099	0.058	0.055	0.064	0.077
Hf	2.535	2.200	2.129	2.535	0.909	0.759	1.359	0.969	1.196	0.975	1.115	1.517	1.156
Ta	0.122	0.129	0.203	0.111	0.070	0.101	0.061	0.071	0.060	0.047	0.086	0.046	0.087
W	0.403	0.459	0.562	0.345	<0.091	0.131	<0.103	<0.082	0.090	0.288	0.066	0.097	<0.063
Au	0.557	0.343	0.363	0.438	0.018	<0.037	0.041	<0.032	<0.028	0.040	<0.036	0.038	<0.035
Tl	0.030	0.076	0.073	0.076	<0.028	0.024	<0.044	<0.0153	0.009	0.037	<0.0246	0.009	0.025
Pb	4125	4085	3956	4137	6	6	6	6	15	16	16	16	19
Bi	0.298	0.612	0.468	0.290	0.060	<0.0207	0.037	0.036	<0.029	<0.025	<0.0177	<0.033	0.035
Th	1.467	1.534	1.467	1.315	0.736	0.650	0.846	0.713	0.787	0.807	0.539	0.894	0.773
U	1.014	1.114	1.156	1.114	0.660	0.491	0.780	0.752	0.829	0.705	0.805	0.781	0.781

	CO58				CO58B				CO58C					
	4.7	6.2	3.6	6.9	6.9	6.0	3.3	7.5	4.0	5.2	4.1	5.1	6.1	4.8
Li	4.7	6.2	3.6	6.9	6.9	6.0	3.3	7.5	4.0	5.2	4.1	5.1	6.1	4.8
Be	<4.95	3.8	<3.03	<5.16	<4.78	<2.81	<3.07	<4.16	<5.09	2.8	-	<4.87	<7.18	5.5
B	78	87	68	109	159	139	136	143	49	58	71	71	52	53
Sc	3.9	3.8	3.1	2.6	3.4	3.6	3.8	4.0	3.2	3.9	3.3	4.4	3.8	3.8
Ti	690	667	660	555	755	810	907	901	491	544	547	583	511	519
V	15	15	15	16	22	24	25	27	10	12	12	13	11	10
Cr	21	22	16	14	14	23	25	25	32	51	43	53	47	45
Co	16	17	15	16	36	37	37	37	14	15	13	16	17	17
Ni	10	10	9	10	16	19	17	19	94	126	112	128	146	134
Cu	798	812	780	1602	1093	1157	1125	1122	102	123	114	109	95	90
Zn	127	45	40	190	129	139	143	157	32	40	42	44	34	32
Ga	2.9	3.5	3.1	2.7	3.0	3.0	2.9	2.9	3.2	2.8	3.5	3.5	2.8	3.4
Ge	<0.82	1.5	<0.77	<0.62	<0.75	1.4	1.0	1.6	1.0	<0.86	0.8	1.4	2.8	1.1
As	11.7	11.0	7.3	19.7	30.4	26.1	21.9	23.8	1.7	3.1	2.4	2.4	2.2	2.0
Rb	10.6	10.9	11.0	16.8	12.8	12.4	12.6	12.4	16.0	17.8	17.8	18.2	19.4	18.2
Sr	404	425	399	424	522	522	507	517	261	302	286	280	243	235
Y	6.4	7.3	6.6	5.8	7.4	7.7	7.0	7.7	6.4	6.3	6.2	7.0	6.4	6.3
Zr	55.3	61.8	55.7	50.8	68.5	72.2	81.0	82.5	47.7	50.6	47.4	50.6	53.0	53.2
Nb	1.80	1.71	1.85	1.84	3.43	2.37	2.27	2.35	1.86	1.55	1.59	2.04	1.57	1.55
Mo	0.54	0.87	0.70	0.57	1.60	2.16	2.01	1.86	0.33	0.33	0.37	0.25	<0.097	0.34
Ag	1.22	1.09	1.08	4.80	0.02	0.08	0.02	0.07	0.34	0.55	0.57	0.53	0.47	0.27
Cd	<0.52	<0.52	0.16	<0.52	<0.83	0.70	<0.33	0.59	0.18	0.16	0.31	<0.55	<0.65	<0.40
In	1.27	1.20	1.43	9.69	2.59	2.71	2.22	2.69	0.59	0.67	0.73	0.84	0.65	0.67
Sn	341	316	313	2378	687	664	623	697	168	197	207	217	158	152
Sb	1078	1037	976	1667	3296	2913	2179	2193	43	42	49	49	36	33
Cs	0.087	0.142	0.124	0.179	0.204	0.231	0.210	0.193	0.295	0.434	0.409	0.416	0.467	0.479
Ba	242	240	237	203	300	297	285	293	138	157	152	155	138	130
La	6.695	7.268	6.856	6.725	8.063	8.454	7.973	7.501	5.912	5.730	5.377	6.134	5.408	5.458
Ce	12.134	12.526	12.124	10.319	13.920	13.589	13.569	13.127	11.037	11.199	11.360	12.399	10.583	10.694
Pr	1.468	1.699	1.508	1.167	1.625	1.605	1.775	1.785	1.352	1.301	1.523	1.544	1.362	1.261
Nd	6.163	6.846	6.595	5.215	7.301	6.769	7.030	7.150	5.821	5.761	5.680	6.195	4.893	5.630
Sm	1.046	1.126	1.106	1.349	1.625	1.946	1.294	1.464	1.382	1.453	1.574	1.614	1.049	0.787
Eu	0.293	0.408	0.317	0.379	0.413	0.489	0.466	0.566	0.383	0.428	0.272	0.306	0.415	0.358
Gd	0.865	1.538	1.015	1.168	1.093	1.444	1.484	1.294	1.059	1.110	0.878	0.817	0.827	1.251
Tb	0.197	0.187	0.104	0.171	0.216	0.191	0.194	0.240	0.168	0.204	0.198	0.212	0.148	0.124
Dy	0.886	1.035	1.116	1.023	1.354	1.274	1.133	1.444	0.878	1.009	0.859	0.797	0.999	0.898
Ho	0.222	0.230	0.185	0.258	0.319	0.263	0.279	0.212	0.241	0.139	0.229	0.234	0.200	0.257
Er	0.635	0.855	0.509	0.799	0.739	0.558	0.769	0.824	0.684	0.718	0.693	0.601	0.726	0.680
Tm	0.089	0.131	0.069	0.052	0.069	0.125	0.116	0.128	0.051	0.093	0.076	0.080	0.079	0.052
Yb	0.653	0.623	0.653	0.695	0.622	0.572	0.589	1.073	0.696	0.542	0.585	0.656	0.736	0.535
Lu	0.118	0.087	0.096	0.093	0.128	0.079	0.160	0.119	0.049	0.082	0.065	0.093	0.060	0.104
Hf	1.558	1.337	0.975	1.218	1.855	1.855	2.036	1.494	1.463	1.322	1.180	1.735	0.999	1.180
Ta	0.078	0.061	0.136	0.085	0.128	0.106	0.095	0.139	0.104	0.144	0.075	0.085	0.114	0.102
W	0.375	0.318	0.338	0.325	0.643	0.852	0.613	0.872	0.063	0.108	<0.120	<0.136	0.224	<0.071
Au	0.607	0.585	0.694	6.574	0.515	0.802	0.842	0.560	0.101	0.524	0.179	0.475	0.429	0.169
Tl	0.027	<0.035	0.032	0.174	0.049	0.054	0.118	0.102	<0.033	<0.043	<0.042	<0.038	<0.045	<0.039
Pb	1818	2017	1741	15123	7233	6846	6203	5830	297	328	336	318	242	247
Bi	0.241	0.207	0.275	6.473	0.778	0.536	0.630	0.532	0.114	0.090	0.233	0.155	<0.066	0.103
Th	0.833	1.014	0.996	1.026	1.294	1.284	1.344	1.324	0.895	0.928	1.019	1.026	0.793	1.024
U	0.995	1.136	1.035	0.846	1.073	1.143	1.103	1.153	0.786	0.835	1.059	0.918	0.797	0.812

	CO88				CO92					CO94		
Li	6.9	<2.59	6.9	7.2	6.9	4.7	5.2	7.3	5.9	5.4	5.9	3.3
Be	<5.16	<4.24	<2.99	1.7	<2.99	4.4	<2.17	<1.93	2.7	<3.47	<7.76	<3.65
B	109	123	140	88	140	168	152	134	148	87	81	71
Sc	2.6	2.9	4.1	2.1	4.1	4.4	4.7	3.8	3.8	2.7	2.1	2.2
Ti	555	584	1079	523	1079	1075	1062	1041	1035	362	358	386
V	16	14	29	13	29	29	29	30	29	7	7	8
Cr	14	20	23	12	23	22	26	21	28	14	11	15
Co	16	17	73	16	73	72	71	71	68	1	1	1
Ni	10	12	28	12	28	28	27	27	29	6	3	5
Cu	1602	1743	3142	1498	3142	3245	3195	3130	3191	12	12	13
Zn	190	216	621	167	621	607	606	571	539	8	5	6
Ga	2.7	2.9	3.8	2.0	3.8	3.3	3.8	3.4	3.8	2.8	2.8	2.5
Ge	<0.62	0.8	1.1	<0.74	1.1	1.6	1.6	2.0	1.6	1.2	<0.79	1.1
As	19.7	23.3	38.6	16.4	38.6	39.1	43.0	41.6	40.0	1.0	1.0	<0.87
Rb	16.8	10.5	11.3	10.7	11.3	10.8	10.2	10.8	10.9	7.7	7.9	8.0
Sr	424	443	603	441	603	612	600	602	609	351	361	346
Y	5.8	6.4	8.1	6.3	8.1	8.8	8.1	8.4	9.0	5.3	5.6	5.5
Zr	50.8	53.8	95.7	52.8	95.7	95.0	104.7	113.1	91.5	39.1	36.2	37.6
Nb	1.84	1.53	2.93	1.45	2.93	2.86	2.84	2.87	2.77	1.39	1.35	1.21
Mo	0.57	0.92	2.14	0.93	2.14	2.62	2.04	2.50	1.99	0.25	<0.122	0.21
Ag	4.80	5.44	9.29	3.95	9.29	9.76	8.79	9.36	8.99	<0.065	<0.132	<0.083
Cd	<0.52	<0.64	<0.43	<0.33	<0.43	<0.39	<0.25	<0.22	<0.49	<0.57	0.92	<0.48
In	9.69	8.50	8.87	8.54	8.87	9.78	8.98	9.14	8.89	0.03	0.04	<0.0134
Sn	2378	2299	2890	2118	2890	2904	2849	2885	2845	2	2	2
Sb	1667	1878	3384	1360	3384	3515	3544	3243	3324	<0.54	-	-
Cs	0.179	0.211	0.170	0.254	0.170	0.230	0.179	0.177	0.247	0.061	0.108	0.059
Ba	203	216	336	204	336	333	327	330	323	175	180	177
La	6.725	7.188	8.998	6.614	8.998	8.827	8.386	8.486	8.556	5.684	5.311	5.724
Ce	10.319	20.668	15.026	12.222	15.026	14.565	14.615	14.455	14.635	10.914	9.876	10.511
Pr	1.167	1.388	1.986	1.255	1.986	1.816	1.826	1.986	1.856	1.240	1.270	1.199
Nd	5.215	6.534	8.346	5.779	8.346	8.225	7.694	7.543	8.085	5.452	5.522	5.129
Sm	1.349	1.158	1.575	1.158	1.575	1.775	1.545	1.595	1.515	1.068	1.149	1.139
Eu	0.379	0.395	0.453	0.356	0.453	0.504	0.375	0.442	0.391	0.290	0.350	0.308
Gd	1.168	1.057	1.465	1.369	1.465	2.046	1.354	1.555	1.575	0.907	0.887	1.149
Tb	0.171	0.199	0.250	0.127	0.250	0.266	0.270	0.198	0.255	0.148	0.180	0.115
Dy	1.023	1.399	1.364	1.349	1.364	1.174	1.304	1.775	1.595	0.967	1.078	0.897
Ho	0.258	0.235	0.293	0.190	0.293	0.304	0.322	0.314	0.277	0.188	0.266	0.173
Er	0.799	0.809	0.917	0.693	0.917	0.768	0.875	1.037	0.624	0.569	0.433	0.624
Tm	0.052	0.087	0.160	0.065	0.160	0.126	0.105	0.127	0.128	0.063	0.086	0.081
Yb	0.695	0.602	0.883	0.469	0.883	0.873	0.768	0.493	0.804	0.816	0.220	0.409
Lu	0.093	0.142	0.082	0.091	0.082	0.125	0.084	0.089	0.122	0.112	0.066	0.086
Hf	1.218	1.420	2.799	1.228	2.799	2.257	2.508	2.427	2.137	0.967	0.877	1.028
Ta	0.085	0.095	0.214	0.166	0.214	0.139	0.171	0.187	0.177	0.089	0.097	0.061
W	0.325	0.516	0.560	0.343	0.560	0.398	0.474	0.282	0.492	0.048	<0.074	0.126
Au	6.574	7.561	2.327	5.738	2.327	2.718	3.090	2.779	2.859	<0.045	<0.057	<0.080
Tl	0.174	0.233	0.328	0.162	0.328	0.270	0.186	0.225	0.232	0.062	<0.027	<0.044
Pb	15123	16830	17630	13483	17630	18162	17870	17635	17119	13	12	13
Bi	6.473	4.712	3.762	3.785	3.762	3.210	3.360	3.711	3.019	<0.032	<0.058	<0.054
Th	1.026	1.102	1.535	0.975	1.535	1.404	1.374	1.354	1.505	0.730	0.738	0.718
U	0.846	1.017	1.274	0.869	1.274	1.334	1.224	1.194	1.204	0.704	0.577	0.525

	CO95				CO96				CO99				CO100A db			
Li	2.2	3.8	4.1	4.1	7.9	9.0	4.9	5.4	2.3	6.9	5.0	2.0	7.3	6.8	8.6	5.4
Be	<6.90	1.8	1.6	<7.71	<5.77	<6.00	<3.65	<3.81	1.6	3.5	<8.15	<3.71	<2.21	<3.94	2.8	1.0
B	170	145	145	160	143	134	140	160	226	226	215	233	102	83	78	104
Sc	4.0	3.3	3.1	3.7	3.0	3.3	3.3	2.9	7.3	7.3	6.7	7.2	4.5	4.3	4.6	5.1
Ti	948	924	936	941	846	862	882	909	3342	3402	3459	3329	815	826	766	906
V	25	26	26	25	24	25	25	24	57	58	60	59	19	19	17	20
Cr	22	23	22	21	23	19	26	26	72	70	69	68	26	22	20	28
Co	36	27	28	28	41.3	43.7	41.0	45.3	16	16	17	17	25	23	19	29
Ni	15	15	15	14	19	22	25	26	19	18	17	16	21	19	21	133
Cu	1801	1775	1851	1792	2503	2513	2578	2721	86	83	85	83	2000	1815	1499	2486
Zn	78	67	76	72	134	177	228	207	30	30	31	28	105	151	144	280
Ga	3.3	3.2	2.8	2.8	3.0	3.2	3.2	3.3	4.6	4.0	4.4	4.9	3.1	3.8	3.0	3.8
Ge	1.7	2.0	1.3	0.8	<0.80	1.3	1.4	1.3	1.6	2.1	1.7	2.0	1.0	0.8	1.5	1.3
As	20.0	21.2	20.0	19.0	18.7	24.1	27.2	21.8	12.1	10.5	11.9	11.6	13.7	13.4	11.2	30.0
Rb	9.8	9.1	9.5	9.3	12.8	11.7	11.9	14.1	5.9	5.4	5.3	5.2	14.3	16.0	16.6	13.5
Sr	502	498	500	500	539	521	526	527	410	418	424	417	429	449	430	445
Y	8.1	8.0	8.1	7.8	7.7	7.5	7.6	8.2	12.2	13.1	13.3	13.2	7.6	7.7	7.9	7.5
Zr	94.5	92.5	92.5	90.9	80.7	82.1	84.8	86.1	297.4	296.2	298.5	298.7	67.4	71.1	67.9	74.8
Nb	2.43	2.25	2.18	2.32	2.44	2.48	2.53	2.35	5.75	6.34	5.99	5.89	2.10	2.60	2.07	2.40
Mo	1.99	1.65	1.86	2.34	2.32	2.83	2.63	1.98	3.24	3.75	3.25	4.57	1.02	1.13	0.91	1.52
Ag	2.15	1.85	2.06	1.75	2.73	3.04	2.98	2.74	<0.059	<0.046	0.06	<0.041	2.20	1.93	1.72	1.01
Cd	<0.46	0.73	<0.35	0.35	<0.48	<0.33	<0.49	0.10	<0.36	0.36	<0.47	<0.43	0.12	<0.59	<0.50	<0.61
In	1.48	1.30	1.53	1.50	2.72	3.78	4.01	3.46	<0.0216	<0.0171	0.03	0.05	2.35	2.73	2.11	6.30
Sn	408	354	373	388	675	969	1034	904	1	1	1	1	583	692	553	1620
Sb	1776	1714	1756	1732	1274	1317	1236	1223	-		1	<0.31	960	1001	762	1122
Cs	0.182	0.127	0.119	0.156	0.129	0.101	0.124	0.125	0.134	0.128	0.122	0.122	0.174	0.149	0.268	0.262
Ba	324	322	322	316	294	301	314	311	842	844	845	838	253	269	256	266
La	8.096	8.016	7.776	7.776	7.967	7.967	8.118	8.148	11.976	11.532	12.570	12.076	6.998	7.430	7.390	7.681
Ce	13.700	13.000	12.940	12.850	13.661	13.027	13.500	13.429	19.217	19.489	20.416	19.499	12.902	13.655	13.274	14.509
Pr	1.613	1.658	1.646	1.538	1.648	1.622	1.728	1.929	2.760	2.589	2.740	2.830	1.496	1.677	1.667	1.707
Nd	7.466	7.225	7.305	7.456	6.961	7.444	7.957	7.957	10.263	10.989	10.878	10.535	6.135	6.918	7.350	7.259
Sm	1.851	1.881	1.631	1.641	1.479	1.298	1.388	2.072	2.528	2.649	2.337	1.894	1.125	2.018	1.185	1.345
Eu	0.439	0.409	0.361	0.354	0.287	0.409	0.512	0.435	0.578	0.615	0.614	0.728	0.282	0.455	0.325	0.359
Gd	0.991	1.601	1.651	1.461	1.137	1.660	1.549	1.257	1.924	2.045	2.427	2.196	1.145	1.115	0.864	1.145
Tb	0.201	0.266	0.228	0.216	0.234	0.158	0.209	0.207	0.335	0.411	0.416	0.403	0.200	0.234	0.182	0.266
Dy	0.951	1.121	1.005	1.531	1.418	1.107	1.589	1.630	2.417	2.236	2.055	2.296	1.356	1.396	1.175	1.325
Ho	0.282	0.309	0.358	0.299	0.299	0.265	0.288	0.388	0.472	0.441	0.456	0.529	0.323	0.264	0.226	0.304
Er	0.891	0.570	0.815	0.719	0.768	0.793	0.847	0.702	1.269	1.662	1.188	1.319	0.489	0.657	0.673	0.517
Tm	0.142	0.095	0.113	0.066	0.127	0.102	0.112	0.098	0.234	0.178	0.205	0.207	0.093	0.134	0.094	0.086
Yb	0.931	0.630	0.881	0.640	0.915	0.636	0.724	0.518	1.511	1.400	1.350	1.541	0.495	0.823	0.743	0.661
Lu	0.094	0.129	0.099	0.088	0.138	0.098	0.149	0.143	0.215	0.215	0.228	0.194	0.075	0.080	0.092	0.115
Hf	2.432	1.911	1.751	2.712	2.183	2.344	2.394	2.424	6.496	7.232	7.272	7.050	1.627	1.757	1.797	1.717
Ta	0.179	0.190	0.205	0.162	0.137	0.171	0.134	0.105	0.335	0.408	0.422	0.389	0.094	0.124	0.061	0.124
W	0.679	0.862	0.916	1.001	0.716	0.540	0.665	1.137	1.033	1.168	1.068	1.138	0.372	0.396	0.192	0.431
Au	0.388	0.487	0.389	0.326	1.358	1.620	0.790	0.788	0.035	<0.034	0.054	<0.00	0.914	0.723	0.681	0.620
Tl	0.127	0.042	0.095	0.073	0.033	0.108	0.089	0.113	<0.029	<0.0227	<0.022	<0.028	<0.024	0.062	0.058	0.108
Pb	4661	4539	4642	4571	4441	5936	7421	5917	7	7	8	8	5049	4119	2925	7702
Bi	0.320	0.312	0.372	0.348	0.571	0.659	0.649	0.623	0.140	0.054	0.072	0.029	0.380	0.540	0.495	0.622
Th	1.331	1.395	1.580	1.337	1.371	1.368	1.404	1.429	2.437	2.447	2.538	2.437	1.145	1.179	1.074	1.285
U	1.033	0.987	1.001	1.006	1.013	0.972	1.070	0.988	1.225	1.292	1.273	1.291	1.094	1.034	1.205	1.044

	CO100A lb			CO100B				CO121A				CO121B			CO121C			
Li	6.2	7.0	3.9	3.2	3.8	5.4	2.0	7.8	6.7	8.4	9.6	3.5	9.5	8.5	3.9	7.5	3.8	<3.06
Be	<4.59	<2.57	<5.00	<2.82	1.3	5.8	<2.78	<5.71	<3.68	<3.29	1.3	<5.67	<4.19	<5.65	<7.38	<4.09	<6.87	<4.85
B	91	104	99	120	124	143	127	151	134	139	140	156	149	136	135	142	128	160
Sc	4.8	5.3	4.6	2.3	2.3	3.1	2.8	2.6	3.2	2.8	3.4	3.1	3.2	2.7	3.0	2.7	3.1	2.2
Ti	898	888	867	623	616	625	599	896	904	845	949	762	819	689	636	636	610	654
V	19	19	19	22	19	20	19	24	24	24	24	19	22	17	18	17	17	18
Cr	25	32	21	19	17	20	20	23	26	23	30	29	25	20	18	14	16	14
Co	40	39	25	18	<1.06	20	19	28	27	24	25	29	22	21	14	13	14	13
Ni	31	32	19	21	21	17	20	16	21	19	18	18	18	13	12	12	10	10
Cu	2735	2763	2490	1554	1608	1559	1470	1263	1245	1200	1224	1957	1762	1927	1443	1511	1520	1490
Zn	446	441	135	32	33	33	33	64	77	83	65	91	87	66	49	61	58	61
Ga	3.4	3.5	2.8	2.3	2.8	2.6	2.3	2.7	2.7	3.1	3.3	3.0	2.9	2.9	2.7	2.9	2.5	2.4
Ge	1.5	<0.74	<1.02	1.5	0.7	1.3	<0.40	0.8	2.0	<0.62	<0.66	0.9	1.4	<0.70	<0.69	1.0	<0.81	1.5
As	57.8	60.4	13.0	17.4	18.7	18.3	18.0	15.8	15.8	16.3	15.1	16.1	16.0	14.4	15.7	13.8	14.3	17.9
Rb	12.5	12.6	12.3	8.0	7.5	8.0	7.8	9.0	9.4	8.7	9.0	10.7	14.5	10.1	8.3	9.2	8.8	8.8
Sr	425	428	442	427	431	429	424	456	465	456	470	458	435	436	426	425	442	451
Y	7.5	7.5	7.6	5.9	5.9	6.1	6.0	7.5	7.1	6.8	7.6	7.4	7.8	6.7	5.9	6.5	7.2	6.9
Zr	73.6	76.3	72.0	54.6	58.2	56.1	53.4	76.9	83.4	74.5	87.0	68.1	67.3	61.7	56.9	56.6	58.5	59.7
Nb	2.36	2.45	2.26	1.88	1.65	1.71	1.81	2.32	2.22	2.05	2.29	2.04	2.42	1.96	1.72	1.74	1.67	1.85
Mo	1.21	1.14	1.18	2.02	1.69	1.52	1.31	1.84	2.29	1.77	2.55	1.62	1.28	1.03	1.61	1.32	1.50	1.39
Ag	2.44	2.58	2.08	2.06	2.45	2.05	1.67	1.28	1.19	1.20	1.40	2.14	1.28	1.88	1.38	0.94	1.03	1.39
Cd	0.77	<0.64	1.14	<0.22	<0.60	<0.21	<0.19	<0.65	<0.68	<0.43	<0.49	<0.61	0.46	<0.49	0.32	0.26	<0.93	0.43
In	14.59	15.39	2.55	0.69	0.75	0.82	0.75	1.47	2.75	2.80	2.10	1.77	1.54	1.82	0.98	1.64	1.17	0.86
Sn	3933	4034	597	174	182	210	202	354	736	706	504	475	406	449	262	428	279	250
Sb	955	990	983	1432	1357	1447	1379	1278	1243	1120	1114	1425	1302	1439	1432	1549	1655	1429
Cs	0.161	0.235	0.169	0.154	0.152	0.178	0.190	0.199	0.212	0.118	0.129	0.214	0.269	0.140	0.243	0.176	0.178	0.115
Ba	255	257	259	263	258	267	252	313	312	310	313	260	251	247	284	259	276	295
La	7.551	7.641	7.088	5.921	6.062	6.162	5.901	7.149	7.502	6.714	7.199	7.098	8.019	6.418	6.756	6.896	6.816	7.117
Ce	13.382	13.624	12.719	11.079	10.668	11.320	11.210	12.389	12.257	12.379	12.671	12.705	13.836	11.994	11.762	11.300	12.325	10.998
Pr	1.790	1.739	1.860	1.234	1.405	1.505	1.254	1.642	1.686	1.656	1.598	1.522	1.722	1.442	1.468	1.498	1.478	1.417
Nd	6.988	6.696	7.350	5.791	6.463	4.948	5.299	6.411	7.573	7.785	7.098	6.938	7.549	6.848	5.961	6.203	6.183	6.615
Sm	1.106	1.709	1.840	1.014	1.174	1.014	0.933	1.434	1.575	1.535	1.939	1.592	1.211	1.572	1.216	1.448	1.025	1.046
Eu	0.417	0.459	0.445	0.197	0.222	0.250	0.274	0.465	0.422	0.492	0.372	0.400	0.431	0.355	0.224	0.364	0.339	0.333
Gd	1.186	1.589	1.458	1.194	1.044	1.104	0.903	1.272	1.928	1.515	1.111	1.191	1.261	1.121	0.945	1.387	1.216	0.875
Tb	0.192	0.260	0.148	0.143	0.142	0.128	0.130	0.125	0.256	0.228	0.221	0.160	0.214	0.144	0.149	0.186	0.218	0.195
Dy	1.327	1.398	1.367	1.194	0.874	0.933	0.932	1.181	1.333	1.535	1.131	1.261	1.292	1.041	1.035	0.829	0.965	1.739
Ho	0.225	0.289	0.330	0.187	0.217	0.193	0.183	0.258	0.358	0.256	0.266	0.235	0.244	0.239	0.262	0.231	0.273	0.204
Er	0.734	0.804	0.680	0.437	0.567	0.401	0.635	0.749	0.671	0.504	0.870	0.981	0.770	0.702	0.632	0.807	0.640	0.675
Tm	0.082	0.108	0.115	0.067	0.073	0.116	0.066	0.079	0.117	0.105	0.139	0.102	0.132	0.095	0.068	0.121	0.080	0.075
Yb	0.744	0.693	0.346	0.702	0.556	0.413	0.502	0.670	0.596	0.737	0.939	0.841	0.589	0.273	0.724	0.694	0.519	0.533
Lu	0.098	0.078	0.098	0.047	0.080	0.054	0.072	0.126	0.104	0.120	0.089	0.040	0.064	0.146	0.111	0.072	0.098	0.091
Hf	1.971	2.142	2.071	1.566	1.435	1.184	1.465	1.817	1.979	1.918	1.797	1.372	2.233	1.282	1.629	1.639	1.518	1.598
Ta	0.143	0.158	0.134	0.145	0.098	0.108	0.112	0.116	0.122	0.118	0.113	0.121	0.137	0.190	0.079	0.180	0.083	0.155
W	0.427	0.329	0.217	0.490	0.548	0.639	0.743	0.705	0.592	0.467	0.509	0.704	0.700	0.871	0.518	1.136	0.701	0.855
Au	0.672	0.955	0.784	1.425	1.425	1.475	1.746	0.515	0.625	0.510	0.449	0.904	1.251	0.981	0.765	0.439	0.724	0.844
Tl	0.141	0.125	<0.044	0.054	0.050	0.061	0.056	0.055	0.097	0.087	0.046	0.072	0.020	0.069	0.096	0.052	0.081	<0.027
Pb	13132	13006	4340	2501	2569	2647	3082	3005	3343	3484	3543	4656	3611	3981	3014	3683	3669	3215
Bi	0.914	0.860	0.347	0.221	0.253	0.230	0.220	0.202	0.214	0.149	0.206	0.348	0.308	0.178	0.165	3.418	1.151	0.283
Th	1.097	1.119	1.327	0.749	0.988	0.892	0.842	1.158	1.276	1.228	1.154	1.230	1.422	1.302	1.216	1.237	1.176	1.146
U	1.207	1.056	1.076	1.044	0.803	0.953	0.863	1.033	0.732	1.132	0.989	0.958	0.903	1.036	1.045	1.116	1.034	1.004

	CO121D				CO121E				CO122			CO184A		
Li	5.1	7.1	3.7	8.8	<2.15	4.3	4.0	3.9	7.6	3.2	4.0	5.6	6.0	4.0
Be	<3.78	<6.77	<3.06	4.6	1.7	<0.00	<7.39	3.7	<6.89	<5.54	<5.14	<3.73	<5.12	<3.33
B	191	160	157	162	155	171	181	159	132	153	170	146	139	146
Sc	2.9	3.0	2.9	3.7	2.7	2.5	2.1	3.0	3.1	2.5	2.2	3.2	3.4	3.3
Ti	757	809	747	810	562	572	569	563	719	552	573	834	848	860
V	22	24	23	23	16	16	16	16	21	17	17	24	23	23
Cr	19	22	15	23	12	11	8	9	19	18	28	32	31	28
Co	40	39	38	42	4	5	5	4	264	285	278	42	40	41
Ni	15	16	14	17	8	7	9	7	27	23	31	24	24	21
Cu	2603	2514	2590	2494	15	16	16	15	2353	2671	2423	1899	1962	1864
Zn	93	91	86	97	18	22	18	23	71	79	64	161	177	161
Ga	2.8	2.8	2.9	2.7	2.8	2.6	2.9	2.2	3.4	3.5	3.3	2.8	3.1	3.9
Ge	<0.74	1.5	<0.53	0.8	1.2	<0.69	1.0	1.5	1.5	<0.77	1.9	2.2	<0.61	0.8
As	24.5	22.5	24.6	27.0	21.1	24.4	22.4	24.3	18.3	24.2	30.0	21.3	21.4	23.4
Rb	9.4	9.2	9.2	8.9	5.4	5.4	5.0	4.3	10.8	10.8	11.4	12.6	11.7	11.9
Sr	485	482	477	483	425	420	426	426	486	481	450	458	460	458
Y	6.9	7.2	6.9	7.7	6.3	6.3	6.3	6.3	7.2	6.8	6.6	7.7	7.2	7.1
Zr	73.6	75.6	70.8	74.2	54.3	54.3	54.1	52.2	127.0	54.7	55.4	75.9	73.9	75.3
Nb	2.04	2.26	2.30	1.98	1.85	1.79	1.68	1.86	1.93	1.78	1.58	2.48	2.20	2.17
Mo	2.31	1.66	1.81	2.22	0.46	0.45	0.40	0.55	1.85	2.17	2.05	1.71	1.48	1.35
Ag	6.45	6.97	6.74	6.33	<0.080	0.06	<0.091	<1.43	1.44	1.07	1.28	1.66	1.75	2.04
Cd	<0.49	<0.48	<0.48	0.26	<0.46	<0.47	<0.37	<0.33	0.14	<0.35	<0.32	<0.68	<0.46	<0.52
In	1.55	1.77	1.43	1.79	<0.025	0.04	<0.0145	<0.0244	1.13	0.84	0.78	2.66	2.66	2.67
Sn	415	438	370	446	2	2	2	2	234	153	158	714	657	640
Sb	2868	2806	2725	2875	2060	1998	2002	2015	4842	6631	7561	1922	1876	1919
Cs	0.123	0.181	0.229	0.178	0.078	0.046	0.066	0.098	0.208	0.108	0.139	0.173	0.215	0.250
Ba	290	290	282	292	181	179	175	174	220	230	227	284	274	276
La	7.482	6.830	7.192	7.533	6.608	6.518	6.809	6.558	6.694	6.765	6.592	7.421	7.250	7.149
Ce	11.494	12.367	11.946	12.136	11.319	11.299	10.917	11.218	11.724	11.214	11.520	12.358	12.348	12.921
Pr	1.474	1.594	1.655	1.459	1.456	1.486	1.355	1.377	1.582	1.510	1.351	1.629	1.609	1.800
Nd	6.399	6.058	6.018	6.148	6.458	7.060	5.735	6.568	6.877	6.092	5.969	7.632	6.315	7.019
Sm	1.174	1.424	1.113	1.324	0.944	1.637	1.165	1.255	0.837	1.378	1.398	1.096	1.187	1.086
Eu	0.380	0.334	0.316	0.423	0.300	0.259	0.298	0.414	0.392	0.284	0.371	0.270	0.341	0.328
Gd	1.274	1.194	0.993	1.374	1.055	1.306	1.105	0.714	1.265	0.857	1.153	1.579	1.126	1.569
Tb	0.152	0.182	0.168	0.238	0.181	0.162	0.142	0.140	0.218	0.137	0.213	0.231	0.203	0.231
Dy	1.224	1.585	0.993	1.184	1.145	1.125	1.115	1.145	1.092	1.214	1.214	1.126	1.247	1.217
Ho	0.164	0.292	0.216	0.232	0.245	0.184	0.218	0.182	0.289	0.274	0.260	0.223	0.309	0.308
Er	0.597	0.743	0.627	0.660	0.639	0.672	0.725	0.594	0.379	0.737	0.722	0.723	0.728	0.726
Tm	0.089	0.098	0.088	0.105	0.079	0.043	0.080	0.094	0.082	0.111	0.076	0.113	0.083	0.132
Yb	0.542	0.832	0.625	0.298	1.024	0.543	0.333	0.502	0.442	0.714	0.765	0.585	0.599	1.076
Lu	0.098	0.091	0.091	0.109	0.069	0.049	0.068	0.126	0.130	0.123	0.118	0.153	0.054	0.120
Hf	1.414	1.535	1.996	1.896	0.954	1.547	1.527	0.653	3.490	1.500	1.429	2.102	2.242	1.931
Ta	0.168	0.127	0.125	0.088	0.077	0.080	0.102	0.088	0.095	0.089	0.098	0.141	0.127	0.095
W	1.093	0.791	0.629	1.204	0.158	<0.130	0.094	0.203	0.361	0.395	0.424	0.746	0.739	0.726
Au	0.877	1.053	0.864	1.131	<0.043	<0.044	<0.097	0.301	0.309	0.583	0.540	1.227	1.136	1.498
Tl	<0.045	0.055	0.081	0.087	0.039	<0.031	0.009	0.043	0.038	0.081	0.030	0.088	0.048	0.026
Pb	4778	4699	4379	4684	22	23	22	21	2300	2205	2799	5190	5386	5359
Bi	0.359	0.358	0.238	0.396	<0.037	0.085	0.090	0.064	0.269	0.308	0.372	0.563	0.528	0.577
Th	1.113	1.413	1.154	1.248	0.964	1.055	0.965	0.897	1.125	1.219	1.114	1.238	1.306	1.200
U	1.070	1.016	0.847	0.936	0.858	0.852	0.820	0.712	0.962	0.929	0.935	0.849	0.889	1.028

	CO184B				CO184C				CO230				CO233A			
Li	4.2	4.5	2.7	5.5	2.5	7.3	4.9	4.4	1.7	5.1	7.9	4.2	5.1	<2.75	3.1	3.7
Be	<7.27	<4.75	<3.49	<0.00	<6.25	3.1	<3.94	<8.26	<4.52	<7.80	<4.30	4.8	<5.74	<4.33	<7.16	3.5
B	165	146	160	153	182	143	153	153	108	74	98	105	98	113	86	97
Sc	3.1	2.8	2.2	2.8	3.1	3.2	2.6	2.9	2.5	2.9	2.7	2.5	3.5	3.8	4.3	3.3
Ti	691	729	545	702	805	798	765	777	533	528	543	571	1568	1540	1516	1520
V	20	19	15	21	23	23	21	21	11	10	11	11	20	22	21	21
Cr	19	16	17	19	27	26	22	18	17	23	31	24	31	31	25	23
Co	25	26	19	27	51	50	44	45	8	7	6	9	6	7	6	7
Ni	13	12	10	12	22	19	16	15	11	14	12	19	7	7	8	7
Cu	2230	2259	1691	2213	2068	2107	2041	2010	580	571	623	654	25	26	24	23
Zn	61	63	44	62	128	133	99	95	110	120	177	371	26	32	26	33
Ga	2.6	3.0	2.9	2.3	2.7	3.2	3.2	2.7	2.4	3.2	2.3	2.8	3.1	3.2	3.0	3.1
Ge	0.8	2.0	<0.40	1.5	0.7	1.0	0.9	0.8	<1.03	1.2	1.4	2.1	2.0	2.1	1.6	<0.70
As	21.7	22.0	18.6	25.2	29.0	29.5	23.5	24.7	6.8	7.2	9.5	19.5	1.1	0.9	0.8	1.1
Rb	9.1	8.8	19.6	8.5	8.5	8.2	8.0	8.5	9.8	8.7	9.2	9.2	5.8	5.8	5.3	6.7
Sr	459	468	432	460	458	457	456	462	417	398	395	410	179	179	169	177
Y	7.1	6.7	4.9	6.9	7.2	6.9	7.1	7.1	6.4	6.2	6.5	6.6	6.6	6.7	6.2	6.3
Zr	64.6	65.7	60.9	64.6	72.6	73.8	70.9	71.3	50.5	49.4	51.0	49.7	178.0	180.2	176.9	171.5
Nb	2.05	1.82	1.72	2.13	2.15	2.02	2.13	1.96	1.56	1.45	1.64	1.92	3.54	3.55	3.57	3.19
Mo	1.75	1.58	1.21	1.74	1.73	2.04	1.80	2.23	0.99	0.34	0.36	0.67	<0.207	0.41	0.51	0.22
Ag	1.44	2.14	1.26	1.81	2.23	2.13	1.98	2.34	0.90	0.97	1.44	0.70	<0.110	0.14	0.19	0.11
Cd	0.43	0.74	<0.35	<0.38	0.34	<0.40	0.50	0.28	<0.45	<0.77	0.56	0.66	<0.55	<0.41	<0.56	0.44
In	0.95	1.16	1.12	1.10	2.07	2.25	1.43	1.26	2.92	2.54	2.81	5.14	0.04	0.03	0.05	<0.034
Sn	249	277	265	252	488	495	366	337	747	664	788	1295	4	5	3	4
Sb	2307	2340	1823	2314	2576	2616	2110	2070	325	171	180	161	14	17	8	17
Cs	0.200	0.185	0.275	0.222	0.134	0.134	0.112	0.136	0.167	0.114	0.164	0.108	0.057	0.067	0.078	0.092
Ba	279	284	241	287	291	288	289	288	207	199	201	200	168	172	161	167
La	7.088	6.947	4.836	6.585	6.673	6.763	6.833	6.844	6.082	5.831	6.273	6.002	6.602	6.944	6.420	6.692
Ce	11.371	11.803	10.064	12.004	12.082	11.770	11.419	11.660	11.362	11.040	10.298	10.980	13.123	13.002	13.183	13.465
Pr	1.508	1.538	1.317	1.568	1.475	1.646	1.495	1.515	1.405	1.564	1.215	1.354	1.553	1.606	1.463	1.574
Nd	6.223	7.158	4.182	6.967	6.432	6.392	6.663	6.081	7.507	6.604	5.982	5.018	6.088	6.823	6.783	6.632
Sm	1.739	1.196	0.714	1.146	1.034	1.395	1.425	1.355	1.194	1.204	1.325	1.074	1.469	1.348	1.057	1.369
Eu	0.314	0.373	0.274	0.404	0.362	0.450	0.254	0.310	0.515	0.325	0.333	0.355	0.286	0.334	0.217	0.328
Gd	0.985	1.136	1.036	1.357	1.385	1.274	1.024	1.264	1.064	1.686	1.124	1.034	1.208	1.067	1.077	0.896
Tb	0.154	0.148	0.126	0.298	0.181	0.141	0.228	0.192	0.176	0.166	0.140	0.164	0.175	0.081	0.142	0.198
Dy	1.217	1.106	0.965	1.267	0.943	1.034	1.234	1.194	0.903	1.345	1.345	0.792	1.187	1.238	1.177	1.198
Ho	0.250	0.258	0.137	0.250	0.290	0.202	0.243	0.209	0.256	0.209	0.199	0.169	0.214	0.218	0.188	0.261
Er	0.804	0.646	0.468	0.915	0.407	0.913	0.516	0.782	0.649	0.763	0.509	0.429	0.539	0.687	0.631	0.751
Tm	0.118	0.105	0.085	0.068	0.054	0.062	0.081	0.128	0.064	0.095	0.094	0.074	0.072	0.134	0.097	0.093
Yb	0.513	0.804	0.258	0.379	0.560	0.803	0.733	0.722	0.474	0.322	0.763	0.763	0.615	1.127	0.684	0.575
Lu	0.099	0.094	0.063	<0.027	0.115	0.136	0.094	0.151	0.099	0.077	0.104	0.079	0.125	0.123	0.114	0.089
Hf	1.669	1.679	2.312	1.920	1.866	1.666	1.415	1.696	1.425	0.913	1.295	0.923	4.931	4.166	3.713	3.864
Ta	0.137	0.121	0.243	0.109	0.134	0.184	0.137	0.111	0.104	0.114	0.127	0.103	0.194	0.251	0.267	0.208
W	0.530	0.739	0.684	0.744	0.710	0.719	0.550	0.721	0.354	0.173	0.162	0.081	0.102	<0.125	0.206	0.109
Au	1.438	1.548	0.925	1.106	1.204	0.933	0.859	0.538	0.678	0.231	0.117	0.302	<0.00	0.061	<0.052	<0.067
Tl	0.106	<0.053	0.059	0.111	0.121	0.046	0.040	0.053	0.073	0.088	0.052	0.135	0.040	<0.027	<0.036	0.032
Pb	4549	4693	3776	4539	5351	5381	4217	3952	3250	3079	3488	4200	44	49	36	46
Bi	0.252	0.411	0.246	0.245	0.438	0.426	0.382	0.417	0.482	0.802	0.928	1.066	<0.037	<0.023	0.041	0.034
Th	1.146	1.156	0.828	1.086	1.063	1.315	1.154	1.144	0.892	0.932	0.968	1.056	1.509	1.550	1.268	1.291
U	0.939	0.911	0.918	0.919	1.145	0.894	0.807	0.998	0.931	0.873	0.979	0.791	1.014	0.978	1.031	1.020

	CO233B			CO233C				CO325				CO365					
Li	6.2	7.2	9.4	6.7	5.2	6.3	6.7	9.8	4.4	4.3	6.5	2.6	5.1	4.8	7.5	5.4	
Be	<2.59	<0.00	<3.11	1.5	<4.26	3.1	9.7	<3.40	<5.10	<4.88	<3.22	<5.76	<4.11	<4.28	<5.02	<6.34	
B	179	182	153	180	177	190	169	128	135	111	143	46	784	49	43	50	
Sc	3.2	3.2	3.5	3.0	3.3	3.3	3.0	3.2	3.4	2.7	2.7	3.4	2.8	2.7	3.0	2.9	
Ti	806	828	838	727	723	710	804	834	807	754	725	442	461	423	419	436	
V	32	29	32	21	21	22	22	21	20	21	19	8	9	8	8	9	
Cr	14	15	17	22	21	19	23	33	20	23	17	23	15	17	12	18	
Co	9	8	8	432	437	435	465	36	31	23	17	2	3	2	2	2	
Ni	20	15	19	66	64	64	63	35	24	19	21	6	5	4	5	6	
Cu	51	47	46	2067	2085	2053	2189	2093	2058	1903	1892	106	111	261	306	243	
Zn	27	25	23	89	86	81	90	341	321	251	155	18	21	17	22	19	
Ga	2.8	3.0	3.2	3.9	3.7	4.1	4.1	2.4	2.8	3.5	3.0	2.7	2.6	3.2	3.0	3.2	
Ge	0.7	1.4	0.6	3.3	2.6	3.3	1.4	1.7	<0.69	0.7	1.3	<0.67	<0.95	0.9	1.3	<0.79	
As	15.6	14.1	14.8	29.3	25.8	21.4	23.6	21.5	17.3	14.1	9.5	2.1	3.2	2.8	1.8	1.7	
Rb	7.7	7.0	7.5	8.6	9.1	8.6	9.7	12.2	9.7	9.6	9.0	9.3	9.4	9.2	9.0	8.9	
Sr	612	612	611	528	545	531	568	487	529	517	519	366	394	383	381	377	
Y	9.8	9.3	10.0	6.8	7.3	6.9	7.8	7.2	7.1	7.1	7.0	6.2	6.3	6.0	6.4	6.6	
Zr	81.5	83.1	82.5	69.2	70.5	71.8	75.0	74.8	74.6	70.2	67.8	42.5	45.3	42.7	41.1	41.8	
Nb	2.54	2.54	2.47	1.82	2.00	2.20	2.00	2.40	2.37	1.96	2.06	1.58	1.47	1.14	1.29	1.54	
Mo	1.92	1.53	1.93	3.10	3.53	2.93	3.52	1.66	1.56	1.32	1.27	0.45	0.24	0.43	0.26	0.29	
Ag	0.03	0.11	0.10	1.36	1.01	1.06	1.22	2.69	2.89	3.11	3.58	0.51	0.41	0.39	0.45	0.66	
Cd	<0.24	<0.56	<0.29	<0.60	0.62	<0.67	<0.70	0.55	<0.35	<0.58	<0.62	<0.68	<0.59	<0.75	<0.62	<0.51	
In	0.04	0.03	0.02	2.35	2.62	2.65	2.77	4.93	5.59	4.50	3.42	0.51	0.92	0.28	0.46	0.32	
Sn	5	5	5	490	504	511	586	1296	1481	1144	891	135	263	78	127	81	
Sb	100	100	102	3326	3350	3281	3439	927	850	626	468	63	155	43	45	57	
Cs	0.051	0.112	0.112	0.152	0.121	0.180	0.180	0.201	0.080	0.117	0.136	0.121	0.160	0.055	0.141	0.098	
Ba	370	358	378	238	242	241	255	248	256	248	242	213	220	223	221	218	
La	10.962	11.032	11.173	7.347	7.016	7.091	7.465	7.221	6.860	6.840	7.101	6.212	6.373	6.121	6.010	6.151	
Ce	13.439	13.098	13.840	12.492	12.342	12.887	13.465	12.775	12.333	12.042	11.942	11.264	11.556	11.203	10.982	11.133	
Pr	2.337	2.146	2.307	1.403	1.463	1.491	1.538	1.418	1.578	1.462	1.433	1.361	1.452	1.472	1.412	1.392	
Nd	10.250	10.059	9.959	6.716	6.663	6.417	6.834	7.121	6.167	6.508	7.081	5.778	6.081	5.395	5.193	5.516	
Sm	1.956	2.307	2.347	1.027	1.700	1.059	1.230	1.547	1.989	1.296	1.255	0.746	1.331	0.978	1.261	1.624	
Eu	0.567	0.582	0.631	0.400	0.374	0.437	0.440	0.298	0.336	0.385	0.474	0.290	0.386	0.435	0.431	0.367	
Gd	1.775	1.705	2.046	1.412	0.973	1.251	1.444	1.286	0.924	1.306	1.456	0.988	1.392	0.787	1.129	0.918	
Tb	0.263	0.313	0.283	0.196	0.182	0.202	0.218	0.199	0.226	0.139	0.207	0.215	0.201	0.132	0.156	0.138	
Dy	1.504	1.725	2.026	1.078	1.123	1.401	1.134	1.406	1.195	1.125	0.971	1.129	1.301	1.170	1.139	0.825	
Ho	0.316	0.440	0.426	0.226	0.212	0.206	0.292	0.230	0.264	0.243	0.253	0.244	0.236	0.196	0.210	0.246	
Er	0.979	0.846	1.153	0.438	0.692	0.760	0.526	0.944	0.892	0.776	0.536	0.576	0.867	0.505	0.867	0.825	
Tm	0.145	0.132	0.124	0.095	0.087	0.077	0.103	0.111	0.105	0.112	0.065	0.073	0.075	0.071	0.075	0.071	
Yb	1.143	1.073	1.153	0.406	0.421	0.543	0.984	0.548	0.864	0.376	0.824	0.746	0.746	0.645	0.736	0.595	
Lu	0.160	0.114	0.105	0.044	0.143	0.111	0.098	0.101	0.158	0.090	0.103	0.122	0.075	0.112	0.074	0.045	
Hf	1.815	1.795	1.835	1.818	1.658	1.561	1.818	1.707	1.868	1.416	1.707	1.059	1.049	1.301	1.099	1.059	
Ta	0.149	0.117	0.109	0.108	0.128	0.181	0.127	0.143	0.134	0.095	0.132	0.098	0.066	0.055	0.094	0.116	
W	0.322	0.438	0.383	0.158	0.332	0.251	0.121	0.342	0.325	0.259	0.239	<0.00	0.151	0.129	<0.063	<0.111	
Au	<0.046	<0.033	0.014	0.185	0.169	0.074	0.163	0.630	0.694	0.624	0.744	0.050	0.136	<0.133	<0.085	0.146	
Tl	<0.027	0.082	0.035	0.067	0.074	0.093	0.083	0.048	0.211	0.077	0.114	0.024	<0.0276	<0.029	<0.023	0.030	
Pb	80	81	80	4114	4202	4150	4589	8970	10088	8788	9134	380	670	691	873	636	
Bi	0.070	<0.024	0.045	0.519	0.468	0.590	0.470	1.241	1.938	1.888	1.658	0.083	<0.071	0.081	0.103	0.435	
Th	1.368	1.263	1.304	1.264	1.241	1.218	1.455	1.278	1.285	1.199	1.073	0.902	0.972	0.819	0.809	0.802	
U	1.265	1.331	1.394	1.151	1.046	1.129	0.886	0.927	0.892	0.862	0.983	0.816	0.708	0.988	0.815	0.827	

	CO366				CO368			CO530db			CO530lb		
Li	4.3	5.5	2.4	3.4	1.8	4.3	3.9	5.7	5.8	2.5	7.8	3.0	5.3
Be	<6.25	<5.54	3.2	<7.05	<2.68	2.5	1.3	<5.13	4.0	<4.11	<2.89	<3.00	<0.00
B	99	101	107	87	46	55	29	96	133	98	94	101	104
Sc	2.8	2.4	2.9	2.2	2.8	2.9	2.8	3.2	2.8	3.0	3.4	3.2	2.9
Ti	543	568	581	529	360	394	373	717	737	708	776	673	702
V	13	14	15	12	7	8	8	21	21	20	22	20	22
Cr	19	17	19	12	6	14	11	17	15	18	17	17	18
Co	9	9	8	9	2	1	2	69	71	71	85	66	69
Ni	8	9	9	8	3	3	4	151	158	155	206	150	152
Cu	311	305	376	399	4	3	3	7132	7249	7174	8941	7746	7592
Zn	42	47	42	42	3	3	2	2320	2317	2320	3181	2247	2269
Ga	2.9	3.1	2.4	3.0	3.3	2.8	3.2	3.4	3.3	3.9	3.0	2.8	2.9
Ge	<0.63	0.7	<0.78	<0.67	0.7	1.7	1.3	1.4	1.7	0.9	1.8	1.1	1.0
As	3.4	3.5	4.7	4.3	1.3	1.0	1.2	111.4	118.5	115.5	203.3	108.4	113.9
Rb	8.9	8.2	8.8	8.4	8.3	8.7	9.4	9.1	8.6	9.3	8.8	9.1	8.5
Sr	447	441	452	434	370	375	362	537	539	537	536	527	519
Y	6.0	5.9	6.0	5.7	5.4	5.9	4.9	7.5	7.2	7.7	7.9	7.4	7.4
Zr	52.0	51.9	53.2	50.3	32.9	32.8	31.5	61.0	62.2	59.7	65.5	61.2	59.7
Nb	1.78	1.50	1.56	1.80	1.19	1.35	1.27	2.20	2.04	2.29	2.28	2.04	2.09
Mo	0.81	0.68	1.03	0.92	0.42	0.60	0.24	1.71	1.47	2.35	1.76	1.67	1.97
Ag	0.72	0.61	0.59	0.88	0.03	<0.053	<0.0272	2.62	2.35	2.37	6.99	2.53	2.39
Cd	0.28	<0.49	<0.37	<0.36	<0.27	<0.19	0.41	<0.47	0.48	0.92	0.36	0.21	0.61
In	0.64	0.64	0.78	0.72	0.02	0.01	<0.0078	22.42	22.62	22.77	29.98	21.03	22.01
Sn	190	189	200	207	1	1	1	5836	5878	5931	11644	8306	8631
Sb	271	274	281	268	-	<0.154	<0.144	238	236	240	300	235	238
Cs	0.105	0.142	0.142	0.199	0.118	0.086	0.100	0.181	0.167	0.180	0.150	0.156	0.187
Ba	221	214	218	215	216	226	211	247	251	250	248	243	242
La	5.985	6.005	6.256	5.473	5.399	5.731	5.560	7.363	7.315	6.883	7.207	6.806	6.911
Ce	10.956	11.227	11.117	10.795	10.939	11.945	10.899	12.451	12.748	12.960	12.629	11.474	12.324
Pr	1.336	1.285	1.617	1.265	1.478	1.387	1.257	1.661	1.603	1.603	1.623	1.470	1.556
Nd	5.443	6.557	5.603	5.413	5.651	4.876	5.248	7.613	6.960	7.814	6.959	7.131	6.482
Sm	1.165	0.934	0.823	1.165	0.915	1.619	1.146	1.622	1.565	1.267	1.594	1.566	1.480
Eu	0.303	0.473	0.169	0.359	0.320	0.289	0.289	0.454	0.381	0.438	0.459	0.481	0.435
Gd	0.954	0.924	0.663	1.105	0.784	0.975	1.327	1.421	1.286	1.738	1.394	1.136	1.365
Tb	0.199	0.137	0.165	0.187	0.120	0.172	0.132	0.230	0.237	0.234	0.225	0.149	0.225
Dy	0.866	0.954	0.763	0.818	1.056	1.166	0.773	1.498	1.546	1.613	1.499	1.422	1.327
Ho	0.218	0.231	0.204	0.196	0.158	0.211	0.180	0.353	0.274	0.204	0.249	0.224	0.261
Er	0.537	0.606	0.420	0.803	0.523	0.675	0.723	0.703	0.623	0.634	0.695	0.964	0.839
Tm	0.076	0.023	0.062	0.102	0.043	0.091	0.073	0.096	0.143	0.088	0.107	0.060	0.095
Yb	0.384	0.555	0.643	0.673	0.523	0.720	0.470	0.720	0.691	0.682	0.678	0.678	0.599
Lu	0.095	0.053	0.115	0.101	0.073	0.113	0.047	0.107	0.135	0.103	0.098	0.112	0.085
Hf	1.326	1.506	1.225	1.326	0.607	0.749	0.845	1.872	1.603	1.402	1.060	2.052	1.499
Ta	0.120	0.100	0.095	0.123	0.116	0.079	0.070	0.131	0.137	0.097	0.164	0.137	0.147
W	0.165	0.146	0.151	0.069	0.196	0.152	0.049	0.514	0.438	0.274	2.444	0.557	0.553
Au	0.160	0.187	0.251	0.187	<0.042	0.052	<0.0268	0.062	0.086	<0.071	<0.063	<0.065	0.071
Tl	<0.0205	<0.026	0.027	0.028	0.014	<0.0177	<0.022	0.242	0.302	0.308	0.287	0.312	0.267
Pb	894	870	920	886	4	5	5	23807	23918	24025	47056	35154	36052
Bi	0.196	0.176	0.169	0.179	0.025	<0.026	<0.0155	1.920	1.814	1.930	2.654	1.890	1.957
Th	0.881	0.810	1.014	0.821	0.469	0.668	0.757	1.162	0.998	1.018	1.098	1.021	1.088
U	1.004	0.854	0.924	0.864	0.675	0.819	0.715	0.941	0.854	1.018	0.897	0.907	0.983

Table S6. The composition of wollastonite crystals measured by EMPA.

	9	10	14	15	18
SiO ₂	52.11	52.46	52.32	54.75	51.61
Al ₂ O ₃	0.37	0.98	1.32	0.16	1.06
FeO	1.11	0.93	0.82	1.75	0.87
MnO	0.27	0.30	0.27	0.35	0.35
MgO	3.43	1.82	1.36	1.94	1.32
CaO	41.22	40.38	40.96	32.74	42.43
Na ₂ O	0.73	2.28	2.48	7.07	1.81
K ₂ O	0.05	0.08	0.09	0.22	0.07
Total	99.24	99.75	99.20	99.59	99.37

Number of ions on the basis of 9O					
SiO ₂	3.005	3.028	3.014	3.148	2.990
Al ₂ O ₃	0.025	0.067	0.090	0.011	0.073
FeO	0.054	0.045	0.039	0.084	0.042
MnO	0.013	0.015	0.013	0.017	0.017
MgO	0.295	0.157	0.116	0.166	0.114
CaO	2.547	2.497	2.528	2.017	2.634
Na ₂ O	0.123	0.379	0.410	1.135	0.301
K ₂ O	0.004	0.006	0.006	0.016	0.005

Table S7. The composition of clinopyroxenes measured by EMPA.

	3	4	6	7	11	12	13	17	19
SiO ₂	55.50	55.95	53.81	51.37	53.89	54.15	54.38	53.26	53.63
TiO ₂	0.14	0.14	0.27	0.37	0.18	0.28	0.17	0.26	0.20
Al ₂ O ₃	2.20	1.32	2.32	5.63	2.45	1.26	4.10	1.75	1.91
FeO	3.43	2.65	3.30	4.24	3.88	4.06	3.81	4.76	2.66
MnO	0.09	0.14	0.15	0.17	0.29	0.30	0.30	0.29	0.32
MgO	11.55	12.79	13.39	10.18	13.76	15.33	12.05	13.91	13.38
CaO	24.12	23.36	22.26	20.20	20.73	22.38	18.44	21.72	22.34
Na ₂ O	2.11	2.61	3.99	6.70	3.89	1.89	6.24	2.85	4.75
K ₂ O	0.11	0.14	0.20	0.16	0.11	0.02	0.18	0.06	0.20
Total	99.25	99.10	99.69	99.01	99.18	99.67	99.68	98.87	99.39

Number of ions on the basis of 6O									
SiO ₂	2.040	2.053	1.983	1.922	1.991	1.990	1.994	1.984	1.986
TiO ₂	0.004	0.004	0.008	0.010	0.005	0.008	0.005	0.007	0.006
Al ₂ O ₃	0.095	0.057	0.101	0.248	0.107	0.055	0.177	0.077	0.083
FeO	0.105	0.081	0.102	0.133	0.120	0.125	0.117	0.148	0.082
MnO	0.003	0.004	0.005	0.005	0.009	0.009	0.009	0.009	0.010
MgO	0.633	0.700	0.735	0.568	0.758	0.840	0.659	0.773	0.739
CaO	0.950	0.918	0.879	0.810	0.820	0.881	0.725	0.867	0.886
Na ₂ O	0.227	0.278	0.417	0.696	0.408	0.200	0.643	0.303	0.494
K ₂ O	0.005	0.007	0.009	0.008	0.005	0.001	0.008	0.003	0.009

Table S8a. The reference and compositional groups used for comparison.

#Table S9b	Group	Used compositional range from
1	<i>Apollonia</i>	Freestone et al. 2000
2	Jalame	Brill 1988
4	HIMT	Freestone 1994
5	Foy 1	Foy et al. 2003
6	HIMT1	Foster and Jackson 2009
7	HIMTa	Ceglia et al. 2015
8	strong HIMT	Rosenow and Rehren 2014
9	Egypt 2 (low Na ₂ O)	Schibille et al. 2019
10	Magby	De Juan Ares et al. 2019
11	Foy 2.1	Foy et al. 2003
12	Foy 2.1	Schibille 2022
13	Foy 3.2	Foy et al. 2003
14	Foy 3.2	Schibille 2022
15	Foy 3.2	Cholakova and Rehren (2018)
16	HIMT2	Foster and Jackson 2009

Table S8b. The composition of reference and compositional groups listed in Tables S9a.

# Table S9a	LEVANT				EGYPT-HIMT			
	<i>I</i>	<i>2</i>	<i>3</i>	<i>4</i>	<i>5</i>	<i>6</i>	<i>7</i>	<i>8</i>
Group	<i>Apollonia</i>	Jalame	Jalame	HIMT	Foy 1	HIMT1	HIMTa	Strong HIMT
Measurements n=	48	53	33	3	43	123	13	28
Chronology	6 th -7 th	4 th	4 th	4 th -6 th	5 th -8 th	4 th -5 th	5 th -7 th	2 nd -7 th
	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.
SiO ₂ (av.)	71.38 1.6	69.74 1.6	68.19 2.0	64.86 1.1	64.49 1.4	67.34 1.7	66.22 1.5	64.76 1.6
TiO ₂ (av.)	0.11 0.1	0.09 -	0.05 -	0.56 0.1	0.49 0.1	0.33 0.1	0.47 0.2	0.50 0.1
Al ₂ O ₃ _av	3.28 0.5	2.74 0.2	2.80 0.1	3.18 0.3	2.88 0.3	2.49 0.3	2.95 0.3	2.70 0.2
FeO_av	0.49 0.3	0.41 0.2	0.34 0.1	2.40 0.7	2.05 0.8	1.22 0.2	1.56 0.3	1.84 0.7
MnO (av.)	0.02 -	0.63 0.9	0.77 0.9	2.25 0.6	2.02 0.4	1.71 0.3	2.02 0.5	2.01 0.4
MgO (av.)	0.66 0.2	0.58 0.1	0.49 0.1	1.21 0.1	1.23 0.2	0.98 0.2	1.06 0.2	1.03 0.1
CaO (av.)	8.19 1.0	8.69 0.6	8.76 0.8	5.63 0.8	6.22 0.9	6.08 0.6	5.95 1.0	5.70 0.5
Na ₂ O (av.)	14.21 1.4	15.74 0.9	15.63 0.8	17.72 0.7	19.12 1.4	19.11 1.1	18.32 1.1	18.15 1.1
K ₂ O (av.)	0.61 0.2	0.78 0.1	0.78 0.1	0.45 -	0.41 0.1	0.50 0.1	0.44 0.1	0.42 0.1
P ₂ O ₅ (av.)	0.05 -	0.14 -	0.09 -	0.10 -	0.11 -	0.05 -	0.06 -	0.06 -
SO ₃ (av.)	0.16 0.1	- -	0.13 0.1	0.21 0.1	- -	- -	0.25 0.1	0.25 0.1
Cl (av.)	0.81 0.1	- -	0.90 0.2	0.99 0.1	- -	- -	1.00 0.1	1.00 0.1

(continued)

# Table S9a	EGYPT SERIES		MAGBY	G2.1		G3.2			
	9	10	11	12	13	14	15	16	
Group	Egypt 2		-	Foy 2.1	Foy 2.1	Foy 3.2	Foy 3.2	HIMT2	
Measurements n=	24	25	5 th -8 th	51	157/180	19	42	221	
Chronology	9 th -12 th	5 th -9 th	5 th -9 th	5 th -7 th	1 st -6 th	4 th -5 th	4 th -6 th	3 rd -5 th	
	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	av. sd.	
SiO ₂ (av.)	70.09 1.4	64.84 1.5	64.42 1.1	65.7 1.7	68.36 1.7	68.1 1.7	68.15 1.87	68.77 1.6	
TiO ₂ (av.)	0.27 -	0.15 -	0.16 -	0.15 0.02	0.09 -	0.10 0.03	0.09 0.02	0.12 -	
Al ₂ O ₃ _av	2.52 0.2	2.03 0.3	2.54 0.2	2.53 0.23	1.93 0.2	1.94 0.19	1.93 0.21	2.25 0.2	
FeO_av	1.06 0.3	1.23 0.5	1.22 0.6	1.04 0.5	0.64 0.1	0.61 0.24	0.54 0.12	0.65 0.1	
MnO (av.)	0.44 0.5	1.53 0.8	1.60 0.4	1.41 0.44	0.91 0.4	0.83 0.27	0.84 0.20	0.98 0.2	
MgO (av.)	0.70 0.2	1.90 0.2	1.23 0.1	1.12 0.25	0.66 0.2	0.64 0.21	0.56 0.15	0.76 0.1	
CaO (av.)	9.57 0.5	9.29 0.7	7.78 0.7	8.12 0.92	6.88 0.8	6.61 0.86	6.59 0.91	6.00 0.6	
Na ₂ O (av.)	13.39 0.6	16.12 0.9	18.50 1.2	17.7 1.3	18.63 1.0	19.0 1.1	19.04 1.01	19.65 1.0	
K ₂ O (av.)	0.51 0.3	1.48 0.2	0.79 0.1	0.75 0.19	0.43 0.1	0.47 0.16	0.42 0.07	0.58 0.1	
P ₂ O ₅ (av.)	0.11 0.1	0.38 0.1	0.18 -	0.16 0.10	0.08 -	0.05 0.03	0.04 0.02	0.05 -	
SO ₃ (av.)	- -	- -	- -	- -	- -	- -	0.21 0.09	- -	
Cl (av.)	1.04 0.10	0.66 0.13	- -	0.83 0.11	- -	1.23 0.24	1.16 0.21	- -	

Table S9. The overall collection from Comacchio and the results of the provenance investigation.

Reference	Publ.no.	Analytical techniques	Context chronology	Type	Colour	Bertini et al. (2020)	Area	Compositional group
Bertini et al. 2020	Com01	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	Intermediate
Bertini et al. 2020	Com02	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com03	EMPA	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com04	EMPA	7 th (mid)	Waster	Blue-green	Intermediate*	-	Intermediate
Bertini et al. 2020	Com06	EMPA+LA-ICP-MS	10 th -11 th	Tessera	Colourless	Foy 2	Egypt	G2.1/G2.2
Bertini et al. 2020	Com08	EMPA	8 th -9 th	Waster	Colourless	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com10	EMPA	7 th (mid)	Fragment	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com11	EMPA+LA-ICP-MS	7 th (mid)	Fragment	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com12	EMPA	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com13	EMPA	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com14	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	Magby
Bertini et al. 2020	Com15	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Levantine A - Apollonia type	Levant	Jalame/ <i>Apollonia</i>
Bertini et al. 2020	Com16	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Levantine B - Jalame type	Levant	<i>Apollonia</i> /Jalame
Bertini et al. 2020	Com18	EMPA+LA-ICP-MS	7 th (1 st half) - 8 th (early)	Fragment	Yellow	Foy 2	Egypt	G2.1/G2.2
Bertini et al. 2020	Com19	EMPA+LA-ICP-MS	7 th (1 st half)	Goblet/lamp	Blue-green	Levantine B - Jalame type	Levant	Jalame-like
Bertini et al. 2020	Com20	EMPA+LA-ICP-MS	7 th (1 st half)	Goblet/lamp	Blue-green	Levantine B - Jalame type	Levant	Jalame-like
Bertini et al. 2020	Com24	EMPA+LA-ICP-MS	7 th (mid)	Fragment	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com26	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com27	EMPA	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	Intermediate
Bertini et al. 2020	Com28	EMPA	7 th (mid)	Fragment	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com29	EMPA+LA-ICP-MS	7 th (mid)	Fragment	Yellow	Foy 2	Egypt	G2.1/G2.2
Bertini et al. 2020	Com30	EMPA	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com31	EMPA	7 th (mid)	Waster	Red	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com34	EMPA+LA-ICP-MS	7 th (1 st half)	Goblet	Green olive	Levantine B - Jalame type	Levant	Jalame/ <i>Apollonia</i>
Bertini et al. 2020	Com35	EMPA	7 th (1 st half)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com36	EMPA+LA-ICP-MS	7 th (1 st half)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com37	EMPA	7 th (1 st half)	Unknown	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com38	EMPA	7 th (1 st half)	Waster	Red	Intermediate*	Egypt	~ G2.1HFe
Bertini et al. 2020	Com39	EMPA+LA-ICP-MS	7 th (mid)	Window	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com40	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com41	EMPA	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com42	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Intermediate*	Levant	Jalame
Bertini et al. 2020	Com44	EMPA+LA-ICP-MS	7 th (1 st half)	Window	Blue-green	Levantine A - Apollonia type	Levant	<i>Apollonia</i> -like
Bertini et al. 2020	Com45	EMPA+LA-ICP-MS	7 th (1 st half)	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com46	EMPA+LA-ICP-MS	7 th (1 st half)	Beaker	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com47	EMPA	7 th (1 st half)	Crucible	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com48	EMPA+LA-ICP-MS	11 th	Lamp	Blue-green	Intermediate*	Egypt	Intermediate
Bertini et al. 2020	Com50	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com51	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2

Reference	Publ.no.	Analytical techniques	Context chronology	Type	Colour	Bertini et al. (2020)	Area	Compositional group
Bertini et al. 2020	Com52	EMPA	7 th (mid)	Lamp	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com53	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Levantine A - Apollonia type	Levant	Apollonia-like
Bertini et al. 2020	Com55	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com56	EMPA+LA-ICP-MS	7 th (mid)	Fragment	Blue-green	Levantine A - Apollonia type	Levant	Apollonia
Bertini et al. 2020	Com57	EMPA	7 th (mid)	Waster	Blue-green	Levantine A - Apollonia type	Levant	Apollonia
Bertini et al. 2020	Com58	EMPA	7 th (mid)	Waster	Blue-green	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com59	EMPA+LA-ICP-MS	7 th (1 st half)	Fragment	Grey light	Levantine A - Apollonia type	Levant	Apollonia-like
Bertini et al. 2020	Com60	EMPA+LA-ICP-MS	7 th (1 st half)	Fragment	Grey light	Levantine A - Apollonia type	Levant	Apollonia-like
Bertini et al. 2020	Com61	EMPA+LA-ICP-MS	7 th (end) - 8 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com62	EMPA	7 th (end) - 8 th	Tessera	Colourless	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com63	EMPA	7 th (end) - 8 th	Waster	Blue-green	Intermediate*	Egypt	Intermediate
Bertini et al. 2020	Com64	EMPA+LA-ICP-MS	7 th (end) - 8 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com65	EMPA+LA-ICP-MS	7 th (end) - 8 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com66	EMPA	7 th (end) - 8 th	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com68	EMPA+LA-ICP-MS	7 th (mid)	Lamp	Blue-green	Levantine B - Jalame type	Levant	Jalame-like
Bertini et al. 2020	Com69	EMPA+LA-ICP-MS	8 th -9 th	Tessera	Blue dark	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com70	EMPA+LA-ICP-MS	8 th -9 th	Tessera	Red	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com71	EMPA+LA-ICP-MS	8 th -9 th	Waster	Blue-green	Intermediate*	Egypt	G3.2-like (/G2.1)
Bertini et al. 2020	Com72	EMPA	8 th -9 th	Bottle/jug	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com73	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com74	EMPA+LA-ICP-MS	8 th -9 th	Waster	Green olive	HIMT strong	Egypt	HIMTa
Bertini et al. 2020	Com75	EMPA+LA-ICP-MS	8 th -9 th	Fragment	Green olive	HIMT strong	Egypt	HIMTa
Bertini et al. 2020	Com76	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Levantine A - Apollonia type	Levant	Jalame-like
Bertini et al. 2020	Com77	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com78	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com81	EMPA	8 th -9 th	Crucible	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com82	EMPA+LA-ICP-MS	8 th -9 th	Crucible	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com85	EMPA+LA-ICP-MS	7 th (mid)	Fragment	Yellow	Foy 2	Egypt	G2.1HFe
Bertini et al. 2020	Com86	EMPA+LA-ICP-MS	7 th (mid)	Waster	Colourless	Intermediate*	Egypt	G3.2-like (/G2.1)
Bertini et al. 2020	Com87	EMPA+LA-ICP-MS	7 th (mid)	Tessera	Colourless	Intermediate*	Egypt	G3.2
Bertini et al. 2020	Com88	EMPA	7 th (mid)	Tessera	Blue dark	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com89	EMPA+LA-ICP-MS	7 th (mid)	Tessera	Blue-green	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com90	EMPA+LA-ICP-MS	7 th (mid)	Waster	Blue dark	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com91	EMPA+LA-ICP-MS	7 th (mid)	Tessera	White	Intermediate*	Egypt	G3.2-like (/G2.1)
Bertini et al. 2020	Com92	EMPA+LA-ICP-MS	7 th (mid)	Tessera	Red	Intermediate*	Egypt	Intermediate
Bertini et al. 2020	Com93	EMPA+LA-ICP-MS	10 th	Crucible	Green olive	Intermediate*	Egypt	Egypt
Bertini et al. 2020	Com94	EMPA	10 th	Crucible	Green olive	Intermediate*	Egypt	~ G2.1HFe
Bertini et al. 2020	Com95	EMPA+LA-ICP-MS	7 th (mid)	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2

Reference	Publ.no.	Analytical techniques	Context chronology	Type	Colour	Bertini et al. (2020)	Area	Compositional group
Bertini et al. 2020	Com96a	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Intermediate*	-	Intermediate
Bertini et al. 2020	Com96b	EMPA	8 th -9 th	Goblet	White	Levantine A - Apollonia type	Levant?	-
Bertini et al. 2020	Com97	EMPA+LA-ICP-MS	9 th	Waster	Blue-green	Intermediate*	Egypt	G2.1/G2.2
Bertini et al. 2020	Com98	EMPA+LA-ICP-MS	8 th -9 th	Goblet	Blue-green	Intermediate*	Egypt	G2.1/G2.2
This study	CO23A	EMPA+LA-ICP-MS	8 th	Fluidity test	Green		Egypt	G2.1/G2.2
This study	CO23B	EMPA+LA-ICP-MS	8 th	Fluidity test	Blue-aqua		Levant	<i>Apollonia</i>
This study	CO24	EMPA+LA-ICP-MS	8 th	Block	Blue		Egypt	G2.1/G2.2
This study	CO25	EMPA+LA-ICP-MS	8 th	Tessera	Colourless		Egypt	G3.2
This study	CO58A	EMPA+LA-ICP-MS	9 th	Block	Green		Egypt	Intermediate
This study	CO58B	EMPA+LA-ICP-MS	9 th	Drop	Green		Egypt	G2.1/G2.2
This study	CO58C	EMPA+LA-ICP-MS	9 th	Glass on crucible	Green		Levant	-
This study	CO88	EMPA+LA-ICP-MS	8 th	Marbled wall	Green light		Egypt	G3.2-like (/G2.1)
This study	CO92	EMPA+LA-ICP-MS	8 th	Goblet	Green light		Egypt	G2.1/G2.2
This study	CO93	EMPA+LA-ICP-MS	8 th	Goblet	Green		Egypt	G2.1/G2.2
This study	CO94	EMPA+LA-ICP-MS	8 th	Goblet	Green light		Levant	Jalame/ <i>Apollonia</i>
This study	CO95	EMPA+LA-ICP-MS	8 th	Goblet	Green		Egypt	G2.1/G2.2
This study	CO96	EMPA+LA-ICP-MS	8 th	Goblet	Green light		Egypt	G2.1/G2.2
This study	CO99	EMPA+LA-ICP-MS	8 th	Unknown	Green olive		Egypt	HIMTa
This study	CO100A	EMPA+LA-ICP-MS	8 th	Collar	Green-red		Egypt	G2.1/G2.2
This study	CO100B	EMPA+LA-ICP-MS	8 th	Block	Green		Egypt	G3.2-like (/G2.1)
This study	CO121A	EMPA+LA-ICP-MS	9 th	Drop	Green light		Egypt	G2.1/G2.2
This study	CO121B	EMPA+LA-ICP-MS	9 th	Drop	Green light		Egypt	G2.1/G2.2
This study	CO121C	EMPA+LA-ICP-MS	9 th	Collar	Green light		Egypt	Intermediate
This study	CO121D	EMPA+LA-ICP-MS	9 th	Collar	Green light		Egypt	G2.1/G2.2
This study	CO121E	EMPA+LA-ICP-MS	9 th	Block	Green light		Egypt	G3.2-like (/G2.1)
This study	CO122	EMPA+LA-ICP-MS	9 th	Block	Blue		Egypt	G2.1/G2.2
This study	CO184A	EMPA+LA-ICP-MS	8 th	Cut	Green		Egypt	G2.1/G2.2
This study	CO184B	EMPA+LA-ICP-MS	8 th	Block	Green		Egypt	G2.1/G2.2
This study	CO184C	EMPA+LA-ICP-MS	8 th	Wall	Green		Egypt	G2.1/G2.2
This study	CO230	EMPA+LA-ICP-MS	7 th (2 st half)	Collar	Green		Levant	<i>Apollonia</i> -like
This study	CO233A	EMPA+LA-ICP-MS	7 th (2 st half)	Window	Green		Egypt	Egypt 2 low Na ₂ O
This study	CO233B	EMPA+LA-ICP-MS	7 th (2 st half)	Window	Green		Egypt	G2.1HFe
This study	CO233C	EMPA+LA-ICP-MS	7 th (2 st half)	Window	Blue		Egypt	G2.1/G2.2
This study	CO325	EMPA+LA-ICP-MS	7 th (2 st half)	Goblet	Green		Egypt	G2.1/G2.2
This study	CO365	EMPA+LA-ICP-MS	7 th (2 st half)	Waste	Green		Levant	<i>Apollonia</i> -like
This study	CO366	EMPA+LA-ICP-MS	7 th (2 st half)	Goblet	Green-blue		Levant	<i>Apollonia</i> /Jalame
This study	CO368	EMPA+LA-ICP-MS	7 th (2 st half)	Goblet	Green-aqua		Levant	<i>Apollonia</i>
This study	CO530	EMPA+LA-ICP-MS	12 th -14 th	Lamp?	Green-red		Egypt	G2.1/G2.2

*In Bertini et al. (2020), "Intermediate" means "Heavy recycled/mixed natron (first half 7th to 11th century CE)".

Table S10. Discussion of the Sn-Pb correlation. For converting elements to oxides, the following factors have been used: 1.07722 for Pb to PbO and 1.1347999 for Sn to SnO₂. The lines filled in grey are those corresponding to R²=0.969.

Sample ID	Colour	Raw values				Alloy/compound calculation		Conversion elements to oxides		
		Sn (ppm)	Pb (ppm)	Sn/Pb	Pb/Sn	Sn %	Pb %	PbO (wt%)	SnO ₂ (wt%)	PbO/SnO ₂
CO58C	Green	183	295	0.62	1.61	38	62	0.032	0.021	1.53
Com89	Blue-green	741	1646	0.45	2.22	31	69	0.177	0.084	2.11
Com58	Blue-green	354	805	0.44	2.27	31	69	0.087	0.040	2.15
Com63	Blue-green	861	2414	0.36	2.80	26	74	0.260	0.098	2.66
Com48	Blue-green	6507	23647	0.28	3.63	22	78	2.547	0.738	3.45
CO230	Green	874	3504	0.25	4.01	20	80	0.377	0.099	3.81
CO100A	Green-red	1801	7719	0.23	4.29	19	81	0.831	0.204	4.07
Com80	Blue-green	278	1245	0.22	4.48	18	82	0.134	0.032	4.25
CO530	Green-red	5277	23672	0.22	4.49	18	82	2.550	0.599	4.26
Com66	Blue-green	2833	12755	0.22	4.50	18	82	1.374	0.321	4.27
CO366	Green-blue	196	893	0.22	4.55	18	82	0.096	0.022	4.31
CO365	Green	137	650	0.21	4.75	17	83	0.070	0.016	4.51
Com93	Green olive	194	927	0.21	4.78	17	83	0.100	0.022	4.54
Com08	Colourless	1124	5793	0.19	5.15	16	84	0.624	0.128	4.89
Com94	Green olive	5883	30604	0.19	5.20	16	84	3.297	0.668	4.94
CO58A	Green	343	1866	0.18	5.44	16	84	0.201	0.039	5.17
Com64	Blue-green	152	834	0.18	5.47	15	85	0.090	0.017	5.19
Com98	Blue-green	2599	14780	0.18	5.69	15	85	1.592	0.295	5.40
Com96a	Blue-green	842	4883	0.17	5.80	15	85	0.526	0.096	5.51
CO121A	Green light	575	3344	0.17	5.81	15	85	0.360	0.065	5.52
CO92	Green light	2875	17683	0.16	6.15	14	86	1.905	0.326	5.84
CO93	Green	706	4578	0.15	6.48	13	87	0.493	0.080	6.15
CO88	Green light	2201	14546	0.15	6.61	13	87	1.567	0.250	6.27
CO96	Green light	896	5929	0.15	6.62	13	87	0.639	0.102	6.28
Com25	Blue-green	424	2807	0.15	6.62	13	87	0.302	0.048	6.28
Com65	Blue-green	193	1283	0.15	6.65	13	87	0.138	0.022	6.31
Com03	Blue-green	2578	17533	0.15	6.80	13	87	1.889	0.293	6.46
Com30	Blue-green	672	4629	0.15	6.89	13	87	0.499	0.076	6.54
Com72	Blue-green	872	6269	0.14	7.19	12	88	0.675	0.099	6.83
Com50	Blue-green	691	4972	0.14	7.20	12	88	0.536	0.078	6.83
Com40	Blue-green	656	4983	0.13	7.60	12	88	0.537	0.074	7.21
CO325	Green	1203	9245	0.13	7.69	12	88	0.996	0.137	7.30
Com02	Blue-green	1700	13267	0.13	7.80	11	89	1.429	0.193	7.41
CO23A	Green	521	4076	0.13	7.83	11	89	0.439	0.059	7.43
CO184A	Green	670	5311	0.13	7.92	11	89	0.572	0.076	7.52
Com36	Blue-green	219	1739	0.13	7.95	11	89	0.187	0.025	7.55
CO233C	Blue	523	4264	0.12	8.16	11	89	0.459	0.059	7.74
Com45	Blue-green	596	4863	0.12	8.16	11	89	0.524	0.068	7.75
Com46	Blue-green	596	4863	0.12	8.16	11	89	0.524	0.068	7.75
Com24	Blue-green	194	1608	0.12	8.30	11	89	0.173	0.022	7.88
Com61	Blue-green	630	5508	0.11	8.74	10	90	0.593	0.072	8.29
Com26	Blue-green	449	3963	0.11	8.82	10	90	0.427	0.051	8.37
Com13	Blue-green	2339	20701	0.11	8.85	10	90	2.230	0.265	8.40
Com01	Blue-green	333	3061	0.11	9.19	10	90	0.330	0.038	8.72
CO121B	Green light	444	4083	0.11	9.20	10	90	0.440	0.050	8.74
Com55	Blue-green	106	979	0.11	9.22	10	90	0.105	0.012	8.75
Com52	Blue-green	840	7795	0.11	9.28	10	90	0.840	0.095	8.81
Com04	Blue-green	2392	22311	0.11	9.33	10	90	2.403	0.271	8.85
CO58B	Green	668	6528	0.10	9.78	9	91	0.703	0.076	9.28
Com39	Blue-green	3250	32277	0.10	9.93	9	91	3.477	0.369	9.43
Com95	Blue-green	4052	42290	0.10	10.44	9	91	4.556	0.460	9.91
Com51	Blue-green	446	4787	0.09	10.74	9	91	0.516	0.051	10.20
Com37	Blue-green	848	9152	0.09	10.79	8	92	0.986	0.096	10.24
Com73	Blue-green	348	3774	0.09	10.83	8	92	0.407	0.040	10.28
CO121D	Green light	417	4635	0.09	11.11	8	92	0.499	0.047	10.55
CO121C	Green light	305	3395	0.09	11.14	8	92	0.366	0.035	10.57
Com78	Blue-green	396	4426	0.09	11.18	8	92	0.477	0.045	10.61
CO184C	Green	421	4725	0.09	11.21	8	92	0.509	0.048	10.64
Com82	Blue-green	183	2081	0.09	11.36	8	92	0.224	0.021	10.79
Com90	Blue dark	208	2480	0.08	11.92	8	92	0.267	0.024	11.31
CO95	Green	381	4603	0.08	12.09	8	92	0.496	0.043	11.48

CO122	Blue	182	2435	0.07	13.39	7	93	0.262	0.021	12.71
Com88	Blue dark	252	3441	0.07	13.65	7	93	0.371	0.029	12.96
Com77	Blue-green	359	4902	0.07	13.67	7	93	0.528	0.041	12.98
CO100B	Green	192	2700	0.07	14.07	7	93	0.291	0.022	13.35
Com97	Blue-green	244	3492	0.07	14.30	7	93	0.376	0.028	13.57
Com71	Blue-green	112	1745	0.06	15.62	6	94	0.188	0.013	14.82
CO184B	Green	261	4389	0.06	16.83	6	94	0.473	0.030	15.98
Com11	Blue-green	315	5717	0.06	18.17	5	95	0.616	0.036	17.25
CO24	Blue	178	3381	0.05	18.95	5	95	0.364	0.020	17.99
Com12	Blue-green	126	2479	0.05	19.68	5	95	0.267	0.014	18.68
Com10	Blue-green	126	3963	0.03	31.47	3	97	0.427	0.014	29.87
Com69	Blue dark	56	1970	0.03	35.14	3	97	0.212	0.006	33.36
Com47	Blue-green	72	2927	0.02	40.84	2	98	0.315	0.008	38.77
Com54	Blue-green	158	17452	0.01	110.79	1	99	1.880	0.018	105.17

Table S11. Discussion of the Cu-Sb correlation.

Sample ID	Colour	Raw values				Ratio		Figure
		Cu (ppm)	Sb (ppm)	Cu/Sb	Sb/Cu	Cu%	Sb%	
Com26	Blue-green	246	2559	0.10	10.40	9	91	
Com69	Blue dark	1937	12740	0.15	6.58	13	87	
Com71	Blue-green	1877	6927	0.27	3.69	21	79	
Com55	Blue-green	216	788	0.27	3.65	22	78	
CO24	Blue	2133	6991	0.31	3.28	23	77	
Com90	Blue dark	2562	6563	0.39	2.56	28	72	
CO122	Blue	2482	6345	0.39	2.56	28	72	
CO58B	Green	1124	2645	0.42	2.35	30	70	
Com58	Blue-green	256	590	0.43	2.31	30	70	
Com12	Blue-green	1603	2582	0.62	1.61	38	62	
CO233C	Blue	2099	3349	0.63	1.60	39	61	
Com30	Blue-green	2535	3631	0.70	1.43	41	59	
Com25	Blue-green	1161	1650	0.70	1.42	41	59	blue
Com24	Blue-green	153	205	0.75	1.34	43	57	
Com80	Blue-green	565	711	0.79	1.26	44	56	
Com78	Blue-green	2259	2666	0.85	1.18	46	54	
Com51	Blue-green	2160	2506	0.86	1.16	46	54	
CO184C	Green	2057	2343	0.88	1.14	47	53	
Com77	Blue-green	1677	1896	0.88	1.13	47	53	
CO121D	Green light	2550	2819	0.90	1.11	48	52	
Com50	Blue-green	2175	2346	0.93	1.08	48	52	
CO92	Green light	3180	3402	0.93	1.07	48	52	
Com45	Blue-green	2930	3113	0.94	1.06	48	52	
Com46	Blue-green	2930	3113	0.94	1.06	48	52	
Com61	Blue-green	2003	2126	0.94	1.06	49	51	
CO184B	Green	2098	2196	0.96	1.05	49	51	
CO23A	Green	885	924	0.96	1.04	49	51	
Com81	Blue-green	1840	1909	0.96	1.04	49	51	
Com47	Blue-green	1427	1473	0.97	1.03	49	51	
CO88	Green light	1561	1608	0.97	1.03	49	51	
CO93	Green	1742	1788	0.97	1.03	49	51	
CO121C	Green light	1491	1516	0.98	1.02	50	50	
CO58A	Green	797	797	1.00	1.00	50	50	
CO184A	Green	1908	1906	1.00	1.00	50	50	
Com36	Blue-green	475	469	1.01	0.99	50	50	
Com97	Blue-green	1877	1849	1.02	0.98	50	50	
Com73	Blue-green	2134	2083	1.02	0.98	51	49	
CO95	Green	1805	1745	1.03	0.97	51	49	
CO121A	Green light	1233	1189	1.04	0.96	51	49	
Com72	Blue-green	2932	2795	1.05	0.95	51	49	
Com10	Blue-green	2112	1982	1.07	0.94	52	48	
Com27	Blue-green	2476	2251	1.10	0.91	52	48	
Com01	Blue-green	1443	1311	1.10	0.91	52	48	
CO100B	Green	1548	1404	1.10	0.91	52	48	
Com11	Blue-green	1830	1580	1.16	0.86	54	46	
Com82	Blue-green	730	609	1.20	0.83	55	45	
CO366	Green-blue	348	273	1.27	0.79	56	44	
Com52	Blue-green	3709	2775	1.34	0.75	57	43	
CO121B	Green light	1882	1389	1.36	0.74	58	42	
Com40	Blue-green	900	574	1.57	0.64	61	39	
Com37	Blue-green	3667	2185	1.68	0.60	63	37	
Com98	Blue-green	2574	1468	1.75	0.57	64	36	

Com64	Blue-green	203	106	1.91	0.52	66	34	
Com39	Blue-green	2779	1429	1.94	0.51	66	34	
CO96	Green light	2579	1263	2.04	0.49	67	33	
CO100A	Green-red	2290	1100	2.08	0.48	68	32	
Com66	Blue-green	2184	1039	2.10	0.48	68	32	
Com65	Blue-green	189	86	2.19	0.46	69	31	
Com63	Blue-green	1134	504	2.25	0.44	69	31	
Com96a	Blue-green	1278	519	2.46	0.41	71	29	
CO58C	Green	105	42	2.51	0.40	72	28	
Com54	Blue-green	6950	2634	2.64	0.38	73	27	
CO325	Green	1986	718	2.77	0.36	73	27	
CO365	Green	205	73	2.83	0.35	74	26	
CO230	Green	607	209	2.90	0.34	74	26	
Com13	Blue-green	2532	775	3.27	0.31	77	23	
Com95	Blue-green	11823	2448	4.83	0.21	83	17	
Com94	Green olive	4474	825	5.42	0.18	84	16	
Com02	Blue-green	2148	237	9.08	0.11	90	10	
CO530	Green-red	7270	301	24.14	0.04	96	4	
Com48	Blue-green	7813	248	31.52	0.03	97	3	
Com89	Blue-green	1679	36	46.26	0.02	98	2	

Table S12. Discussion of the Sb-Pb correlation.

Sample ID	Colour	Raw data				Ratio		Figure 6C
		Sb (ppm)	Pb (ppm)	Pb/Sb	Sb/Pb	Sb%	Pb%	
Com48	Blue-green	248	23647	95.39	0.01	1	99	
CO530	Green-red	301	23672	78.62	0.01	1	99	
Com02	Blue-green	237	13267	56.08	0.02	2	98	
Com89	Blue-green	36	1646	45.35	0.02	2	98	
Com94	Green olive	825	30604	37.10	0.03	3	97	
Com13	Blue-green	775	20701	26.70	0.04	4	96	
Com39	Blue-green	1429	32277	22.58	0.04	4	96	
Com95	Blue-green	2448	42290	17.27	0.06	5	95	
CO230	Green	209	3504	16.76	0.06	6	94	
Com65	Blue-green	86	1283	14.86	0.07	6	94	
Com93	Green olive	67	927	13.85	0.07	7	93	
CO325	Green	718	9245	12.88	0.08	7	93	
Com66	Blue-green	1039	12755	12.28	0.08	8	92	
Com98	Blue-green	1468	14780	10.07	0.10	9	91	
Com96a	Blue-green	519	4883	9.42	0.11	10	90	
CO88	Green light	1608	14546	9.05	0.11	10	90	
CO365	Green	73	650	8.96	0.11	10	90	
Com40	Blue-green	574	4983	8.69	0.12	10	90	
Com24	Blue-green	205	1608	7.84	0.13	11	89	
Com64	Blue-green	106	834	7.83	0.13	11	89	
CO100A	Green-red	1100	7719	7.02	0.14	12	88	
CO58C	Green	42	295	7.01	0.14	12	88	
Com54	Blue-green	2634	17452	6.62	0.15	13	87	
CO92	Green light	3402	17683	5.20	0.19	16	84	
Com63	Blue-green	504	2414	4.79	0.21	17	83	
CO96	Green light	1263	5929	4.70	0.21	18	82	
CO23A	Green	924	4076	4.41	0.23	18	82	
Com37	Blue-green	2185	9152	4.19	0.24	19	81	
Com36	Blue-green	469	1739	3.71	0.27	21	79	
Com11	Blue-green	1580	5717	3.62	0.28	22	78	
Com82	Blue-green	609	2081	3.42	0.29	23	77	red
CO366	Green-blue	273	893	3.26	0.31	23	77	red
CO121B	Green light	1389	4083	2.94	0.34	25	75	red
CO121A	Green light	1189	3344	2.81	0.36	26	74	red
Com52	Blue-green	2775	7795	2.81	0.36	26	74	red
CO184A	Green	1906	5311	2.79	0.36	26	74	red
CO95	Green	1745	4603	2.64	0.38	27	73	red
Com61	Blue-green	2126	5508	2.59	0.39	28	72	red
Com77	Blue-green	1896	4902	2.59	0.39	28	72	red
CO93	Green	1788	4578	2.56	0.39	28	72	red
CO58B	Green	2645	6528	2.47	0.41	29	71	red
CO58A	Green	797	1866	2.34	0.43	30	70	red
Com01	Blue-green	1311	3061	2.33	0.43	30	70	red
Com72	Blue-green	2795	6269	2.24	0.45	31	69	red
CO121C	Green light	1516	3395	2.24	0.45	31	69	red
Com50	Blue-green	2346	4972	2.12	0.47	32	68	orange
CO184C	Green	2343	4725	2.02	0.50	33	67	orange
Com10	Blue-green	1982	3963	2.00	0.50	33	67	orange
CO184B	Green	2196	4389	2.00	0.50	33	67	orange
Com47	Blue-green	1473	2927	1.99	0.50	33	67	orange
Com27	Blue-green	2251	4369	1.94	0.52	34	66	orange
CO100B	Green	1404	2700	1.92	0.52	34	66	orange
Com51	Blue-green	2506	4787	1.91	0.52	34	66	orange
Com97	Blue-green	1849	3492	1.89	0.53	35	65	orange
Com73	Blue-green	2083	3774	1.81	0.55	36	64	orange
Com80	Blue-green	711	1245	1.75	0.57	36	64	orange
Com25	Blue-green	1650	2807	1.70	0.59	37	63	orange
Com78	Blue-green	2666	4426	1.66	0.60	38	62	orange
CO121D	Green light	2819	4635	1.64	0.61	38	62	orange
Com81	Blue-green	1909	3017	1.58	0.63	39	61	yellow
Com45	Blue-green	3113	4863	1.56	0.64	39	61	yellow
Com46	Blue-green	3113	4863	1.56	0.64	39	61	yellow
Com26	Blue-green	2559	3963	1.55	0.65	39	61	yellow
Com58	Blue-green	590	805	1.36	0.73	42	58	yellow
Com30	Blue-green	3631	4629	1.28	0.78	44	56	yellow

CO233C	Blue	3349	4264	1.27	0.79	44	56	yellow
Com55	Blue-green	788	979	1.24	0.80	45	55	yellow
Com12	Blue-green	2582	2479	0.96	1.04	51	49	
CO233B	Green	101	80	0.80	1.25	56	44	
CO24	Blue	6991	3381	0.48	2.07	67	33	
CO122	Blue	6345	2435	0.38	2.61	72	28	
Com90	Blue dark	6563	2480	0.38	2.65	73	27	
Com71	Blue-green	6927	1745	0.25	3.97	80	20	
Com69	Blue dark	12740	1970	0.15	6.47	87	13	
CO121E	Green light	2019	22	0.01	91.61	99	1	

Table S13. Calculation of bronze and brass hypothetical alloys.

Sample ID	Zn	Cu%	Zn%	Sample ID	Sn	Cu%	Sn%	Sample ID	Cu%	Zn%	Sn%
Com54	161	98	2	Com54	158	98	2	Com54	96	2	2
Com46	128	96	4	Com10	126	94	6	Com47	86	10	4
Com61	104	95	5	Com71	112	94	6	Com10	84	11	5
Com72	142	95	5	CO122	182	93	7	Com71	84	11	5
CO184C	114	95	5	Com12	126	93	7	CO122	91	3	7
Com39	158	95	5	CO24	178	92	8	Com90	88	5	7
Com90	150	94	6	Com90	208	92	8	Com12	84	10	7
Com95	723	94	6	CO100B	192	89	11	CO24	90	2	8
CO96	187	93	7	CO184B	261	89	11	CO100B	87	2	11
Com37	287	93	7	Com97	244	88	12	CO184B	87	2	11
Com97	131	93	7	CO121D	417	86	14	Com97	83	6	11
Com81	147	93	7	Com73	348	86	14	Com73	79	8	13
Com25	102	92	8	Com11	315	85	15	Com11	77	10	13
Com50	182	92	8	Com78	396	85	15	CO121D	83	3	14
CO184A	166	92	8	Com45	596	83	17	Com78	79	8	14
Com45	265	92	8	Com46	596	83	17	Com51	75	10	15
Com27	217	92	8	CO121C	305	83	17	CO121C	80	3	16
Com52	364	91	9	CO184C	421	83	17	Com46	80	4	16
Com73	214	91	9	CO95	381	83	17	CO184C	79	4	16
Com78	222	91	9	Com51	446	83	17	Com45	77	7	16
CO23A	102	90	10	Com52	840	82	18	Com77	73	11	16
CO100A	255	90	10	Com77	359	82	18	Com82	64	19	16
Com47	161	90	10	CO121B	444	81	19	CO95	80	3	17
CO88	186	89	11	Com01	333	81	19	Com52	75	7	17
CO58B	142	89	11	Com37	848	81	19	CO121B	78	3	18
Com10	268	89	11	CO233C	523	80	20	Com01	79	3	18
Com12	190	89	11	Com82	183	80	20	Com37	76	6	18
CO325	267	88	12	Com30	672	79	21	CO233C	78	3	19
Com11	246	88	12	Com72	872	77	23	Com55	41	39	20
Com51	285	88	12	Com50	691	76	24	Com89	47	32	21
Com71	246	88	12	Com61	630	76	24	Com72	74	4	22
Com77	252	87	13	CO184A	670	74	26	Com61	73	4	23
Com13	428	86	14	CO96	896	74	26	Com50	71	6	23
CO92	589	84	16	Com95	4052	74	26	Com95	71	4	24
Com98	482	84	16	Com25	424	73	27	CO96	70	5	24
Com94	905	83	17	CO93	706	71	29	CO184A	70	6	24
Com66	506	81	19	CO58A	343	70	30	Com25	69	6	25
Com02	527	80	20	Com89	741	69	31	Com36	56	19	26
Com40	230	80	20	CO121A	575	68	32	Com65	25	49	26
Com96a	316	80	20	Com36	219	68	32	CO93	69	3	28
Com82	220	77	23	Com55	106	67	33	CO58A	66	5	28
CO230	194	76	24	Com80	278	67	33	Com64	37	36	28
Com48	2455	76	24	CO366	196	64	36	Com80	62	8	30
Com36	161	75	25	CO23A	521	63	37	CO121A	66	4	31
CO530	2442	75	25	CO58B	668	63	37	CO366	59	7	33
Com58	153	63	37	CO325	1203	62	38	CO23A	59	7	35
Com89	1154	59	41	CO365	137	60	40	CO58B	58	7	35
Com24	142	52	48	Com96a	842	60	40	CO325	57	8	35
Com26	241	51	49	Com40	656	58	42	Com96a	52	13	35
Com64	198	51	49	CO530	5277	58	42	CO530	48	16	35
Com55	206	51	49	Com64	152	57	43	Com40	50	13	37
Com65	364	34	66	Com63	861	57	43	CO365	57	5	38
				Com02	1700	56	44	Com02	49	12	39
				CO100A	1801	56	44	Com48	47	15	39
				Com48	6507	55	45	Com24	31	29	40
				CO92	2875	53	47	CO100A	53	6	41
				Com13	2339	52	48	CO92	48	9	43
				Com98	2599	50	50	Com13	48	8	44
				Com65	193	49	51	Com98	46	9	46
				Com39	3250	46	54	Com58	34	20	46
				Com24	194	44	56	Com26	26	26	48
				Com66	2833	44	56	Com66	40	9	51
				Com94	5883	43	57	Com94	40	8	52
				Com58	354	42	58	CO230	36	12	52
				CO88	2201	41	59	Com39	45	3	53
				CO230	874	41	59	CO88	40	5	56
				CO58C	183	37	63	CO58C	32	11	56
				Com26	449	35	65				

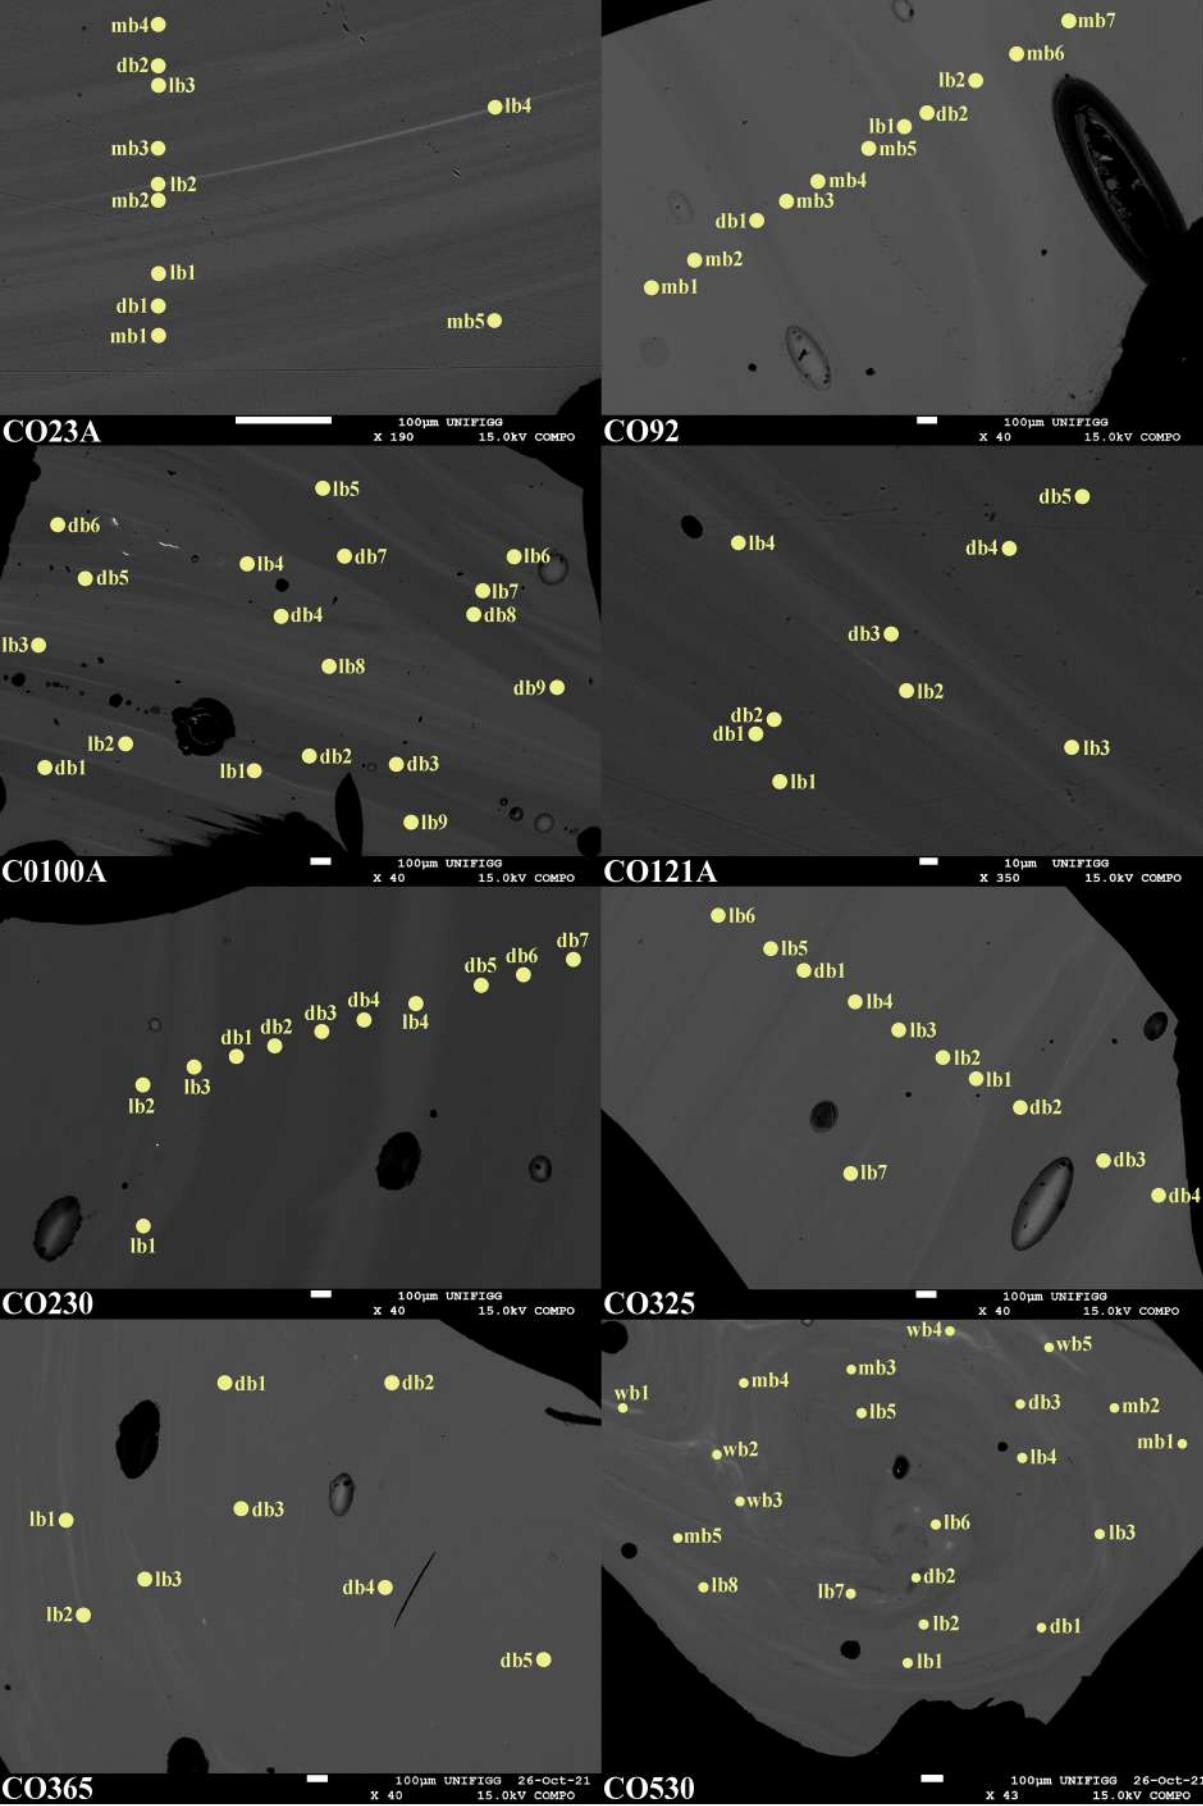


Figure S1. Banded samples CO23A, 92, 100A, 121A, 230, 325, 365 and 530. The spot analysis is reported in Supplementary Table S4.

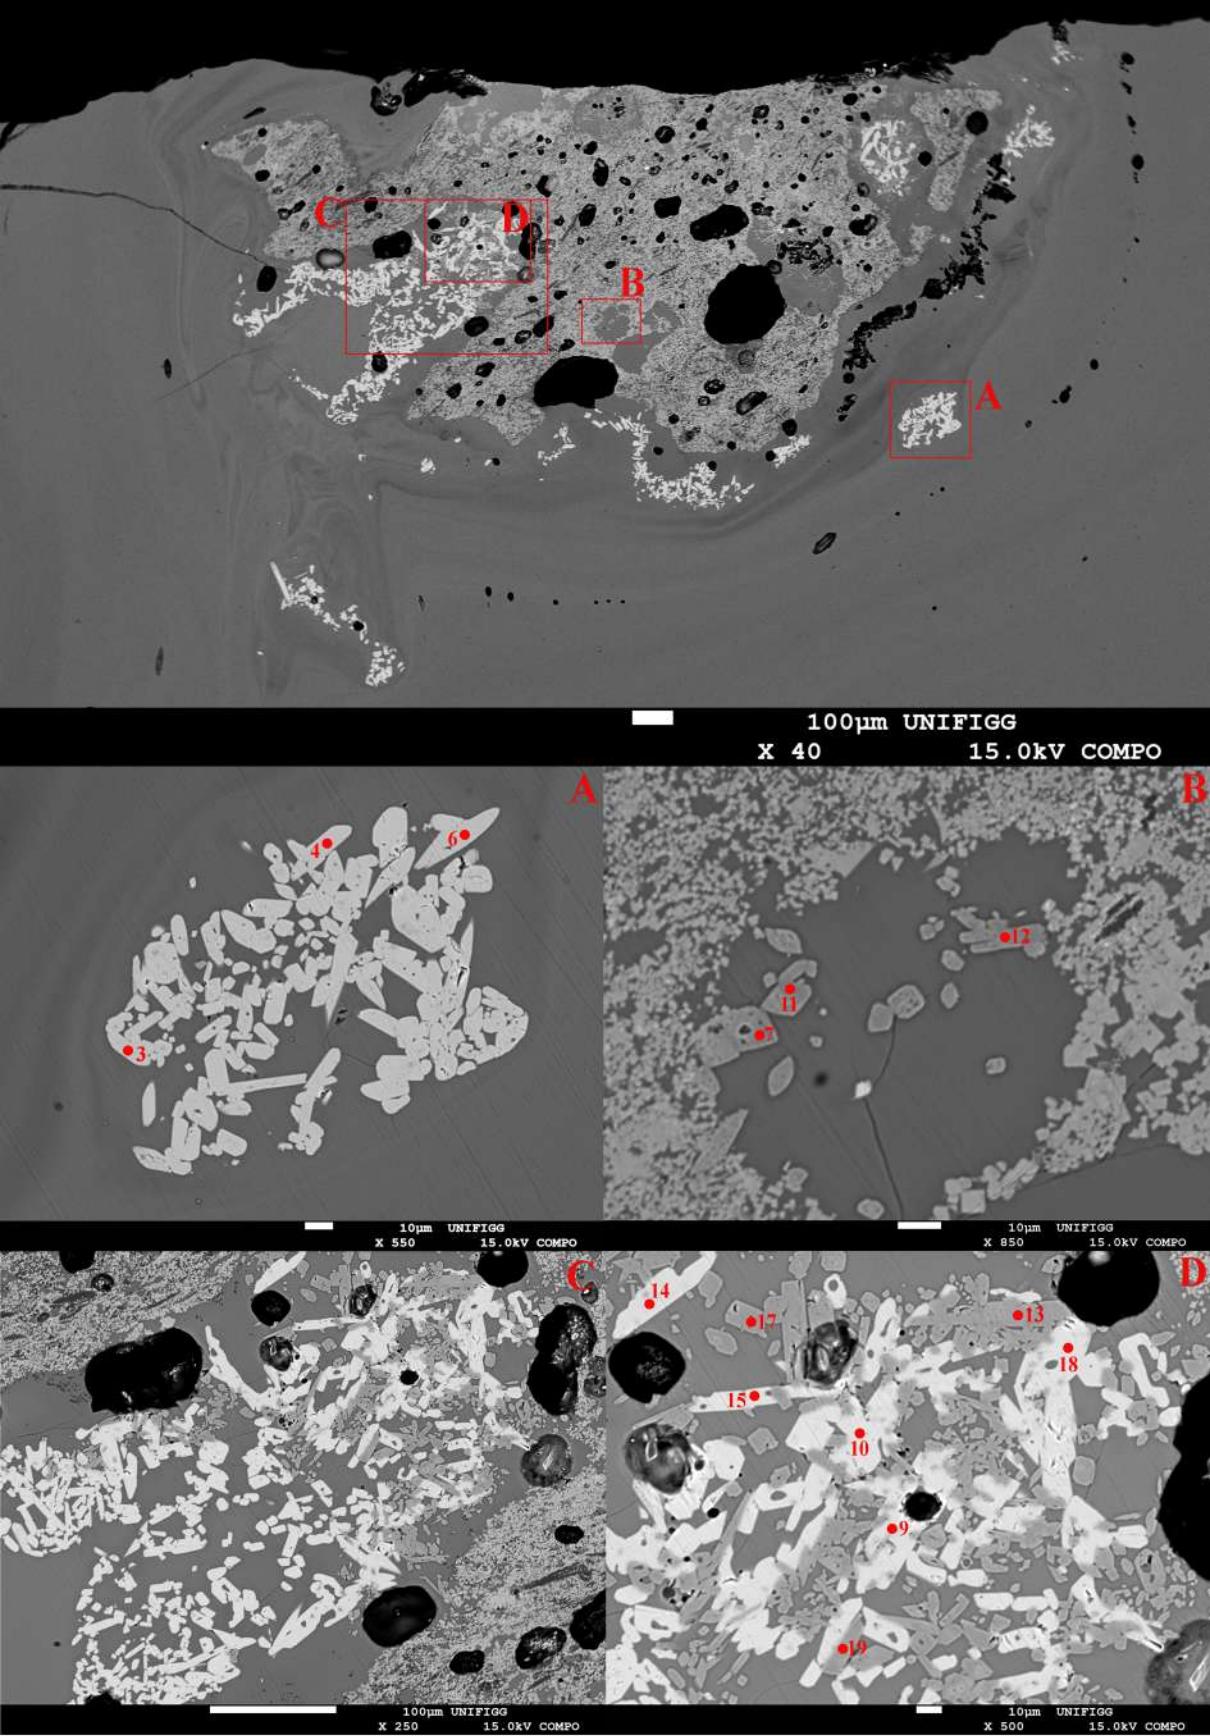


Figure S2. The sample CO23. Spot analyses are provided in Tables S6 and S7.

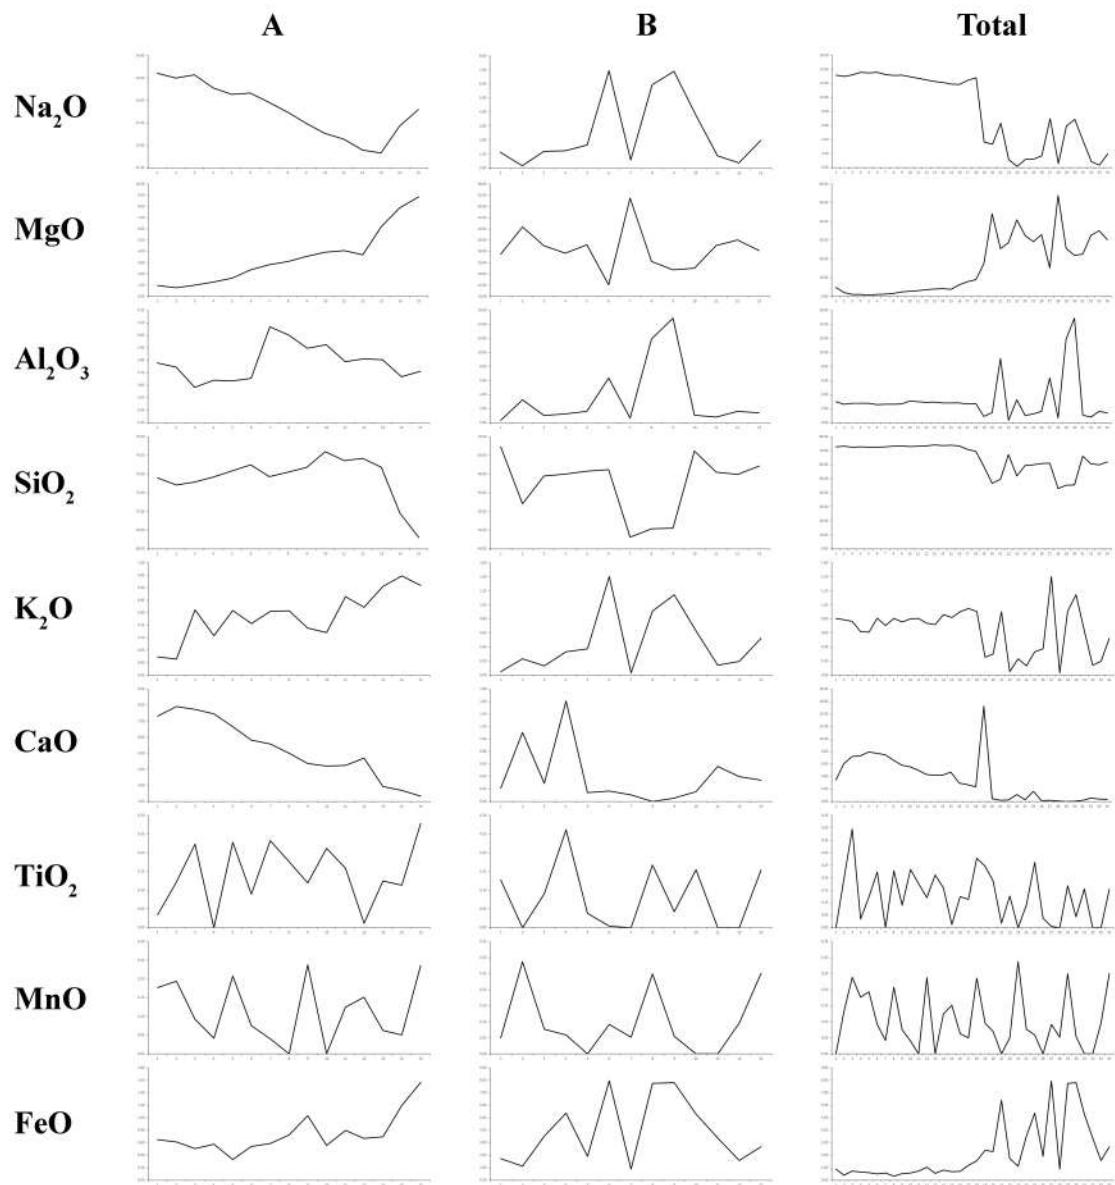
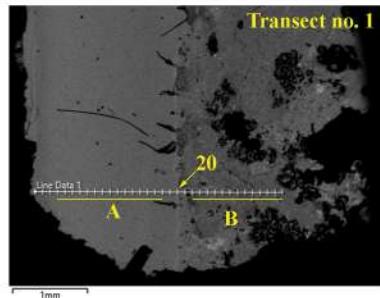


Figure S3. Transect no. 1 on CO58C glass.

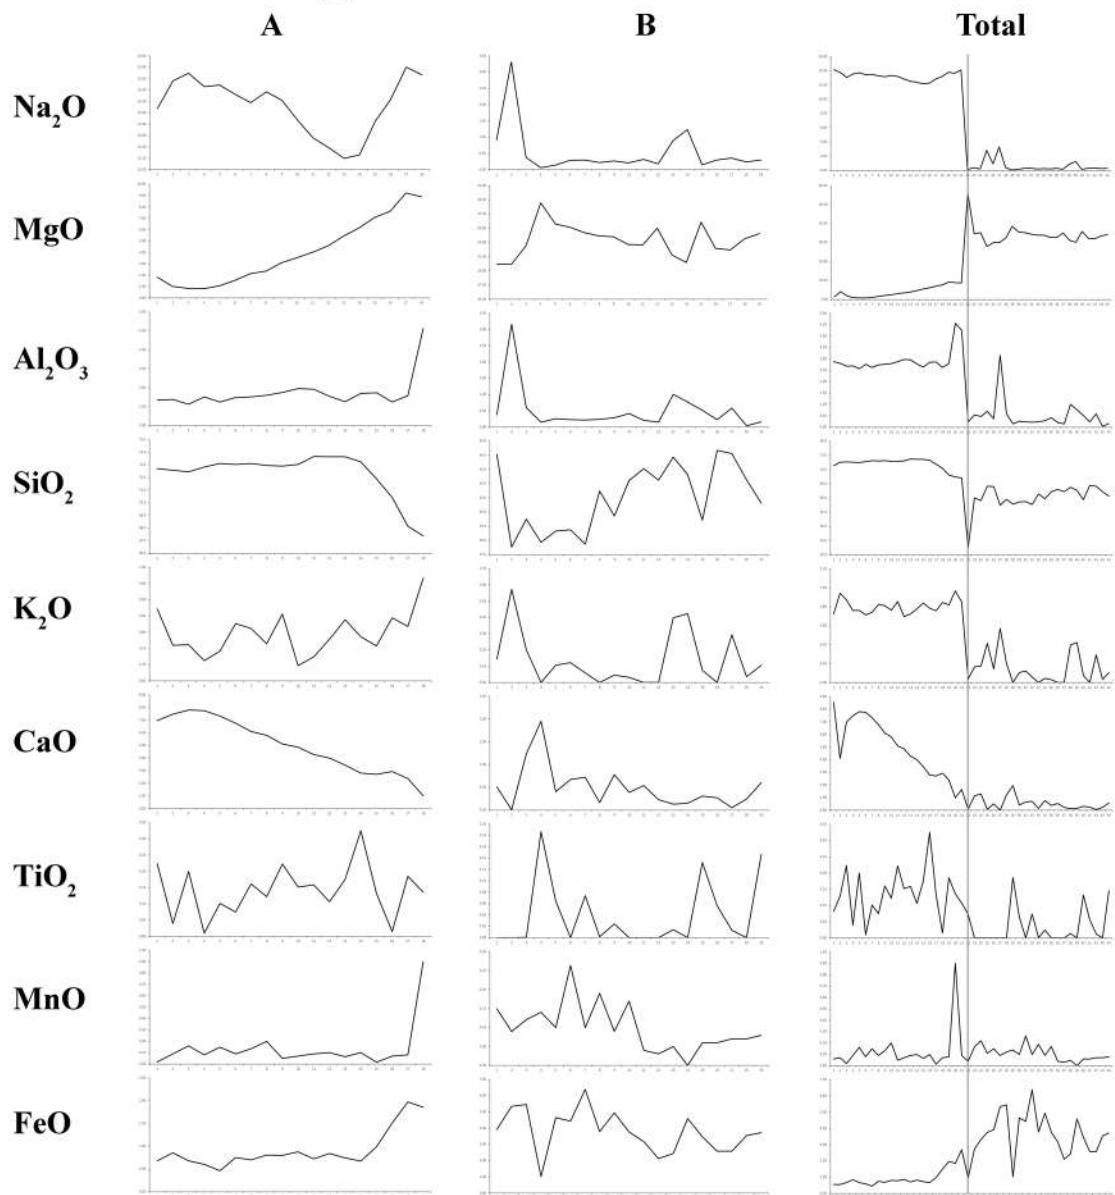
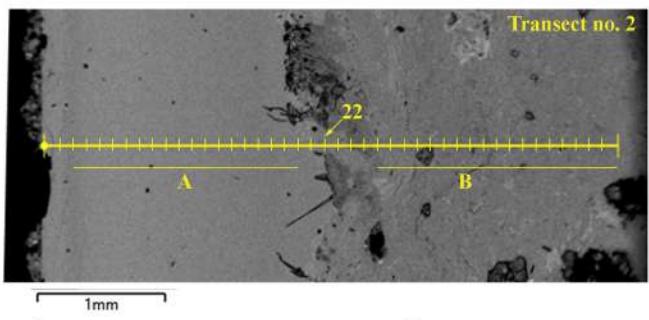


Figure S4. Transect no. 2 on CO58C glass.

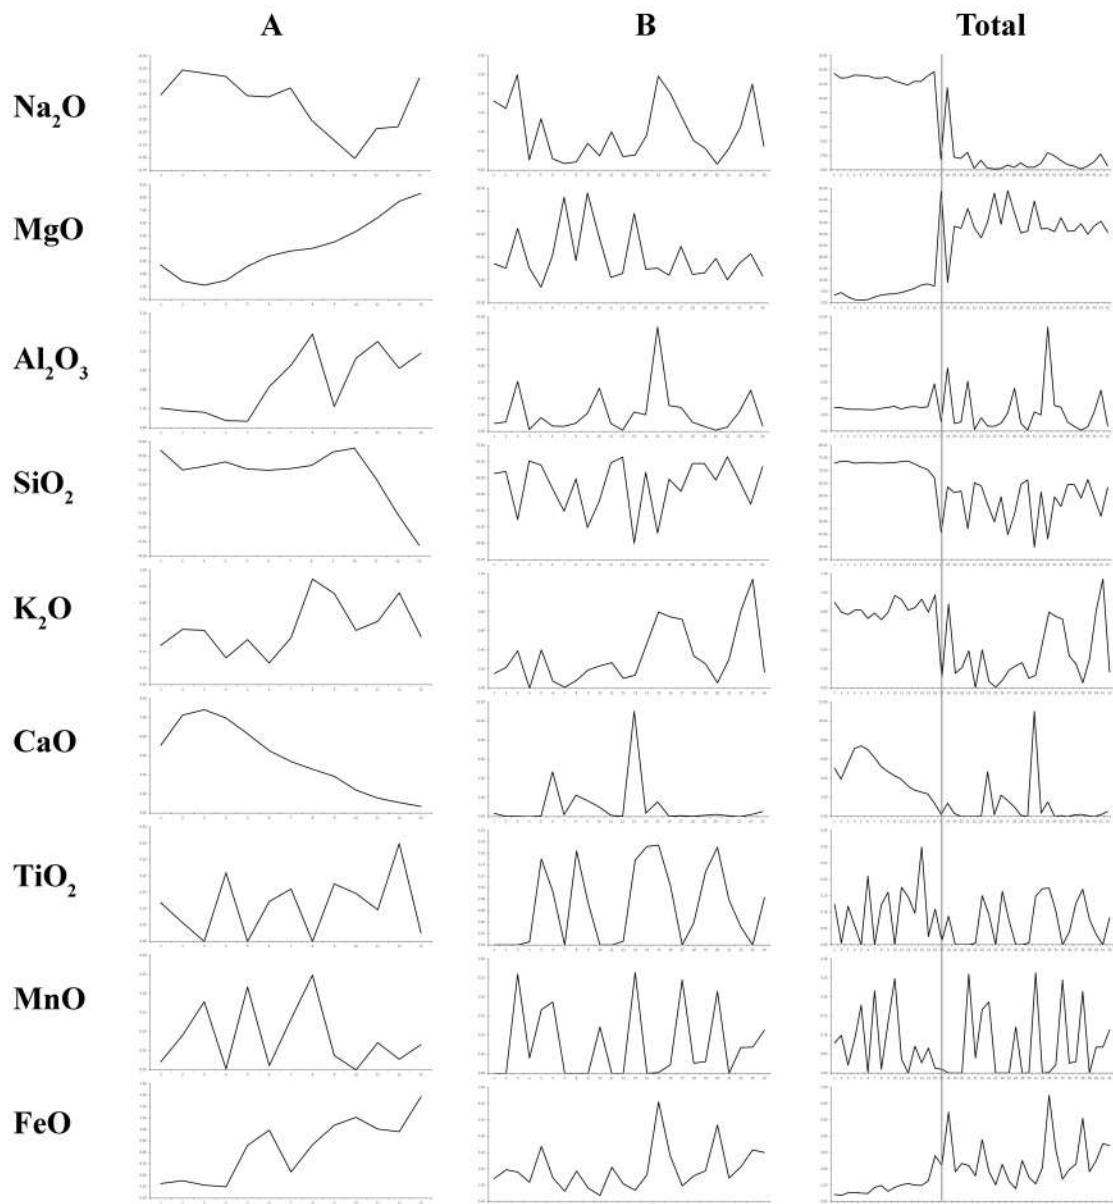
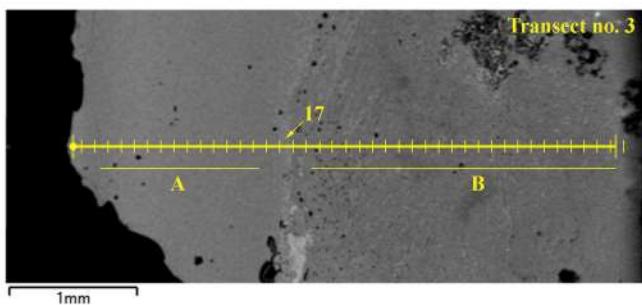


Figure S5. Transect no. 3 on CO58C glass.

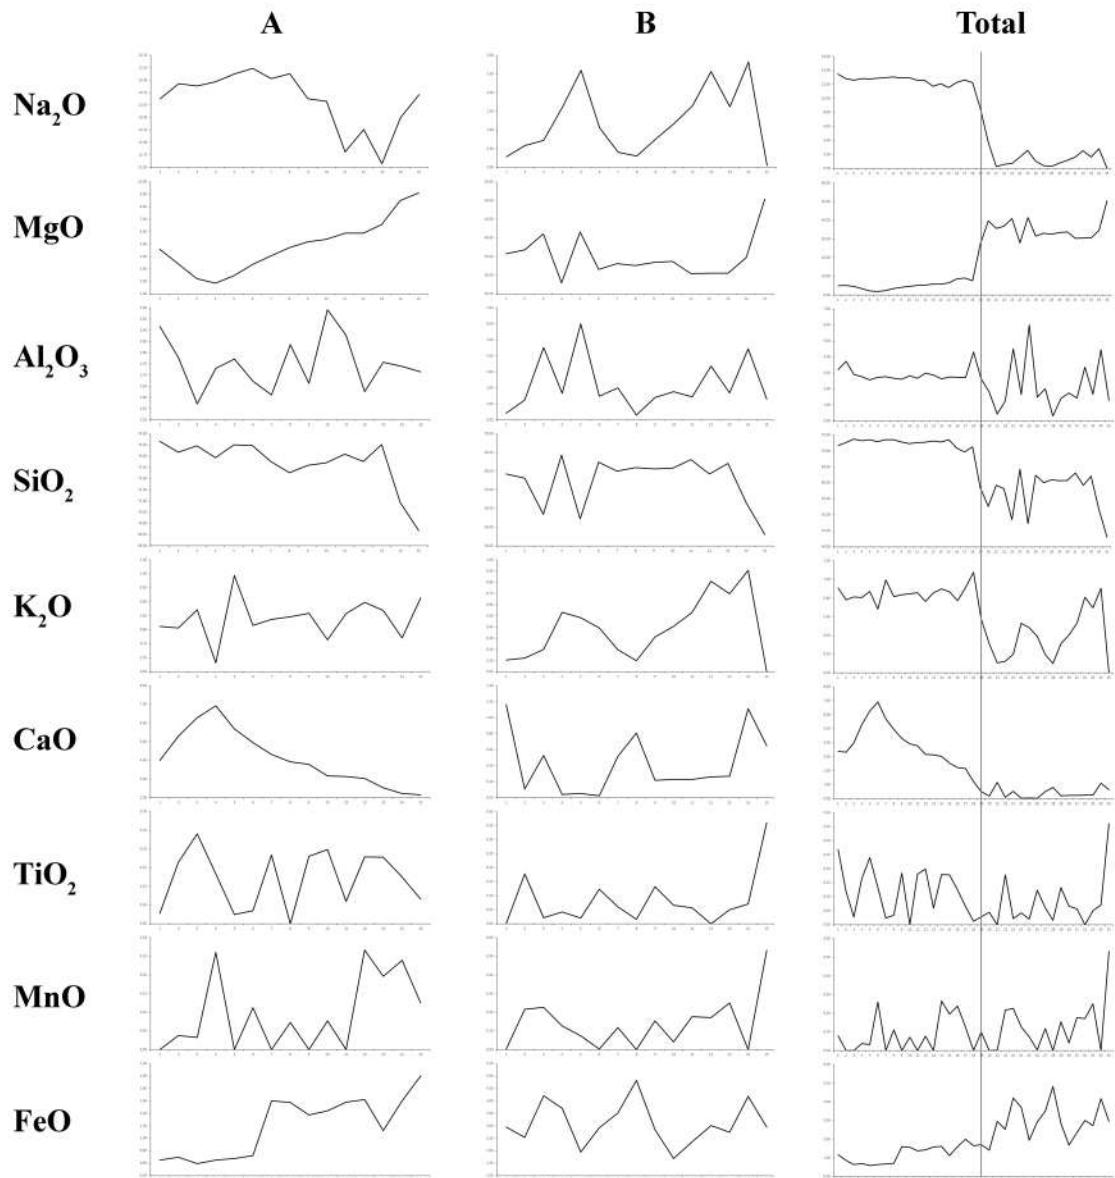
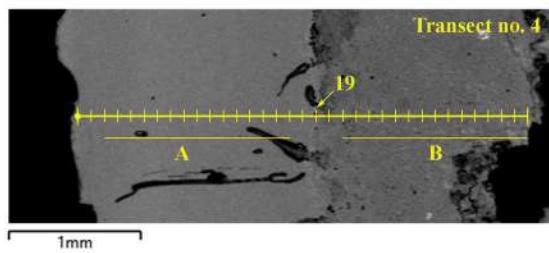


Figure S6. Transect no. 4 on CO58C glass.

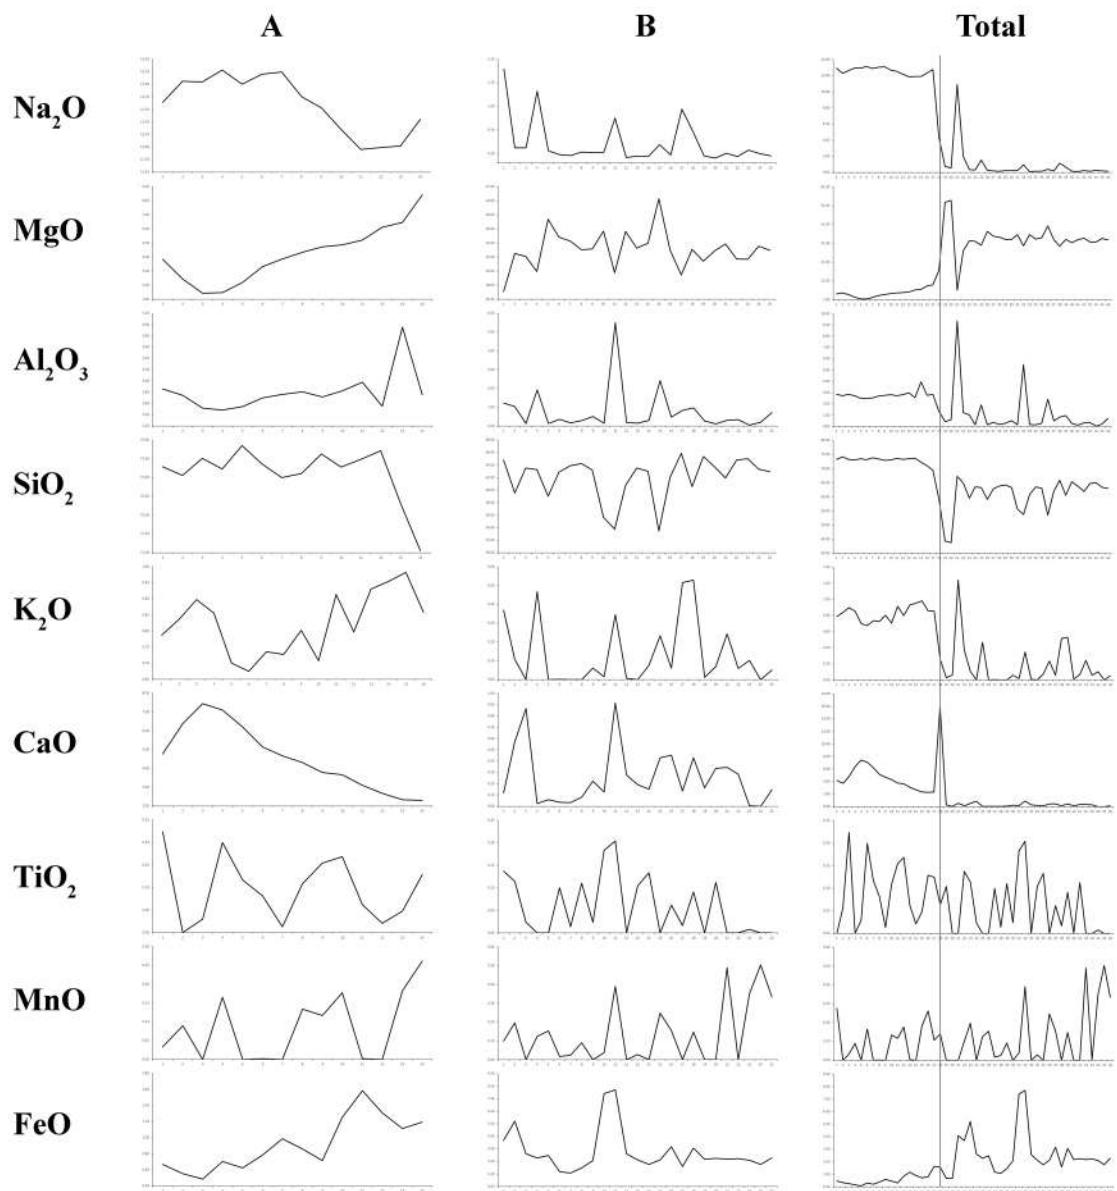
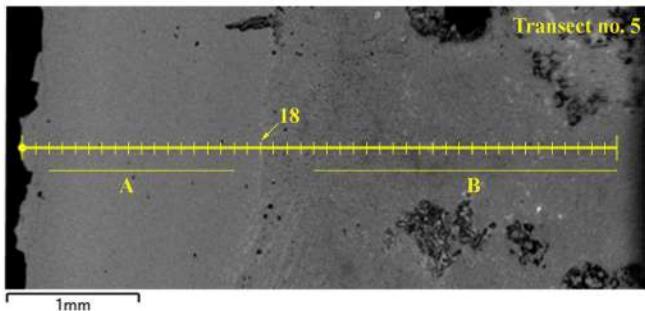


Figure S7. Transect no. 5 on CO58C glass.

Appendix.

In the following pages, Cu, Zn, Sn, Sb and Pb values have been recalculated, assuming they were introduced as unalloyed copper, bronze, brass, ternary Cu-Zn-Sn alloy (indicated as gunmetal), lead antimonate and lead stannate.

The observed correlations are also specified next to the sample number at the top of the page.

In the table, each row corresponds to a possible combination (indicated in the last column on the right) and the numbers indicate the percentages of each compound. The “raw” alloys -calculated based on the absolute element contents are listed in the first raw in blue, orange, red and black.

As for the colours:

- blue text means the calculated alloy is reasonable.
- orange text indicates that alloying is possible but not frequent or unlikely.
- red text means that the calculated alloy is not reasonable.
- orange highlighting distinguishes values obtained using constraint no. 1, *i.e.* arbitrarily fixing the composition of the bronze alloy to Cu₉₀Sn₁₀.
- green highlighting is for values obtained using constraint no. 2, *i.e.* arbitrarily fixing the composition of Pb antimonate to Sb₄₂Pb₅₈.
- blue highlighting marks the values obtained with constraint no. 3, *i.e.* arbitrarily fixing both the composition of the bronze alloy to Cu₉₀Sn₁₀ and the composition of the Pb antimonate to Sb₄₂Pb₅₈.
- Dark orange highlighting is used for the calculation of a gunmetal alloy where the Sn value is brought to match that of Zn (*i.e.* to the lowest value).

The last rows outside the table specify how much Pb and Sn remain free after setting the I, II and III constraints, respectively.

Lastly, the vertical thick lines at the end of the last column indicates which combinations were considered the most reasonable and reported in the summary tables at the end of the sheets provided for each sample.

Com01 – Correlations Cu/Sb (1.10), SnPb, red group lead antimonates ($\text{Sb}_{30}\text{Pb}_{70}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total		
		Blue-green	1443	51	333	1311	3061	6199		
			Pb							
			Sn							
		Cu	Sn							
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 51 ppm Zn content as “natural”)
					Sn ₁₀ Pb ₉₀		Sb ₄₂ Pb ₅₈	Sb ₃₀ Pb ₇₀		
	23				55			21	100	✓
	23					50		21	95	x 333 ppm Sn
	23						71		95	x 333 ppm Sn
	23				20	51			95	x 333 ppm Sn
	23				Sn ₂₁ Pb ₇₉					
					26	51		100		Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
		29			55			21	105	✓ [Sn counted twice]
		29				50		21	100	✓
Bronze		29					71		100	✓
		29			20	51			100	✓
		29			Sn ₂₁ Pb ₇₉					
		29			26	51		105		Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
		26			Sn ₅ Pb ₉₅			21	100	
		26			43					Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
		26			Sn ₁₂ Pb ₈₈			23	51	
									100	✓
										Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 41% Pb free (1250 ppm)

II constraint Cu₉₀Sn₁₀ → 52% Sn free (173 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com02 – Correlation strong SnPb.

I constraint Sb₄₂Pb₅₈ → 98% Pb free (12940 ppm)

II constraint Cu₉₀Sn₁₀ → 86% Sn free (1461 ppm)

III constraint : gunmetal with Sn=Zn → 69% Sn free (1173 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com10 – Correlations Cu/Sb (1.07), SnPb, orange group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Blue-green	2112	268	126	1982	3963	8451	
Sn								
			Pb					
Cu								
Brass Bronze Gunmetal								
<chem>Cu89Zn11</chem> <chem>Cu94Sn6</chem> <chem>Cu90Sn10</chem> <chem>Cu84Sn5Zn11</chem> <chem>Cu80Sn10Zn10</chem> <chem>Sn3Pb97</chem> <chem>Sb42Pb58</chem> <chem>Sb33Pb67</chem>								
Unalloyed	25		48			23 97	x 268 ppm Zn x 126 ppm Sn + 268 ppm Zn x 126 ppm Sn + 268 ppm Zn x 126 ppm Sn + 268 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	25			47		23 95		
	25				70	95		
	25			15 56		95		
	25						x 268 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	28		48			23 100	✓	Brass + SnPb + Sb
	28			47		23 99	x 126 ppm Sn	Brass + Pb + Sb
	28				70	99	x 126 ppm Sn	Brass + SbPb
	28		15* 56			99	x 126 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28		16	56		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	26		48			23 98	x 268 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	26			47		23 97	x 268 ppm Zn	Bronze + Pb + Sb
	26				70	97	x 268 ppm Zn	Bronze + SbPb
	26		15* 56			97	x 268 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26		16	56		98	x 268 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	28			-		23 -	x -	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	28				56		x -	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	30		48			23 101	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	30			47		23 100	✓	Gunmetal + Pb + Sb
	30				70	100	✓	Gunmetal + SbPb
	30		15* 56			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
31								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								
Low Sn								

Com11 – Correlations Cu/Sb (1.16), SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Blue-green	1830	246	315	1580	5717	9687	
			Pb					
		Sn						
		Cu						
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
								Sb ₄₂ Pb ₅₈
								Sb ₂₂ Pb ₇₈
Unalloyed	19				62			16 97
	19					59		16 94
	19						75	94
	19					37 39		94
	19							x 246 ppm Zn x 315 ppm Sn + 246 ppm Zn x 315 ppm Sn + 246 ppm Zn x 315 ppm Sn + 246 ppm Zn
Brass	21					Sn ₈ Pb ₉₂		
	21				62	40	39	97
	21					59		16 100
	21						75	16 97
	21					37*	39	97
	21					40	39	100
Bronze	22				62			16 101
	22					59		16 97
	22						75	97
	22					36*	39	97
	22					Sn ₈ Pb ₉₂	40 39	101
	21					Sn ₂ Pb ₉₈	60	16 97
Gunmetal	21					Sn ₃ Pb ₉₇		x 246 ppm Zn
	25				62			x 246 ppm Zn [Sn counted twice]
	25					59		x 246 ppm Zn
	25						75	x 246 ppm Zn
	25					36*	39	x 246 ppm Zn
	24					Sn ₂ Pb ₉₈	37 39	97
								x 246 ppm Zn
								✓ [Sn counted twice]
								✓
								✓
								✓
								✓
								✓
								Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 62% Pb free (3535 ppm)

II constraint Cu₉₀Sn₁₀ → 35% Sn free (111 ppm)

III constraint : gunmetal with Sn=Zn → 22% Sn free (68 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com12 – Correlation SnPb.

Colour	Cu	Zn	Sn	Sb	Pb	Total
Blue-green	1603	190	126	2582	2479	6980

		Sn		Pb									
		Cu		Sb									
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 190 ppm Zn content as “non natural”)	
Unalloyed	Cu ₈₉ Zn ₁₁	Cu ₉₃ Sn ₇	Cu ₉₀ Sn ₁₀	Cu ₈₄ Sn ₇ Zn ₁₀	Cu ₈₁ Sn ₁₀ Zn ₁₀	Sn ₅ Pb ₉₅			Sb ₄₂ Pb ₅₈	Sb ₅₁ Pb ₄₉			
	23					37			37	97	x 190 ppm Zn		Unalloyed Cu + SnPb + Sb
	23						36		37	95	x 126 ppm Sn + 190 ppm Zn		Unalloyed Cu + Pb + Sb
	23							-	73	95	x 126 ppm Sn + 190 ppm Zn		Unalloyed Cu + SbPb
Brass	23							Low Pb		96	x -		Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	23										x -		Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	26					37			37	100	✓		Brass + SnPb + Sb
	26						36		37	98	x 126 ppm Sn		Brass + Pb + Sb
Bronze	26							-	73	98	x 126 ppm Sn		Brass + SbPb
	26							Low Pb		98	x -		Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26									100	x -		Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
	25					37			37	99	x 190 ppm Zn [Sn counted twice]		Bronze + SnPb + Sb
Gunmetal	25						36		37	97	x 190 ppm Zn		Bronze + Pb + Sb
	25							-	73	97	x 190 ppm Zn		Bronze + SbPb
	25							Low Pb		-	x 190 ppm Zn		Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	25										x 190 ppm Zn [Sn counted twice]		Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	26										x 190 ppm Zn		Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	26							-					Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	27					37			37	102	✓ [Sn counted twice]		Gunmetal + SnPb + Sb
	27						36		37	100	✓		Gunmetal + Pb + Sb
	27							-	73	100	✓		Gunmetal + SbPb
	27							Low Pb		100	x -		Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28									100	x -		Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 44% Pb less (1087 ppm missing)

II constraint Cu₉₀Sn₁₀ → 41% Sn less (52 ppm missing)

III constraint : gunmetal with Sn=Zn → 51% Sn less (64 ppm missing)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com13 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	2532	428	2339	775	20701	26777					
Pb												
		Sn										
		Cu		Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 428 ppm Zn content as “non natural”)		
Unalloyed	Cu ₈₆ Zn ₁₄	Cu ₅₂ Sn ₄₈	Cu ₉₀ Sn ₁₀	Cu ₄₈ Sn ₄₄ Zn ₈	Cu ₇₅ Sn ₁₃ Zn ₁₃	Sn ₁₀ Pb ₉₀		Sb ₄₂ Pb ₅₈	Sb ₄ Pb ₉₆			
	9					86		3	98	x 428 ppm Zn	Unalloyed Cu + SnPb + Sb	
	9						77	3	90	x 2339 ppm Sn + 428 ppm Zn	Unalloyed Cu + Pb + Sb	
	9							80	90	x 2339 ppm Sn + 428 ppm Zn	Unalloyed Cu + SbPb	
	9						73	7	90	x 2339 ppm Sn + 428 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
Brass	9											
	11						82	7	98	x 428 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	11						86		3	100	✓	Brass + SnPb + Sb
	11						77	3	91	x 2339 ppm Sn	Brass + Pb + Sb	
	11							80	91	x 2339 ppm Sn	Brass + SbPb	
Bronze	11						73	7	91	x 2339 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	18						82	7	100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	18						86		3	107	x 428 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	18						77	3	98	x 428 ppm Zn	Bronze + Pb + Sb	
	18							80	98	x 428 ppm Zn	Bronze + SbPb	
Gunmetal	18						73	7	98	x 428 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	18											
	11						82	7	107	x 428 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	11						85		3	98	x 428 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	11						Sn ₉ Pb ₉₁	81	7	98	x 428 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	20						86		3	109	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	20						77	3	100	✓		Gunmetal + Pb + Sb
	20							80	100	✓		Gunmetal + SbPb
	20						73	7	100	✓		Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	13						Sn ₉ Pb ₉₁	80	7	100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 95% Pb free (19631 ppm)


II constraint Cu₉₀Sn₁₀ → 88% Sn free (2058 ppm)

III constraint : gunmetal with Sn=Zn → 82% Sn free (1911 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com24 – Correlations Cu/Sb (0.75), strong SnPb.

Colour	Cu	Zn	Sn	Sb	Pb	Total
Blue-green	153	142	194	205	1608	2301

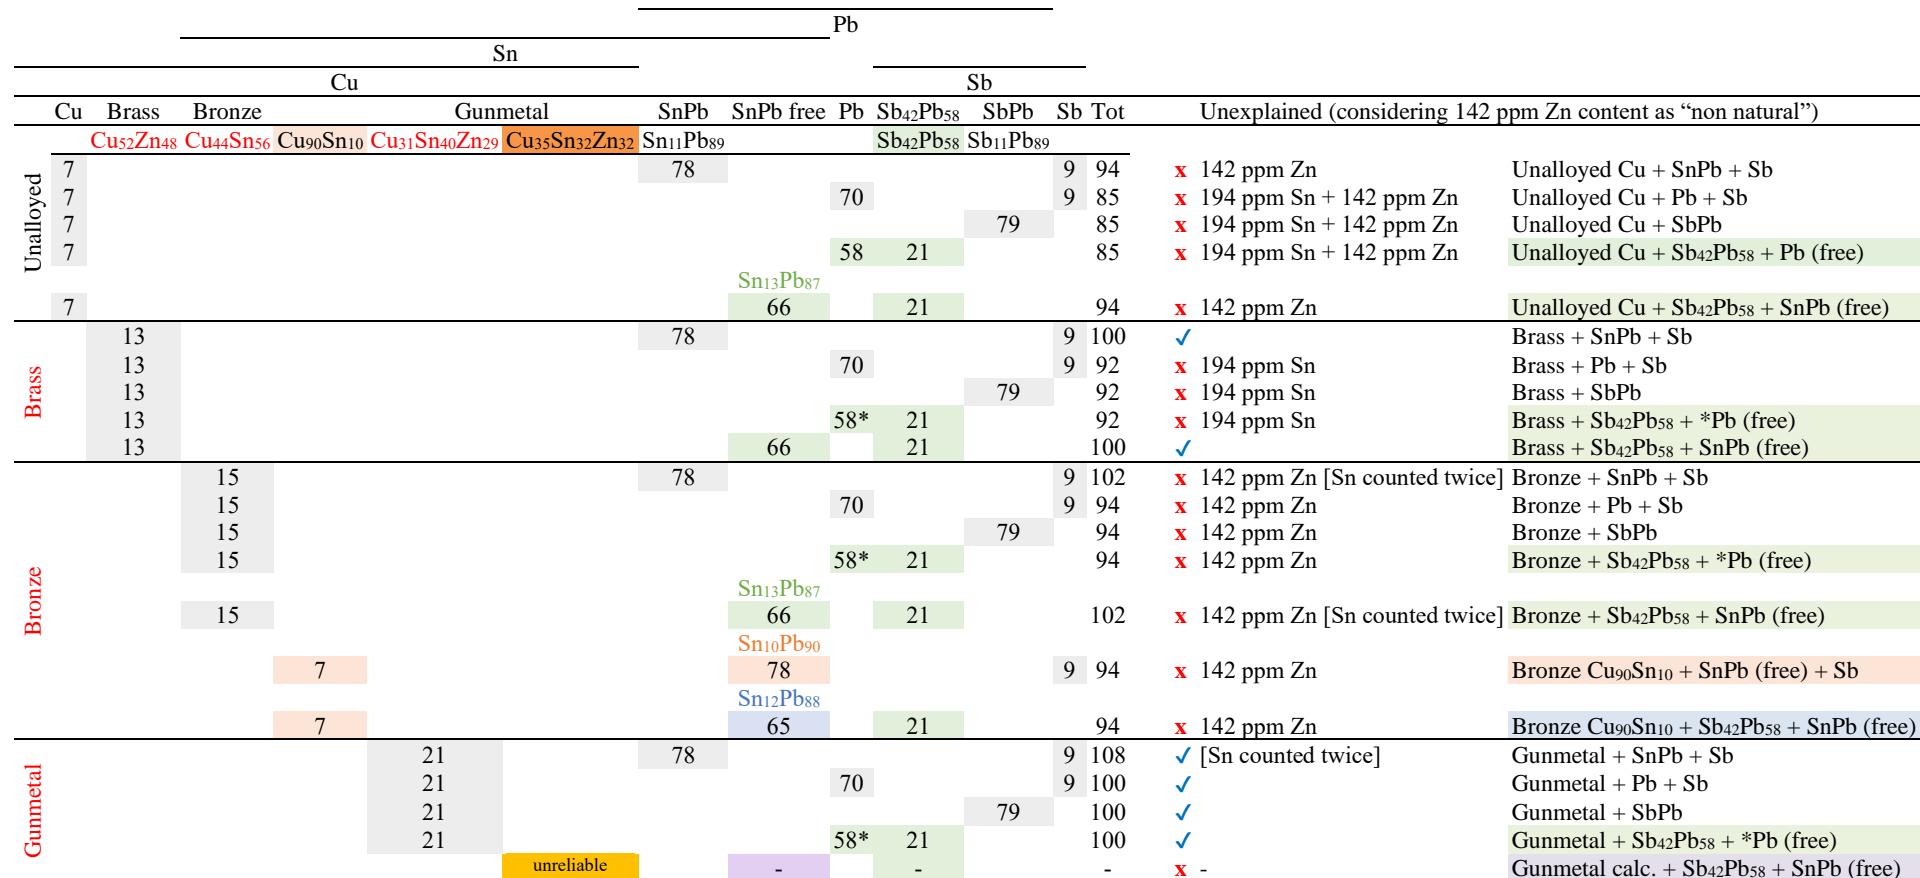

I constraint Sb₄₂Pb₅₈ → 82% Pb free (1325 ppm)

II constraint Cu₉₀Sn₁₀ → 91% Sn free (177 ppm)

III constraint : gunmetal with Sn=Zn → 27% Sn free (52 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com25 – Correlations Cu/Sb (0.70), strong SnPb, orange correlation lead antimonates ($\text{Sb}_{37}\text{Pb}_{63}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total				
		Blue-green	1161	102	424	1650	2807	6143				
		Pb										
		Sn										
		Cu										
Unalloyed		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 102 ppm Zn content as “non natural”)
		Cu ₉₂ Zn ₈	Cu ₇₃ Sn ₂₇	Cu ₉₀ Sn ₁₀	Cu ₆₉ Sn ₂₅ Zn ₆	Cu ₈₆ Sn ₇ Zn ₇	Sn ₁₃ Pb ₈₇		Sn ₄₂ Pb ₅₈	Sn ₃₇ Pb ₆₃		
19						53			27	98		x 102 ppm Zn
19							46		27	91		x 424 ppm Sn + 102 ppm Zn
19								73	91		x 424 ppm Sn + 102 ppm Zn	
19							9	64		91		x 424 ppm Sn + 102 ppm Zn
												Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
19												Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	21					53			27	100	✓	Unalloyed Cu + SnPb + Sb
	21						46		27	93		x 424 ppm Sn
	21							73	93		x 424 ppm Sn	
	21						9*	64		93		x 424 ppm Sn
	21									100	✓	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
												Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	26					53			27	105	x 102 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	26						46		27	98	x 102 ppm Zn	Bronze + Pb + Sb
	26							73	98		x 102 ppm Zn	Bronze + SbPb
	26						9*	64		98		Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26									105	x 102 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	21											Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	21											Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	27					53			27	107	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	27						46		27	100	✓	Gunmetal + Pb + Sb
	27							73	100	✓	Gunmetal + SbPb	
	27						9*	64		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	22									100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 19% Pb free (528 ppm)

II constraint Cu₉₀Sn₁₀ → 70% Sn free (295 ppm)

III constraint : gunmetal with Sn=Zn → 76% Sn free (322 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com26 – Correlations strong SnPb, yellow correlation lead antimonates ($\text{Sb}_{39}\text{Pb}_{61}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Blue-green	246	241	449	2559	3963	7458				
				Pb							
			Sn								
		Cu			Sb						
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 241 ppm Zn content as “non natural”)	
	$\text{Cu}_{51}\text{Zn}_{49}$	$\text{Cu}_{35}\text{Sn}_{65}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{26}\text{Sn}_{48}\text{Zn}_{26}$	$\text{Cu}_{34}\text{Sn}_{33}\text{Zn}_{33}$	$\text{Sn}_{10}\text{Pb}_{90}$		$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{39}\text{Pb}_{61}$		
Unalloyed	3				59			34	97	x 241 ppm Zn x 449 ppm Sn + 241 ppm Zn x 449 ppm Sn + 241 ppm Zn x 449 ppm Sn + 241 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	3					53		34	91		
	3						87		91		
	3					6	82		91		
	3										
Brass	3				$\text{Sn}_{51}\text{Pb}_{49}$	12	82		97	x 241 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	7				59			34	100	✓	Brass + SnPb + Sb
	7					53		34	94	x 449 ppm Sn	Brass + Pb + Sb
	7						87		94	x 449 ppm Sn	Brass + SbPb
	7					6	82		94	x 449 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Bronze	9				59			34	100	✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	9					53		34	97	x 241 ppm Zn	Bronze + SnPb + Sb
	9						87		97	x 241 ppm Zn	Bronze + Pb + Sb
	9					6	82		97	x 241 ppm Zn	Bronze + SbPb
	9				$\text{Sn}_{51}\text{Pb}_{49}$	12	82		103	x 241 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Gunmetal	9				$\text{Sn}_{10}\text{Pb}_{90}$			34	97	x 241 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	4				$\text{Sn}_{50}\text{Pb}_{50}$						Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	4				11	82		97	x 241 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
	13				59			34	106	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	13					53		34	100	✓	Gunmetal + Pb + Sb
							87		100	✓	Gunmetal + SbPb
						6	82		100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
											Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
					unreliable		-	-		x	

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow$ 11% Pb free (430 ppm)

II constraint Cu₉₀Sn₁₀ → 94% Sn free (422 ppm)

III constraint : gunmetal with Sn=Zn → not calculated

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com36 – Correlations Cu/Sb (1.01), strong SnPb.

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow$ 63% Pb free (1092 ppm)

II constraint Cu₉₀Sn₁₀ → 76% Sn free (166 ppm)

III constraint : gunmetal with Sn=Zn \rightarrow 27% Sn free (58 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com37 – Correlation SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total				
		Blue-green	3667	287	848	2185	9152	16139				
		Pb										
		Sn										
		Cu										
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 287 ppm Zn content as “non natural”)		
	23				62			14	98	x 287 ppm Zn	Unalloyed Cu + SnPb + Sb	
	23					57		14	93	x 848 ppm Sn + 287 ppm Zn	Unalloyed Cu + Pb + Sb	
	23						70		93	x 848 ppm Sn + 287 ppm Zn	Unalloyed Cu + SbPb	
	23					38	32		93	x 848 ppm Sn + 287 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
Brass	23					Sn ₁₂ Pb ₈₈						
	24				62			43	32	98	x 287 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	24					57			14	100	✓	Brass + SnPb + Sb
	24						70		95	x 848 ppm Sn	Brass + Pb + Sb	
	24					38	32		95	x 848 ppm Sn	Brass + SbPb	
Bronze	24							43	32	100	✓	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28				62				14	103	x 287 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	28					57			14	98	x 287 ppm Zn	Bronze + Pb + Sb
	28						70		98	x 287 ppm Zn	Bronze + SbPb	
	28					38	32		98	x 287 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
Gunmetal	28					Sn ₁₂ Pb ₈₈						
	28				43			32		103	x 287 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	25					59			14	98	x 287 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	25					Sn ₅ Pb ₉₅						
	25					Sn ₇ Pb ₉₃						
	30				62			41	32	98	x 287 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	30					57			14	105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	30						70		100	✓		Gunmetal + Pb + Sb
	30					38	32		100	✓		Gunmetal + SbPb
						Sn ₈ Pb ₉₂			100	✓		Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 67% Pb free (6134 ppm)

II constraint Cu₉₀Sn₁₀ → 52% Sn free (441 ppm)

III constraint : gunmetal with Sn=Zn → 66% Sn free (561 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com39 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	2779	158	3250	1429	32277	39892					
Pb												
Sn												
	Cu	Sn		Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 158 ppm Zn content as “non natural”)	
	Cu ₉₅ Zn ₅	Cu ₄₆ Sn ₅₄	Cu ₉₀ Sn ₁₀	Cu ₄₅ Sn ₅₃ Zn ₃	Cu ₉₀ Sn ₅ Zn ₅	Sn ₉ Pb ₉₁		Sb ₄₂ Pb ₅₈	Sb ₄ Pb ₉₆			
Unalloyed	7						89			4 100	x 158 ppm Zn	Unalloyed Cu + SnPb + Sb
	7							81		4 91	x 3250 ppm Sn + 158 ppm Zn	Unalloyed Cu + Pb + Sb
	7								84	91	x 3250 ppm Sn + 158 ppm Zn	Unalloyed Cu + SbPb
	7						76	9		91	x 3250 ppm Sn + 158 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	7									100	x 158 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	7						84	9		100	✓	Brass + SnPb + Sb
	7						89			4 100	x 3250 ppm Sn	Brass + Pb + Sb
	7							81		4 92	x 3250 ppm Sn	Brass + SbPb
	7								84	92	x 3250 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	7						76	9		92	x 3250 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	15						89			4 108	x 158 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	15							81		4 100	x 158 ppm Zn	Bronze + Pb + Sb
	15								84	100	x 158 ppm Zn	Bronze + SbPb
	15						76	9		100	x 158 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	15									108	x 158 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	8									4 100	x 158 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	8									100	x 158 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	16						89			4 108	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	16							81		4 100	✓	Gunmetal + Pb + Sb
	16								84	100	✓	Gunmetal + SbPb
	16						76	9		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	8									100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 94% Pb free (30303 ppm)

II constraint Cu₉₀Sn₁₀ → 90% Sn free (2941 ppm)

III constraint : gunmetal with Sn=Zn → 95% Sn free (3092 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com40 – Correlation strong SnPb.

I constraint Sb₄₂Pb₅₈ → 84% Pb free (4191 ppm)

II constraint Cu₉₀Sn₁₀ → 85% Sn free (556 ppm)

III constraint : gunmetal with Sn=Zn \rightarrow 65% Sn free (425 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com45 – Correlations Cu/Sb (0.94), strong SnPb, yellow group lead antimonates ($\text{Sb}_{39}\text{Pb}_{61}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total						
		Blue-green	2930	265	596	3113	4863	11767						
		Sn		Pb										
		Cu			Sb									
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 128 ppm Zn content as “non natural”)		
		$\text{Cu}_{92}\text{Zn}_8$	$\text{Cu}_{83}\text{Sn}_{17}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{77}\text{Sn}_{16}\text{Zn}_7$	$\text{Cu}_{85}\text{Sn}_8\text{Zn}_8$	$\text{Sn}_{11}\text{Pb}_{89}$		$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{39}\text{Pb}_{61}$				
Unalloyed	25					46			26	98	x 265 ppm Zn	Unalloyed Cu + SnPb + Sb		
	25						41		26	93	x 596 ppm Sn + 265 ppm Zn	Unalloyed Cu + Pb + Sb		
	25							68	93	x 596 ppm Sn + 265 ppm Zn	Unalloyed Cu + SbPb			
	25						5	63	93	x 596 ppm Sn + 265 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)			
Brass	25					$\text{Sn}_{51}\text{Pb}_{49}$	10	63	98	x 265 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)			
	27					46			26	100	✓	Brass + SnPb + Sb		
	27						41		26	95	x 596 ppm Sn	Brass + Pb + Sb		
	27							68	95	x 596 ppm Sn	Brass + SbPb			
	27						5*	63	95	x 596 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)			
Bronze	27						10	63	100	✓		Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)		
	30					46			26	103	x 265 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb		
	30						41		26	98	x 265 ppm Zn	Bronze + Pb + Sb		
	30							68	98	x 265 ppm Zn	Bronze + SbPb			
	30						5*	63	98	x 265 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)			
Gunmetal	30					$\text{Sn}_{51}\text{Pb}_{49}$	10	63	103	x 265 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)			
	28					$\text{Sn}_{5}\text{Pb}_{95}$	44		26	98	x 265 ppm Zn	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + SnPb (free) + Sb		
	28					$\text{Sn}_{32}\text{Pb}_{68}$	7	63	98	x 265 ppm Zn	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)			
	32					46			26	105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb		
	32						41		26	100	✓	Gunmetal + Pb + Sb		
	32							68	100	✓		Gunmetal + SbPb		
	32						5*	63	100	✓		Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)		
	29					$\text{Sn}_{37}\text{Pb}_{63}$	8	63	100	✓		Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)		

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 12\% \text{ Pb free (564 ppm)}$

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 45\% \text{ Sn free (270 ppm)}$

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 55\% \text{ Sn free (331 ppm)}$

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com46 – Correlations Cu/Sb (0.94), strong SnPb, yellow group lead antimonates ($\text{Sb}_{39}\text{Pb}_{61}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	2930	128	596	3113	4863	11630					
	Pb											
	Sn											
	Cu		Sb									
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb	Tot	Unexplained (considering 128 ppm Zn content as “non natural”)	
	$\text{Cu}_{96}\text{Zn}_4$	$\text{Cu}_{83}\text{Sn}_{17}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{80}\text{Sn}_{16}\text{Zn}_4$	$\text{Cu}_{92}\text{Sn}_4\text{Zn}_4$	$\text{Sn}_{11}\text{Pb}_{89}$	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{39}\text{Pb}_{61}$				
Unalloyed	25					47			27	99	x 128 ppm Zn	Unalloyed Cu + SnPb + Sb
	25						42		27	94	x 596 ppm Sn + 128 ppm Zn	Unalloyed Cu + Pb + Sb
	25							69		94	x 596 ppm Sn + 128 ppm Zn	Unalloyed Cu + SbPb
	25						5	64		94	x 596 ppm Sn + 128 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	25											Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Brass	26					47			27	100	✓	Brass + SnPb + Sb
	26						42		27	95	x 596 ppm Sn	Brass + Pb + Sb
	26							69		95	x 596 ppm Sn	Brass + SbPb
	26					5*	64			95	x 596 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	26					10		64		100	✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Bronze	30					47			27	104	x 128 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	30						42		27	99	x 128 ppm Zn	Bronze + Pb + Sb
	30							69		99	x 128 ppm Zn	Bronze + SbPb
	30					5*	64			99	x 128 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	30											Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Gunmetal	28					47			104		x 128 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	28						42					Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	28							69				Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	31					7	64			99	x 128 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	31					47			27	105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	31						42		27	100	✓	Gunmetal + Pb + Sb
	31							69		100	✓	Gunmetal + SbPb
	31					5*	64			100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	27									100	✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 12\% \text{ Pb free (564 ppm)}$

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 45\% \text{ Sn free (270 ppm)}$

III constraint : gunmetal with Sn=Zn $\rightarrow 78\% \text{ Sn free (467 ppm)}$

* If contained in the copper alloy \rightarrow leaded brass, leaded bronze, leaded gunmetal.

Com47 – Correlations Cu/Sb (0.97), SnPb, orange group lead antimonates ($\text{Sb}_{33}\text{Pb}_{67}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	1427	161	72	1473	2927	6060					
	Sn		Pb									
	Cu		Sb									
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 161 ppm Zn content as “non natural”)	
	$\text{Cu}_{90}\text{Zn}_{10}$	$\text{Cu}_{95}\text{Sn}_5$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{86}\text{Sn}_4\text{Zn}_{10}$	$\text{Cu}_{82}\text{Sn}_9\text{Zn}_9$	$\text{Sn}_2\text{Pb}_{98}$		$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{33}\text{Pb}_{67}$			
Unalloyed	24					49				24 97	x 161 ppm Zn	Unalloyed Cu + SnPb + Sb
	24						48			24 96	x 72 ppm Sn + 161 ppm Zn	Unalloyed Cu + Pb + Sb
	24							73		96	x 72 ppm Sn + 161 ppm Zn	Unalloyed Cu + SbPb
	24						15 58			96	x 72 ppm Sn + 161 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
Brass	24									97	x 161 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	26					49				24 100	✓	Brass + SnPb + Sb
	26						48			24 99	x 72 ppm Sn	Brass + Pb + Sb
	26							73		99	x 72 ppm Sn	Brass + SbPb
	26					15 58				99	x 72 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	26						16	58		100	✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Bronze	25					49				24 99	x 161 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	25						48			24 97	x 161 ppm Zn	Bronze + Pb + Sb
	25							73		97	x 161 ppm Zn	Bronze + SbPb
	25					15 58				97	x 161 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	25									99	x 161 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	26									24 -	x -	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + SnPb (free) + Sb
Gunmetal	26						-	58		-	x -	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	27					49				24 101	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	27						48			24 100	✓	Gunmetal + Pb + Sb
	27							73		100	✓	Gunmetal + SbPb
	27					15 58				100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
											x	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
					29		-	58				

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 31\% \text{ Pb free (893 ppm)}$

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 121\% \text{ less Sn (87 ppm missing)}$

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 124\% \text{ less Sn (89 ppm missing)}$

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com48 – Correlation SnPb.

I constraint Sb₄₂Pb₅₈ → 99% Pb free (23304 ppm)

II constraint Cu₉₀Sn₁₀ → 87% Sn free (5639 ppm)

III constraint : gunmetal with Sn=Zn → 62% Sn free (4051 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com50 – Correlations Cu/Sb (0.93), strong SnPb, orange group lead antimonates ($\text{Sb}_{32}\text{Pb}_{68}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total				
		Blue-green	2175	182	691	2346	4972	10366				
Pb												
Sn												
		Cu			Sb							
		Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 182 ppm Zn content as “non natural”)	
$\text{Cu}_{92}\text{Zn}_8$ $\text{Cu}_{76}\text{Sn}_{24}$ $\text{Cu}_{90}\text{Sn}_{10}$ $\text{Cu}_{71}\text{Sn}_{23}\text{Zn}_6$ $\text{Cu}_{86}\text{Sn}_7\text{Zn}_7$ $\text{Sn}_{12}\text{Pb}_{88}$												
Unalloyed	21				55				23	98	x 182 ppm Zn x 691 ppm Sn + 182 ppm Zn x 691 ppm Sn + 182 ppm Zn x 691 ppm Sn + 182 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	21						48		23	92		
	21							71		92		
	21					17	54			92		
	21										Sn₂₉Pb₇₁	
Brass	23				55				23	100	x 182 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	23						48		23	93	✓	Brass + SnPb + Sb
	23							71		93	x 691 ppm Sn	Brass + Pb + Sb
	23					17*	54			93	x 691 ppm Sn	Brass + SbPb
	23				23		54			100	x 691 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Bronze	28				55				23	105	x 182 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	28						48		23	98	x 182 ppm Zn	Bronze + Pb + Sb
	28							71		98	x 182 ppm Zn	Bronze + SbPb
	28					17*	54			98	x 182 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	28										Sn₂₉Pb₇₁	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Gunmetal	23										x 182 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	23										x 182 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	21				29		55				✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	21				29						✓	Gunmetal + Pb + Sb
	21				29						✓	Gunmetal + SbPb
	21				29						✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	21										✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	21											

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 35\% \text{ Pb free}$ (564 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 65\% \text{ Sn free}$ (270 ppm)

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 74\% \text{ Sn free}$ (467 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com51 – Correlations Cu/Sb (0.86), SnPb, orange group lead antimonates ($\text{Sb}_{34}\text{Pb}_{66}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total
		Blue-green	2160	285	446	2506	4787	10183
Pb								
Sn								
Cu								
Brass Bronze Gunmetal								
$\text{Cu}_{88}\text{Zn}_{12}$ $\text{Cu}_{83}\text{Sn}_{17}$ $\text{Cu}_{90}\text{Sn}_{10}$ $\text{Cu}_{75}\text{Sn}_{15}\text{Zn}_{10}$ $\text{Cu}_{79}\text{Sn}_{10}\text{Zn}_{10}$ $\text{Sn}_{9}\text{Pb}_{91}$ SnPb free Pb $\text{Sb}_{42}\text{Pb}_{58}$ SbPb Sb Tot								
Unalloyed	21		51			25	97	x 285 ppm Zn
	21			47		25	93	x 446 ppm Sn + 285 ppm Zn
	21				72	93	x 446 ppm Sn + 285 ppm Zn	Unalloyed Cu + SbPb
	21			13	59	93	x 446 ppm Sn + 285 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	21							Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Brass	24		51			25	100	✓
	24			47		25	96	x 446 ppm Sn
	24				72	96	x 446 ppm Sn	Brass + SbPb
	24			13	59	96	x 446 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	24			17	59	100	✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Bronze	26		51			25	102	x 285 ppm Zn [Sn counted twice]
	26			47		25	97	x 285 ppm Zn
	26				72	97	x 285 ppm Zn	Bronze + SbPb
	26			13	59	97	x 285 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	26					102	x 285 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Gunmetal	24							Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	24							Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	28		51			25	104	✓ [Sn counted twice]
	28			47		25	100	✓
	28				72	100	✓	Gunmetal + SbPb
	28			13	59	100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
								Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
			27					

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow$ 28% Pb free (1326 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow$ 46% Sn free (206 ppm)

III constraint : gunmetal with Sn=Zn \rightarrow 36% Sn free (160 ppm)

* If contained in the copper alloy \rightarrow leaded brass, leaded bronze, leaded gunmetal.

Com52 – Correlations SnPb, red group lead antimonates ($\text{Sb}_{26}\text{Pb}_{74}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total						
	Blue-green	3709	364	840	2775	7795	15484						
	Pb												
	Sn												
	Cu		Sb										
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 364 ppm Zn content as “non natural”)		
	$\text{Cu}_{91}\text{Zn}_9$	$\text{Cu}_{82}\text{Sn}_{18}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{75}\text{Sn}_{17}\text{Zn}_7$	$\text{Cu}_{84}\text{Sn}_8\text{Zn}_8$	$\text{Sn}_{10}\text{Pb}_{90}$		$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{26}\text{Pb}_{74}$				
24						56				18 98	x 364 ppm Zn	Unalloyed Cu + SnPb + Sb	
24							50			18 92	x 840 ppm Sn + 364 ppm Zn	Unalloyed Cu + Pb + Sb	
24								68		92	x 840 ppm Sn + 364 ppm Zn	Unalloyed Cu + SbPb	
24						26	43			92	x 840 ppm Sn + 364 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)	
24									31	43			
Brass	26					56				98	x 364 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
	26						50			18 100	✓	Brass + SnPb + Sb	
	26							68		18 95	x 840 ppm Sn	Brass + Pb + Sb	
	26					26*	43			95	x 840 ppm Sn	Brass + SbPb	
	26						31	43		100	x 840 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
											✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
Bronze	29					56				18 103	x 364 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb	
	29						50			18 98	x 364 ppm Zn	Bronze + Pb + Sb	
	29							68		98	x 364 ppm Zn	Bronze + SbPb	
	29					26*	43			98	x 364 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
	29								31	43	103	x 364 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	27								53		18 98	x 364 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	27									98	x 364 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
Gunmetal	32					56				18 105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb	
	32						50			18 100	✓	Gunmetal + Pb + Sb	
	32							68		100	✓	Gunmetal + SbPb	
	32					26*	43			100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
									29	43	100	✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 51\% \text{ Pb free}$ (3963 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 51\% \text{ Sn free}$ (428 ppm)

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 57\% \text{ Sn free}$ (476 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com54 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Blue-green	6950	161	158	2634	17452	27355		
	Pb								
	Sn								
	Cu								
Unalloyed	Cu Cu ₉₈ Zn ₂	Brass Cu ₉₈ Sn ₂	Bronze Cu ₉₀ Sn ₁₀	Gunmetal Cu ₉₆ Sn ₂ Zn ₂	SnPb Sn ₁ Pb ₉₉	SnPb free Sb ₄₂ Pb ₅₈	Pb Sb ₄₂ Pb ₅₈	SbPb Sb ₁₃ Pb ₈₇	Unexplained (considering 161 ppm Zn content as “non natural”)
25				64			10	99	x 161 ppm Zn Unalloyed Cu + SnPb + Sb
25					64		10	99	x 158 ppm Sn + 161 ppm Zn Unalloyed Cu + Pb + Sb
25						73		99	x 158 ppm Sn + 161 ppm Zn Unalloyed Cu + SbPb
25					51	23		99	x 158 ppm Sn + 161 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
25							99		x 161 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	26			64			10	100	✓ Brass + SnPb + Sb
26					64		10	99	x 158 ppm Sn Brass + Pb + Sb
26						73		99	x 158 ppm Sn Brass + SbPb
26					51*	23		99	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
26							100		Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	26			64			10	100	x 161 ppm Zn [Sn counted twice] Bronze + SnPb + Sb
26					64		10	99	x 161 ppm Zn Bronze + Pb + Sb
26						73		99	x 161 ppm Zn Bronze + SbPb
26					50*	23		99	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26						100		Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	28								Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	28						10	-	x -
Gunmetal	27			64			10	101	✓ [Sn counted twice] Gunmetal + SnPb + Sb
27					64		10	100	✓ Gunmetal + Pb + Sb
27						73		100	✓ Gunmetal + SbPb
27					50*	23		100	✓ Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	27								Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 79% Pb free (13814 ppm)

II constraint Cu₉₀Sn₁₀ → 8% less Sn (615 ppm missing)

III constraint : gunmetal with Sn=Zn → equal

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com55 – Correlations SnPb, yellow group lead antimonates ($\text{Sb}_{45}\text{Pb}_{55}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Blue-green	216	206	106	788	979	2295	
		Pb						
		Sn						
		Cu						
		Brass Bronze Gunmetal						
		$\text{Cu}_{51}\text{Zn}_{49}$ $\text{Cu}_{67}\text{Sn}_{33}$ $\text{Cu}_{90}\text{Sn}_{10}$ $\text{Cu}_{41}\text{Sn}_{20}\text{Zn}_{39}$ $\text{Cu}_{34}\text{Sn}_{33}\text{Zn}_{33}$ $\text{Sn}_{10}\text{Pb}_{90}$						
		SnPb SnPb free Pb $\text{Sb}_{42}\text{Pb}_{58}$ SbPb Sb Tot						
		$\text{Sb}_{42}\text{Pb}_{58}$ $\text{Sb}_{45}\text{Pb}_{55}$						
Unalloyed	9		47		34	91	x 206 ppm Zn	Unalloyed Cu + SnPb + Sb
	9			43	34	86	x 106 ppm Sn + 206 ppm Zn	Unalloyed Cu + Pb + Sb
	9				77	86	x 106 ppm Sn + 206 ppm Zn	Unalloyed Cu + SbPb
	9			- Low Pb		86	x -	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	9							
Brass	18		47	-	Low Pb	91	x -	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	18			43		34 100	✓	Brass + SnPb + Sb
	18				77	34 95	x 106 ppm Sn	Brass + Pb + Sb
	18			- Low Pb		95	x 106 ppm Sn	Brass + SbPb
	18			- Low Pb		95	x -	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Bronze	14		47		34 96	x 206 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb	
	14			43	34 91	x 206 ppm Zn	Bronze + Pb + Sb	
	14				77	91	x 206 ppm Zn	Bronze + SbPb
	14			- Low Pb		91	x -	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	14			-	Low Pb	96	x -	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Gunmetal	10			46	34 91	x 206 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb	
	10			Low Sn				
	23		47	-	Low Pb	91	x -	Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	23			43	34 105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb	
	23				34 100	✓	Gunmetal + Pb + Sb	
	23			- Low Pb	77	100	✓	Gunmetal + SbPb
	23			- Low Pb		100	x -	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	27		-	Low Pb		100	x -	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 11\% \text{ Pb less}$ (109 ppm missing)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 77\% \text{ Sn free}$ (82 ppm)

III constraint : gunmetal with Sn=Zn $\rightarrow 94\% \text{ Sn less}$ (100 ppm missing)

* If contained in the copper alloy \rightarrow leaded brass, leaded bronze, leaded gunmetal.

Com58 – Correlations SnPb, yellow group lead antimonates ($\text{Sb}_{45}\text{Pb}_{55}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Blue-green	256	153	354	590	805	2157				
				Pb							
			Sn								
		Cu			Sb						
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 153 ppm Zn content as “non natural”)	
	$\text{Cu}_{63}\text{Zn}_{37}$	$\text{Cu}_{42}\text{Sn}_{58}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{34}\text{Sn}_{46}\text{Zn}_{20}$	$\text{Cu}_{46}\text{Sn}_{27}\text{Zn}_{27}$	$\text{Sn}_{31}\text{Pb}_{69}$	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{42}\text{Pb}_{58}$			
Unalloyed	12				54			27	93	x 153 ppm Zn x 354 ppm Sn + 153 ppm Zn x 354 ppm Sn + 153 ppm Zn x 354 ppm Sn + 153 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	12					37		27	76		
	12						65	76			
	12					-	65	77			
	12										
Brass	19				54			27	100	✓	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	19					37		27	84	x 354 ppm Sn	Brass + SnPb + Sb
	19						65	84		x 354 ppm Sn	Brass + Pb + Sb
	19					-	65	84		x 354 ppm Sn	Brass + SbPb
	19				16		65	100		✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	19										Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Bronze	28				54			27	109	x 153 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	28					37		27	93	x 153 ppm Zn	Bronze + Pb + Sb
	28						65	93		x 153 ppm Zn	Bronze + SbPb
	28					-	65	93		x 153 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	28									x -	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	13				52			27	93	x 153 ppm Zn	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + SnPb (free) + Sb
Gunmetal	13					Low Pb				x -	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	35				54			27	116	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	35					37		27	100	✓	Gunmetal + Pb + Sb
	35						65	100	✓	Gunmetal + SbPb	
	35					-	65	100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
	26									x -	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 0\%$ Pb free

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 92\%$ Sn free (326 ppm)

III constraint : gunmetal with Sn=Zn $\rightarrow 57\%$ Sn free (202 ppm)

* If contained in the copper alloy \rightarrow leaded brass, leaded bronze, leaded gunmetal.

Com61 – Correlations Cu/Sb (0.94), strong SnPb, red group lead antimonates ($\text{Sb}_{31}\text{Pb}_{69}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	2003	104	630	2126	5508	10371					
Pb												
Sn												
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 104 ppm Zn content as “non natural”)	
$\text{Cu}_{95}\text{Zn}_5$ $\text{Cu}_{76}\text{Sn}_{24}$ $\text{Cu}_{90}\text{Sn}_{10}$ $\text{Cu}_{73}\text{Sn}_{23}\text{Zn}_4$ $\text{Cu}_{91}\text{Sn}_5\text{Zn}_5$ $\text{Sn}_{10}\text{Pb}_{90}$ $\text{Sb}_{42}\text{Pb}_{58}$ $\text{Sb}_{28}\text{Pb}_{72}$												
Unalloyed	19				59			20	99		x 104 ppm Zn x 630 ppm Sn + 104 ppm Zn x 630 ppm Sn + 104 ppm Zn x 630 ppm Sn + 104 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	19					53		20	93			
	19						74	93				
	19				25	49		93				
Brass	19											
	20				59			20	100	✓	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
	20					53		20	94	x 630 ppm Sn	Brass + SnPb + Sb	
	20						74	94		x 630 ppm Sn	Brass + Pb + Sb	
	20				25*	49		94		x 630 ppm Sn	Brass + SbPb	
Bronze	20					31		100			Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
	25				59						Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)	
	25					53						
	25						74					
	25				25*	49						
	25					31						
Gunmetal	21											
	21				59			20	105	x 104 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb	
	26					53		20	99	x 104 ppm Zn	Bronze + Pb + Sb	
	26						74	99		x 104 ppm Zn	Bronze + SbPb	
	26				25*	49		99		x 104 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)	
	21											
$\text{Sn}_{20}\text{Pb}_{80}$ $\text{Sn}_{7}\text{Pb}_{93}$ $\text{Sn}_{14}\text{Pb}_{86}$ $\text{Sn}_{17}\text{Pb}_{83}$												
21												
30												
49												
100												
✓												
Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)												

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 47\% \text{ Pb free}$ (2572 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 65\% \text{ Sn free}$ (408 ppm)

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 83\% \text{ Sn free}$ (526 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com64 – Correlations strong SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total	
		Blue-green	203	198	152	106	834	1494	
Pb									
Sn									
		Cu			Sb				
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
Unalloyed copper	Cu ₅₁ Zn ₄₉	Cu ₅₇ Sn ₄₃	Cu ₉₀ Sn ₁₀	Cu ₃₇ Sn ₂₈ Zn ₃₆	Cu ₃₄ Sn ₃₃ Zn ₃₃	Sn ₁₅ Pb ₈₅		Sb ₄₂ Pb ₅₈	Sb ₁₁ Pb ₈₉
	14					66			7 87
	14						56		7 77
	14							63	77
	14					46	17		77
Brass									Sn ₁₈ Pb ₈₂
	14						56		87
	27					66			✓ 198 ppm Zn
	27						56		7 100
	27							63	7 90
Bronze	27						46*	17	90
	27						56		90
	24					66			✓ 198 ppm Zn
	24						56		7 97
	24							63	7 87
Gummetal	24						46*	17	87
	24								✓ 198 ppm Zn [Sn counted twice]
	15								✓ 198 ppm Zn
	15								✓ 198 ppm Zn
	37					66			✓ 198 ppm Zn
unreliable									
Unexplained (considering 198 ppm Zn content as “non natural”)									
Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)									
Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free) Brass + SnPb + Sb Brass + Pb + Sb Brass + SbPb Brass + Sb ₄₂ Pb ₅₈ + *Pb (free) Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)									
Bronze + SnPb + Sb Bronze + Pb + Sb Bronze + SbPb Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free) Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)									
Bronze + SnPb + Sb Bronze + Pb + Sb Bronze + SbPb Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free) Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)									
Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)									
Gunmetal + SnPb + Sb Gunmetal + Pb + Sb Gunmetal + SbPb Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)									
Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)									

I constraint Sb₄₂Pb₅₈ → 82% Pb free (687 ppm)

II constraint Cu₉₀Sn₁₀ → 85% Sn free (130 ppm)

III constraint : gunmetal with Sn=Zn → unreliable

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com65 – Correlations strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Blue-green	189	364	193	86	1283	2116		
	Pb								
	Sn								
	Cu								
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈ SbPb Sb Tot	Unexplained (considering 364 ppm Zn content as “non natural”)
	Cu ₃₄ Zn ₆₆	Cu ₄₉ Sn ₅₁	Cu ₉₀ Sn ₁₀	Cu ₂₅ Sn ₂₆ Zn ₄₉	Cu ₂₁ Sn ₄₀ Zn ₄₀	Sn ₁₃ Pb ₈₇		Sb ₄₂ Pb ₅₈ Sb ₆ Pb ₉₄	
9					70			4 83	x 364 ppm Zn Unalloyed Cu + SnPb + Sb
9						61		4 74	x 193 ppm Sn + 364 ppm Zn Unalloyed Cu + Pb + Sb
9							65	74	x 193 ppm Sn + 364 ppm Zn Unalloyed Cu + SbPb
9						55	10	74	x 193 ppm Sn + 364 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
9									
Brass						Sn ₁₄ Pb ₈₆			
	26				70	64	10	83	x 364 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
26						61		4 100 ✓	Brass + SnPb + Sb
26							65	4 91	x 193 ppm Sn Brass + Pb + Sb
26						55*	10	91	x 193 ppm Sn Brass + SbPb
26						64	10	91	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
								100	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze					18	70		4 92	x 364 ppm Zn [Sn counted twice] Bronze + SnPb + Sb
					18		61	4 83	x 364 ppm Zn Bronze + Pb + Sb
					18			83	x 364 ppm Zn Bronze + SbPb
					18	55*	10	83	x 364 ppm Zn Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
					18	Sn ₁₄ Pb ₈₆	10	92	x 364 ppm Zn [Sn counted twice] Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
					10	Sn ₁₂ Pb ₈₈		4 83	x 364 ppm Zn Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
					10	Sn ₁₃ Pb ₈₇		83	x 364 ppm Zn Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal					35	70		4 109 ✓ [Sn counted twice]	Gunmetal + SnPb + Sb
					35		61	4 100 ✓	Gunmetal + Pb + Sb
					35			100	✓ Gunmetal + SbPb
					35	55*	10	100	✓ Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
						Unreliable		x	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 91% Pb free (1164 ppm)

II constraint Cu₉₀Sn₁₀ → 89% Sn free (172 ppm)

III constraint : gunmetal with Sn=Zn → unreliable, not calculated

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com66 – Correlation SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total			
		Blue-green	2184	506	2833	1039	12755	19316			
Pb											
Sn											
Cu		Sb									
Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 158 ppm Zn content as “non natural”)	
Cu ₈₁ Zn ₁₉	Cu ₄₄ Sn ₅₆	Cu ₉₀ Sn ₁₀	Cu ₄₀ Sn ₅₁ Zn ₉	Cu ₆₈ Sn ₁₆ Zn ₁₆	Sn ₁₈ Pb ₈₂		Sb ₄₂ Pb ₅₈	Sb ₈ Pb ₉₂			
11					81				5 97	x 506 ppm Zn	Unalloyed Cu + SnPb + Sb
11						66			5 83	x 2833 ppm Sn + 506 ppm Zn	Unalloyed Cu + Pb + Sb
11							71		83	x 2833 ppm Sn + 506 ppm Zn	Unalloyed Cu + SbPb
11						59	13		83	x 2833 ppm Sn + 506 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Sn ₂₀ Pb ₈₀											
11					73	13			97	x 506 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
14					81				5 100	✓	Brass + SnPb + Sb
14						66			5 85	x 2833 ppm Sn	Brass + Pb + Sb
14							71		85	x 2833 ppm Sn	Brass + SbPb
14						59*	13		85	x 2833 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
14					73	13			100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Sn ₂₀ Pb ₈₀											
26					81				5 112	x 506 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
26						66			5 97	x 506 ppm Zn	Bronze + Pb + Sb
26							71		97	x 506 ppm Zn	Bronze + SbPb
26						59*	13		97	x 506 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
Sn ₁₇ Pb ₈₃											
26					73	13			112	x 506 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
13					79				5 97	x 506 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
Sn ₁₉ Pb ₈₁											
13					72	13			97	x 506 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
Sn ₁₇ Pb ₈₃											
29					81				5 115	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
29						66			5 100	✓	Gunmetal + Pb + Sb
29							71		100	✓	Gunmetal + SbPb
29						59*	13		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
Sn ₁₇ Pb ₈₃											
17					71	13			100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 89% Pb free (11321 ppm)

II constraint Cu₉₀Sn₁₀ → 91% Sn free (2590 ppm)

III constraint : gunmetal with Sn=Zn → 82% Sn free (2327 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com71 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	1877	246	112	6927	1745	10907					
Pb												
Sn												
	Cu			Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb	Tot	Unexplained (considering 246 ppm Zn content as “non natural”)
<chem>Cu88Zn12</chem> <chem>Cu94Sn6</chem> <chem>Cu90Sn10</chem> <chem>Cu84Sn5Zn11</chem> <chem>Cu79Sn10Zn10</chem> <chem>Sn6Pb94</chem>								<chem>Sb42Pb58</chem>	<chem>Sb80Pb20</chem>			
Unalloyed	17				17			64	98	x	246 ppm Zn	Unalloyed Cu + SnPb + Sb
	17					16		64	97	x	112 ppm Sn + 246 ppm Zn	Unalloyed Cu + Pb + Sb
	17						80		97	x	112 ppm Sn + 246 ppm Zn	Unalloyed Cu + SbPb
	17				16	Low Pb		-		x	-	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Brass	17					Low Sn	Low Pb	-		x	-	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	19				17			64	100	✓		Brass + SnPb + Sb
	19					16		64	99	x	112 ppm Sn	Brass + Pb + Sb
	19						80		99	x	112 ppm Sn	Brass + SbPb
	19				16*	Low Pb	Low Pb	-		x	-	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Bronze	18				17			64	99	x	246 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	18					16		64	98	x	246 ppm Zn	Bronze + Pb + Sb
	18						80		98	x	246 ppm Zn	Bronze + SbPb
	18				16*	Low Pb		-		x	-	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	18					Low Sn	Low Pb	-		x	-	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	19					Low Sn	Low Sn	64	-	x	-	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	19						Low Sn	-		x	-	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	20				17			64	101	✓	[Sn counted twice]	Gunmetal + SnPb + Sb
	20					16		64	100	✓		Gunmetal + Pb + Sb
	20						80		100	✓		Gunmetal + SbPb
	20				16*	Low Pb		100		x		Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	22					Sn	Low Pb	-		x	-	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 448% less Pb (7820 ppm missing)

II constraint Cu₉₀Sn₁₀ → 87% less Sn (97 ppm missing)

III constraint : gunmetal with Sn=Zn → 120% less Sn (135 ppm missing)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com72 – Correlations Cu/Sb (1.05), strong SnPb, red group lead antimonates ($\text{Sb}_{31}\text{Pb}_{69}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total								
	Blue-green	2932	142	872	2795	6269	13010								
	Pb														
	Sn														
	Cu		Sb												
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{21}\text{Pb}_{73}$	$\text{Sb}_{31}\text{Pb}_{69}$	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{31}\text{Pb}_{69}$	Sb Tot	Unexplained (considering 142 ppm Zn content as “non natural”)	
	$\text{Cu}_{95}\text{Zn}_5$	$\text{Cu}_{77}\text{Sn}_{23}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{74}\text{Sn}_{22}\text{Zn}_4$	$\text{Cu}_{91}\text{Sn}_4\text{Zn}_4$	$\text{Sn}_{12}\text{Pb}_{88}$									
23							55				21	99		x 142 ppm Zn	Unalloyed Cu + SnPb + Sb
23								48			21	92		x 872 ppm Sn + 142 ppm Zn	Unalloyed Cu + Pb + Sb
23									70			92		x 872 ppm Sn + 142 ppm Zn	Unalloyed Cu + SbPb
23								19	51			92		x 872 ppm Sn + 142 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
										$\text{Sn}_{27}\text{Pb}_{73}$					
23								25		51		99		x 142 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Brass	24						55				21	100	✓		Brass + SnPb + Sb
	24							48			21	93		x 872 ppm Sn	Brass + Pb + Sb
	24								70			93		x 872 ppm Sn	Brass + SbPb
	24						19*	51				93		x 872 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	24						25		51			100		✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Bronze	29						55				21	106		x 142 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	29							48			21	99		x 142 ppm Zn	Bronze + Pb + Sb
	29								70			99		x 142 ppm Zn	Bronze + SbPb
	29						19*	51				99		x 142 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	29								$\text{Sn}_{27}\text{Pb}_{73}$						
	29						25		51			106		x 142 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	25							52			21	99		x 142 ppm Zn	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + SnPb (free) + Sb
Gunmetal	25							$\text{Sn}_{18}\text{Pb}_{82}$		51		99		x 142 ppm Zn	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
							30		55			21	107	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
							30			48		21	100	✓	Gunmetal + Pb + Sb
							30				70		100	✓	Gunmetal + SbPb
							30		19*	51			100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
									$\text{Sn}_{23}\text{Pb}_{77}$						
							25		24		51		100	✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 38\% \text{ Pb free}$ (2409 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 63\% \text{ Sn free}$ (546 ppm)

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 84\% \text{ Sn free}$ (730 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com73 – Correlations Cu/Sb (1.02), SnPb, orange group lead antimonates ($\text{Sb}_{36}\text{Pb}_{64}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	2134	214	348	2083	3774	8554					
	Pb											
	Sn				Pb							
	Cu		Sb									
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 214 ppm Zn content as “non natural”)	
								$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{36}\text{Pb}_{64}$			
Unalloyed	25				48			24	97		x 214 ppm Zn x 348 ppm Sn + 214 ppm Zn x 348 ppm Sn + 214 ppm Zn x 348 ppm Sn + 214 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	25					44		24	93			
	25						68	93				
	25				11	58		93				
	25											
Brass	25							97			x 214 ppm Zn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	27				48			24	100		✓	Brass + SnPb + Sb
	27					44		24	96		x 348 ppm Sn	Brass + Pb + Sb
	27						68	96			x 348 ppm Sn	Brass + SbPb
	27				11*	58		96			x 348 ppm Sn	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Bronze	27				15	58		100			✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	29				48			24	102		x 214 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	29					44		24	97		x 214 ppm Zn	Bronze + Pb + Sb
	29						68	97			x 214 ppm Zn	Bronze + SbPb
	29				10*	58		97			x 214 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
Gunmetal	29							102			x 214 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	28											Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	28											Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	32				48			24	104		✓ Sn counted twice	Gunmetal + SnPb + Sb
	32					44		24	100		✓	Gunmetal + Pb + Sb
	32						68	100			✓	Gunmetal + SbPb
	32				10*	58		100			✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	30							100			✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	12											
	58											

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 24\% \text{ Pb free (897 ppm)}$

II constraint Cu₉₀Sn₁₀ → 32% Sn free (111 ppm)

III constraint : gunmetal with Sn=Zn → 39% Sn free (134 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com77 – Correlations Cu/Sb (0.88), SnPb, red group lead antimonates ($\text{Sb}_{28}\text{Pb}_{72}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total
	Blue-green	1677	252	359	1896	4902	9085
Pb							
Sn							
Cu							
Gunmetal							
SnPb SnPb free Pb $\text{Sb}_{42}\text{Pb}_{58}$ SbPb Sb Tot							
$\text{Sn}_7\text{Pb}_{93}$ $\text{Sb}_{42}\text{Pb}_{58}$ $\text{Sb}_{28}\text{Pb}_{72}$							
Unalloyed	18		58		21	97	
	18			54	21	93	
	18				75	93	
	18			25	50	93	
	18						
Brass	21		58		21	100	✓
	21			54	21	96	
	21				75	96	
	21			25*	50	96	
	21					100	✓
Bronze	22		58		21	101	
	22			54	21	97	
	22				75	97	
	22			25*	50	97	
	22						
Gunmetal	21		56		21	97	
	21			$\text{Sn}_3\text{Pb}_{97}$	21	97	
	21			$\text{Sn}_7\text{Pb}_{93}$	27	50	
	25		58		21	104	✓ [Sn counted twice]
	25			54	21	100	✓
	25				75	100	✓
	25			25*	50	100	✓
	24			$\text{Sn}_4\text{Pb}_{96}$		100	✓
Unexplained (considering 252 ppm Zn content as “non natural”)							
X 252 ppm Zn							
X 359 ppm Sn + 252 ppm Zn							
X 359 ppm Sn + 252 ppm Zn							
X 359 ppm Sn + 252 ppm Zn							
Unalloyed Cu + SnPb + Sb							
Unalloyed Cu + Pb + Sb							
Unalloyed Cu + SbPb							
Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)							
Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)							
Brass + SnPb + Sb							
Brass + Pb + Sb							
Brass + SbPb							
Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)							
Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)							
Bronze + SnPb + Sb							
Bronze + Pb + Sb							
Bronze + SbPb							
Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)							
Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)							
Bronze + SnPb + Sb							
Bronze + Pb + Sb							
Bronze + SbPb							
Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)							
Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb							
Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)							
Gunmetal + SnPb + Sb							
Gunmetal + Pb + Sb							
Gunmetal + SbPb							
Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)							
Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)							

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 47\% \text{ Pb free (2284 ppm)}$

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 48\% \text{ Sn free (172 ppm)}$

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 30\% \text{ Sn free (107 ppm)}$

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com78 – Correlations Cu/Sb (0.85), SnPb, orange correlation lead antimonates ($\text{Sb}_{38}\text{Pb}_{62}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Blue-green	2259	222	396	2666	4426	9969				
	Pb										
	Sn										
	Cu		Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	$\text{Sb}_{42}\text{Pb}_{58}$	SbPb	Sb Tot	Unexplained (considering 222 ppm Zn content as “non natural”)	
	$\text{Cu}_{91}\text{Zn}_9$	$\text{Cu}_{85}\text{Sn}_{15}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Cu}_{79}\text{Sn}_{14}\text{Zn}_8$	$\text{Cu}_{84}\text{Sn}_8\text{Zn}_8$	$\text{Sn}_8\text{Pb}_{92}$	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{38}\text{Pb}_{62}$			
Unalloyed	23					48			27 98	x 222 ppm Zn x 396 ppm Sn + 222 ppm Zn x 396 ppm Sn + 222 ppm Zn x 396 ppm Sn + 222 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
	23						44		27 94		
	23							71	94		
	23					7	64		94		
Brass	23										
	25										
	25										
	25										
	25										
Bronze	27					48			27 100	✓	
	27						44		27 96	x 396 ppm Sn	Brass + SnPb + Sb
	27							71	96	x 396 ppm Sn	Brass + Pb + Sb
	27					7*	64		96	x 396 ppm Sn	Brass + SbPb
	27					11	64		100	✓	Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free) Brass + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
Gunmetal	27					48			27 102	x 222 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	27						44		27 98	x 222 ppm Zn	Bronze + Pb + Sb
	27							71	98	x 222 ppm Zn	Bronze + SbPb
	27					7*	64		98	x 222 ppm Zn	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	27								102	x 222 ppm Zn [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	25										Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	25										
	25										
	25										
	25										Bronze Cu ₉₀ Sn ₁₀ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	29					48			27 104	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	29						44		27 100	✓	Gunmetal + Pb + Sb
	29							71	100	✓	Gunmetal + SbPb
	29					7*	64		100	✓	Gunmetal + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	27								100	✓	Gunmetal calc. + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 17\% \text{ Pb free (744 ppm)}$

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 37\% \text{ Sn free (145 ppm)}$

III constraint : gunmetal with $\text{Sn}=\text{Zn} \rightarrow 44\% \text{ Sn free (174 ppm)}$

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com80 – Correlations Cu/Sb (0.80), SnPb, orange group lead antimonates ($\text{Sb}_{36}\text{Pb}_{64}$).

		Colour	Cu	Zn	Sn	Sb	Pb	Total	
		Blue-green	565	75	278	711	1245	2874	
			Pb						
			Sn						
		Cu	Sb						
	Cu	Brass	SnPb	SnPb free	Pb	$\text{Sb}_{42}\text{Pb}_{58}$	Sb_{Pb}	Sb Tot	
	Bronze	$\text{Cu}_{67}\text{Sn}_{33}$	$\text{Cu}_{90}\text{Sn}_{10}$	$\text{Sn}_{18}\text{Pb}_{82}$	$\text{Sb}_{42}\text{Pb}_{58}$	$\text{Sb}_{36}\text{Pb}_{64}$			
Unalloyed	20			54			25	100 ✓	Unalloyed Cu + SnPb + Sb
	20				44		25	90 ✗ 278 ppm Sn	Unalloyed Cu + Pb + Sb
	20					70	90	✗ 278 ppm Sn	Unalloyed Cu + SbPb
	20			9	60		90	✗ 278 ppm Sn	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + Pb (free)
Bronze	20			$\text{Sn}_{51}\text{Pb}_{49}$	19	60	100	✓	Unalloyed Cu + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	30			54			25	110 ✓ [Sn counted twice]	Bronze + SnPb + Sb
	30				44		25	100 ✓	Bronze + Pb + Sb
	30					70	100	✓	Bronze + SbPb
	30			9	60		100	✓	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + *Pb (free)
	30			$\text{Sn}_{51}\text{Pb}_{49}$	19	60	110	✓ [Sn counted twice]	Bronze + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)
	22			$\text{Sn}_{15}\text{Pb}_{85}$	52		25	100 ✓	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + SnPb (free) + Sb
	22			$\text{Sn}_{45}\text{Pb}_{55}$	17	60	100	✓	Bronze $\text{Cu}_{90}\text{Sn}_{10}$ + $\text{Sb}_{42}\text{Pb}_{58}$ + SnPb (free)

I constraint $\text{Sb}_{42}\text{Pb}_{58} \rightarrow 21\% \text{ Pb free}$ (263 ppm)

II constraint $\text{Cu}_{90}\text{Sn}_{10} \rightarrow 77\% \text{ Sn free}$ (215 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com82 – Correlations Cu/Sb (1.20), SnPb, red group lead antimonates ($\text{Sb}_{23}\text{Pb}_{77}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Blue-green	730	220	183	609	2081	3824					
Pb												
Sn												
	Cu			Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 220 ppm Zn content as “non natural”)		
<chem>Cu77Zn23</chem> <chem>Cu80Sn20</chem> <chem>Cu90Sn10</chem> <chem>Cu64Sn16Zn19</chem> <chem>Cu62Sn19Zn19</chem> <chem>Sn8Pb92</chem> <chem>Sn42Pb58</chem> <chem>Sn23Pb77</chem>												
Unalloyed	19				59				16 94	x 220 ppm Zn	Unalloyed Cu + SnPb + Sb	
	19					54			16 89	x 183 ppm Sn + 220 ppm Zn	Unalloyed Cu + Pb + Sb	
	19						70		89	x 183 ppm Sn + 220 ppm Zn	Unalloyed Cu + SbPb	
	19					32 38			89	x 183 ppm Sn + 220 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
	19				Sn ₁₃ Pb ₈₇	37	38		94	x 220 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Brass	25				59				16 100	✓	Brass + SnPb + Sb	
	25					54			16 95	x 183 ppm Sn	Brass + Pb + Sb	
	25						70		95	x 183 ppm Sn	Brass + SbPb	
	25					32 38			95	x 183 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	25				37	38			100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Bronze	24				59				16 99	x 220 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb	
	24					54			16 94	x 220 ppm Zn	Bronze + Pb + Sb	
	24						70		94	x 220 ppm Zn	Bronze + SbPb	
	24					32 38			94	x 220 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	24				Sn ₁₃ Pb ₈₇	37	38		99	x 220 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Gunmetal	21					Sn ₂ Pb ₉₅	57		16 94	x 220 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb	
	21					Sn ₈ Pb ₉₂		38		94	x 220 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	30				59				16 105	✓ [Sn counted twice]	Gunmetal + SnPb + Sb	
	30					54			16 100	✓	Gunmetal + Pb + Sb	
	30						70		100	✓	Gunmetal + SbPb	
	30					32 38			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)	
Low Sn												
	31				-		38		-	x -	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)	

I constraint Sb₄₂Pb₅₈ → 60% Pb free (1240 ppm)

II constraint Cu₉₀Sn₁₀ → 56% Sn free (102 ppm)

III constraint : gunmetal with Sn=Zn → 20% Sn less (36 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com89 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Blue-green	1679	1154	741	36	1646	5257	
	Pb							
	Sn							
	Cu		Sb					
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
Unalloyed	Cu ₅₉ Zn ₄₁	Cu ₆₉ Sn ₃₁	Cu ₉₀ Sn ₁₀	Cu ₄₇ Sn ₂₁ Zn ₃₂	Cu ₄₂ Sn ₂₉ Zn ₂₉	Sn ₃₁ Pb ₆₉	Sb ₄₂ Pb ₅₈	Sb ₂ Pb ₉₈
	32				45			1 78
	32					31		1 64
	32						32	64
	32					30	2	64
								Sn ₃₂ Pb ₆₈
					44		2	78
	32							x 1154 ppm Zn
Brass	54				45			✓ 100
	54					31		x 741 ppm Sn
	54						32	86
	54					30	2	86
	54				44		2	100
								✓
Bronze	46				45			x 1154 ppm Zn [Sn counted twice]
	46					31		x 1154 ppm Zn
	46						32	78
	46					30	2	78
								Sn ₃₂ Pb ₆₈
					44		2	92
								x 1154 ppm Zn [Sn counted twice]
	46							Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	35					42		1 78
								Sn ₂₅ Pb ₇₅
								Sn ₂₆ Pb ₇₄
					41		2	78
								x 1154 ppm Zn
Gunmetal	35				45			✓ [Sn counted twice]
	68					31		1 114
	68						1 100	✓
	68						100	✓
	68					30	2	100
								Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
			Low Sn		76	-	2	-
								x -
								Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 97% Pb free (1596 ppm)

II constraint Cu₉₀Sn₁₀ → 75% Sn free (555 ppm)

III constraint : gunmetal with Sn=Zn → 56% Sn less (413 ppm missing)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com90 – Correlations SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total				
		Blue dark	2562	150	208	6563	2480	11963				
Pb												
Sn												
		Cu			Sb							
		Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈				
		Cu ₉₄ Zn ₆	Cu ₉₂ Sn ₈	Cu ₉₀ Sn ₁₀	Cu ₈₈ Sn ₇ Zn ₅	Cu ₉₀ Sn ₅ Zn ₅	Sn ₈ Pb ₉₂	Sb ₄₂ Pb ₅₈	Sb ₇₃ Pb ₂₇	Sb Tot	Unexplained (considering 150 ppm Zn content as “non natural”)	
Unalloyed	21				22			55	99		x 150 ppm Zn x 208 ppm Sn + 150 ppm Zn x 208 ppm Sn + 150 ppm Zn x 208 ppm Sn + 150 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	21					21		55	97			
	21						76		97			
	21				-	Low Pb			97			
Brass	21							99		x -	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	23				22			55	100	✓	Brass + SnPb + Sb	
	23					21		55	98	x 208 ppm Sn x 208 ppm Sn	Brass + Pb + Sb	
	23						76		98		Brass + SbPb	
	23				-	Low Pb			98	x -	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	23					Low Pb			100	x -	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Bronze	23				22			55	100	x 150 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb	
	23					21		55	99	x 150 ppm Zn	Bronze + Pb + Sb	
	23						76		99	x 150 ppm Zn	Bronze + SbPb	
	23				-	Low Pb			99	x 150 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	23							100		x -	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	24							55	99	x -	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb	
Gunmetal	24					-	Low Pb		99	x -	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	24				22			55	102	✓ [Sn counted twice]	Gunmetal + SnPb + Sb	
	24					21		55	100	✓	Gunmetal + Pb + Sb	
	24						76		100	✓	Gunmetal + SbPb	
	24				-	Low Pb			100	x -	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	24							100		x -	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)	

I constraint Sb₄₂Pb₅₈ → 265% Pb less (6584 ppm missing)

II constraint Cu₉₀Sn₁₀ → 37% Sn less (77 ppm missing)

III constraint : gunmetal with Sn=Zn → 28% Sn free (58 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com94 – Correlation strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Green olive	4474	905	5883	825	30604	42690					
Pb												
Sn												
	Cu											
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 905 ppm Zn content as “non natural”)	
Unalloyed	Cu ₈₃ Zn ₁₇	Cu ₄₃ Sn ₅₇	Cu ₉₀ Sn ₁₀	Cu ₄₀ Sn ₅₂ Zn ₈	Cu ₇₁ Sn ₁₄ Zn ₁₄	Sn ₁₆ Pb ₈₄		Sb ₄₂ Pb ₅₈	Sb ₃ Pb ₉₇			
	10					85				2 98	x 905 ppm Zn	Unalloyed Cu + SnPb + Sb
	10						72			2 84	x 5883 ppm Sn + 905 ppm Zn	Unalloyed Cu + Pb + Sb
	10							74		84	x 5883 ppm Sn + 905 ppm Zn	Unalloyed Cu + SbPb
	10					69	5			84	x 5883 ppm Sn + 905 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Brass	10							Sn ₁₇ Pb ₈₃				
	13					83			5	98	x 905 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	13						85			2 100	✓	Brass + SnPb + Sb
	13						72			2 86	x 5883 ppm Sn	Brass + Pb + Sb
	13							74		86	x 5883 ppm Sn	Brass + SbPb
	13					69*	5			86	x 5883 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Bronze	24					83		5		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
	24						85			2 112	x 905 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	24						72			2 98	x 905 ppm Zn	Bronze + Pb + Sb
	24							74		98	x 905 ppm Zn	Bronze + SbPb
	24					69*	5			98	x 905 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	24						Sn ₁₇ Pb ₈₃		5	112	x 905 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	12						83		5			Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	12						Sn ₁₅ Pb ₈₅			2 98	x 905 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	12						84					
	12						Sn ₁₅ Pb ₈₅					
	26					82		5		98	x 905 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	26						85			2 114	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	26						72			2 100	✓	Gunmetal + Pb + Sb
	26							74		100	✓	Gunmetal + SbPb
	26					69*	5			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
							Sn ₁₄ Pb ₈₆		5			Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)
						15		81		100	✓	

I constraint Sb₄₂Pb₅₈ → 96% Pb free (29464 ppm)

II constraint Cu₉₀Sn₁₀ → 92% Sn free (5386 ppm)

III constraint : gunmetal with Sn=Zn → 85% Sn free (4978 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com95 – Correlations SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total							
		Blue-green	11823	723	4052	2448	42290	61336							
		Sn		Pb											
		Cu			Sb										
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 723 ppm Zn content as “non natural”)			
		Cu ₉₄ Zn ₆	Cu ₇₄ Sn ₂₆	Cu ₉₀ Sn ₁₀	Cu ₇₁ Sn ₂₄ Zn ₄	Cu ₈₉ Sn ₅ Zn ₅	Sn ₉ Pb ₉₁		Sb ₄₂ Pb ₅₈	Sb ₅ Pb ₉₅					
Unalloyed	19					76				4	99	x 723 ppm Zn	Unalloyed Cu + SnPb + Sb		
	19						69			4	92	x 4052 ppm Sn + 723 ppm Zn	Unalloyed Cu + Pb + Sb		
	19								73		92	x 4052 ppm Sn + 723 ppm Zn	Unalloyed Cu + SbPb		
	19						63	10			92	x 4052 ppm Sn + 723 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)		
Brass	19					Sn ₉ Pb ₉₁						x 723 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)		
	20					76				4	100	✓	Brass + SnPb + Sb		
	20						69			4	93	x 4052 ppm Sn	Brass + Pb + Sb		
	20								73		93	x 4052 ppm Sn	Brass + SbPb		
	20						63*	10			93	x 4052 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)		
Bronze	20					70		10			100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)		
	26					76				4	105	x 723 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb		
	26						69			4	99	x 723 ppm Zn	Bronze + Pb + Sb		
	26								73		99	x 723 ppm Zn	Bronze + SbPb		
	26					63*	10				99	x 723 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)		
	26					Sn ₉ Pb ₉₁						x 723 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)		
Gunmetal	21					70		10			105	x 723 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)		
	21					Sn ₆ Pb ₉₄						x 723 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb		
	21					73				4	99	x 723 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)		
	27					68		10			99	x 723 ppm Zn	Gunmetal + SnPb + Sb		
	27					76				4	107	✓ [Sn counted twice]	Gunmetal + Pb + Sb		
	27						69			4	100	✓	Gunmetal + SbPb		
	27								73		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)		
	22					Sn ₈ Pb ₉₂					100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)		

I constraint Sb₄₂Pb₅₈ → 92% Pb free (38909 ppm)

II constraint Cu₉₀Sn₁₀ → 68% Sn free (2738 ppm)

III constraint : gunmetal with Sn=Zn → 82% Sn free (3329 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com96a – Correlation SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total					
		Blue-green	1278	316	842	519	4883	7838					
Pb													
Sn													
		Cu											
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 316 ppm Zn content as “non natural”)	
		Cu ₈₀ Zn ₂₀	Cu ₆₀ Sn ₄₀	Cu ₉₀ Sn ₁₀	Cu ₅₂ Sn ₃₅ Zn ₁₃	Cu ₆₇ Sn ₁₇ Zn ₁₇	Sn ₁₅ Pb ₈₅		Sb ₄₂ Pb ₅₈	Sb ₁₀ Pb ₉₀			
Unalloyed copper	16						73			7	96	x 316 ppm Zn	Unalloyed Cu + SnPb + Sb
	16							62		7	85	x 842 ppm Sn + 316 ppm Zn	Unalloyed Cu + Pb + Sb
	16								69		85	x 842 ppm Sn + 316 ppm Zn	Unalloyed Cu + SbPb
	16						53	16			85	x 842 ppm Sn + 316 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	16												Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	20						73			7	100	✓	Brass + SnPb + Sb
	20							62		7	89	x 842 ppm Sn	Brass + Pb + Sb
	20								69		89	x 842 ppm Sn	Brass + SbPb
	20						53*	16			89	x 842 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	20						64		16		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	27						73			7	107	x 316 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	27							62		7	96	x 316 ppm Zn	Bronze + Pb + Sb
	27								69		96	x 316 ppm Zn	Bronze + SbPb
	27						53*	16			96	x 316 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	27						64		16		107	x 316 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	18							71		7	96	x 316 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	18							Sn ₁₄ Pb ₈₆					Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	31						73			7	111	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	31							62		7	100	✓	Gunmetal + Pb + Sb
	31								69		100	✓	Gunmetal + SbPb
	31						53*	16			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
													Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 85% Pb free (4617 ppm)

II constraint Cu₉₀Sn₁₀ → 83% Sn free (700 ppm)

III constraint : gunmetal with Sn=Zn → 62% Sn free (526 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com97 – Correlations Cu/Sb (1.02), SnPb, orange group lead antimonates ($\text{Sb}_{35}\text{Pb}_{65}$).

	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Green	1908	166	670	1906	5311	9962		
		Pb							
		Sn							
		Cu							
		Brass Bronze Gunmetal SnPb SnPb free Pb Sb ₄₂ Pb ₅₈ SbPb Sb Tot						Unexplained (considering 166 ppm Zn content as “non natural”)	
		$\text{Cu}_{93}\text{Zn}_7$ $\text{Cu}_{88}\text{Sn}_{12}$ $\text{Cu}_{90}\text{Sn}_{10}$ $\text{Cu}_{83}\text{Sn}_{11}\text{Zn}_6$ $\text{Cu}_{88}\text{Sn}_6\text{Zn}_6$ $\text{Sn}_7\text{Pb}_{93}$ $\text{Sb}_{42}\text{Pb}_{58}$ $\text{Sb}_{35}\text{Pb}_{65}$							
Unalloyed	25			49			24 98	x 131 ppm Zn	Unalloyed Cu + SnPb + Sb
	25				46		24 95	x 244 ppm Sn + 131 ppm Zn	Unalloyed Cu + Pb + Sb
	25					70	95	x 244 ppm Sn + 131 ppm Zn	Unalloyed Cu + SbPb
	25				12 58		95	x 244 ppm Sn + 131 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	25						98	x 131 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	26			49			24 100	✓	Brass + SnPb + Sb
	26				46		24 97	x 244 ppm Sn	Brass + Pb + Sb
	26					70	97	x 244 ppm Sn	Brass + SbPb
	26				12* 58		97	x 244 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26				16 58		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	28			49			24 101	x 131 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	28				46		24 98	x 131 ppm Zn	Bronze + Pb + Sb
	28					70	98	x 131 ppm Zn	Bronze + SbPb
	28				12* 58		98	x 131 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28						101	x 131 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	27						24 98	x 131 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	27						98	x 131 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	30			49			24 103	✓ Sn counted twice	Gunmetal + SnPb + Sb
	30				46		24 100	✓	Gunmetal + Pb + Sb
	30					70	100	✓	Gunmetal + SbPb
	30				12* 58		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28						100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)
	14								

I constraint Sb₄₂Pb₅₈ → 27% Pb free (939 ppm)

II constraint Cu₉₀Sn₁₀ → 15% Sn free (36 ppm)

III constraint : gunmetal with Sn=Zn → 46% Sn free (113 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

Com98 – Correlation strong SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total		
		Blue-green	2574	482	2599	1468	14780	21903		
Pb										
Sn										
		Cu								
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb		
		Cu ₈₄ Zn ₁₆	Cu ₅₀ Sn ₅₀	Cu ₉₀ Sn ₁₀	Cu ₄₆ Sn ₄₆ Zn ₉	Cu ₇₃ Sn ₁₄ Zn ₁₄	Sn ₁₅ Pb ₈₅	Sn ₄₂ Pb ₅₈		
								Sn ₄₂ Pb ₅₈		
Unalloyed	12					79			7 98 x 482 ppm Zn	Unalloyed Cu + SnPb + Sb
	12						67		7 86 x 2599 ppm Sn + 482 ppm Zn	Unalloyed Cu + Pb + Sb
	12							74	7 86 x 2599 ppm Sn + 482 ppm Zn	Unalloyed Cu + SbPb
	12					58	16		86 x 2599 ppm Sn + 482 ppm Zn	Unalloyed Cu + Sn ₄₂ Pb ₅₈ + Pb (free)
	12					70	16	98	x 482 ppm Zn	Unalloyed Cu + Sn ₄₂ Pb ₅₈ + SnPb (free)
Brass	14					79			7 100 ✓	Brass + SnPb + Sb
	14						67		7 88 x 2599 ppm Sn	Brass + Pb + Sb
	14							74	88 x 2599 ppm Sn	Brass + SbPb
	14					58*	16		88 x 2599 ppm Sn	Brass + Sn ₄₂ Pb ₅₈ + *Pb (free)
	14					70	16	100	✓	Brass + Sn ₄₂ Pb ₅₈ + SnPb (free)
Bronze	24					79			7 110 x 482 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	24						67		7 98 x 482 ppm Zn	Bronze + Pb + Sb
	24							74	98 x 482 ppm Zn	Bronze + SbPb
	24					58*	16		98 x 482 ppm Zn	Bronze + Sn ₄₂ Pb ₅₈ + *Pb (free)
	24					70	16	110	x 482 ppm Zn [Sn counted twice]	Bronze + Sn ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	13						78		7 98 x 482 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	13						Sn ₁₅ Pb ₈₅		98 x 482 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sn ₄₂ Pb ₅₈ + SnPb (free)
	26					79			7 112 ✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	26						67		7 100 ✓	Gunmetal + Pb + Sb
	26							74	100 ✓	Gunmetal + SbPb
	26					58*	16	100	✓	Gunmetal + Sn ₄₂ Pb ₅₈ + *Pb (free)
						Sn ₁₄ Pb ₈₆				
						16	68	16	100 ✓	Gunmetal calc. + Sn ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sn₄₂Pb₅₈ → 86% Pb free (12753 ppm)

II constraint Cu₉₀Sn₁₀ → 89% Sn free (2313 ppm)

III constraint : gunmetal with Sn=Zn → 81% Sn free (2117 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO23A – Correlations Cu/Sb (0.96), strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Green	885	102	521	924	4076	6507					
	Pb											
	Sn											
	Cu											
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 102 ppm Zn content as “non natural”)	
	Cu ₉₀ Zn ₁₀	Cu ₆₃ Sn ₃₇	Cu ₉₀ Sn ₁₀	Cu ₅₉ Sn ₃₅ Zn ₇	Cu ₈₁ Sn ₉ Zn ₉	Sn ₁₁ Pb ₈₉		Sb ₄₂ Pb ₅₈	Sb ₁₈ Pb ₈₂			
14						71				14 98	x 102 ppm Zn	Unalloyed Cu + SnPb + Sb
14							63			14 90	x 521 ppm Sn + 102 ppm Zn	Unalloyed Cu + Pb + Sb
14								77		90	x 521 ppm Sn + 102 ppm Zn	Unalloyed Cu + SbPb
14						43	34			90	x 521 ppm Sn + 102 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
14					Sn ₁₆ Pb ₈₄							
					51		34			98	x 102 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Brass	15					71				14 100	✓	Brass + SnPb + Sb
	15						63			14 92	x 521 ppm Sn	Brass + Pb + Sb
	15							77		92	x 521 ppm Sn	Brass + SbPb
	15					43*	34			92	x 521 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	15					51		34		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	22					71				14 106	x 102 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	22						63			14 98	x 102 ppm Zn	Bronze + Pb + Sb
	22							77		98	x 102 ppm Zn	Bronze + SbPb
	22				Sn ₁₆ Pb ₈₄	43*	34			98	x 102 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	22					51		34		106	x 102 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	15				Sn ₉ Pb ₉₁	69				14 98	x 102 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	15				Sn ₁₃ Pb ₈₇	50		34		98	x 102 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	23					71				14 108	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	23						63			14 100	✓	Gunmetal + Pb + Sb
	23							77		100	✓	Gunmetal + SbPb
	23				Sn ₁₃ Pb ₈₇	43*	34			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
					17	49		34		100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 69% Pb free (2800 ppm)

II constraint Cu₉₀Sn₁₀ → 81% Sn free (422 ppm)

III constraint : gunmetal with Sn=Zn → 80% Sn free (419 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO24 – Correlations Cu/Sb (0.30), SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total						
	Blue	2133	59	178	6991	3381	12742						
Pb													
		Sn											
		Cu											
			Sb										
				Sb									
					Tot								
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 59 ppm Zn content as “natural”)		
					Sn ₅ Pb ₉₅			Sb ₄₂ Pb ₅₈	Sb ₆₇ Pb ₃₃				
Bronze	17				28				55	100	✓	Unalloyed Cu + SnPb + Sb	
	17						27		55	99	✗ 178 ppm Sn	Unalloyed Cu + Pb + Sb	
	17							82		99	✗ 178 ppm Sn	Unalloyed Cu + SbPb	
	17				-	Low Pb				-	✗ -	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
	17					Low Sn							
	18				28				55	101	✓ [Sn counted twice]	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	18						27		55	100	✓	Bronze + SnPb + Sb	
	18							82		100	✓	Bronze + Pb + Sb	
	18				-	Low Pb			-	-	✗ -	Bronze + SbPb	
	18					Low Sn						Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
Brass	19					Low Sn							
	19					-							
	19					-	Low Pb					Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Gunmetal	19								55	-	✗ -	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb	
	19								-	-	✗ -	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	19												

I constraint Sb₄₂Pb₅₈ → 186% Pb less (6273 ppm missing)

II constraint Cu₉₀Sn₁₀ → 33% Sn less (59 ppm missing)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO58A – Correlations Cu/Sb (1.0), strong SnPb, red group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Green	797	65	343	797	1866	3869				
		Pb									
		Sn									
		Cu									
		Cu									
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 65 ppm Zn content as “natural”)
					Sn ₁₆ Pb ₈₄			Sb ₄₂ Pb ₅₈	Sb ₃₀ Pb ₇₀		
	21				58			21	100	✓	Unalloyed Cu + SnPb + Sb
	21						49	21	91	x 343 ppm Sn	Unalloyed Cu + Pb + Sb
	21							69	91	x 343 ppm Sn	Unalloyed Cu + SbPb
	21					20	50		91	x 343 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	21										
					Sn ₃₁ Pb ₆₉						
					29		50		100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	30				58			21	109	✓ [Sn counted twice]	Bronze + SnPb + Sb
	30						49	21	100	✓	Bronze + Pb + Sb
	30							70	100	✓	Bronze + SbPb
	30					20*	50		100	✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	30										
					Sn ₃₁ Pb ₆₉						
					29		50		109	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
					Sn ₁₂ Pb ₈₈						
					56			21	100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
					Sn ₂₅ Pb ₇₅						
					27		50		100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 41% Pb free (766 ppm)

II constraint Cu₉₀Sn₁₀ → 74% Sn free (254 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO58B – Correlations SnPb, red group lead antimonates.

		Colour	Cu	Zn	Sn	Sb	Pb	Total	
		Green	1124	142	668	2645	6528	11107	
Pb									
Sn									
Cu									
Brass Bronze Gunmetal									
<chem>Cu89Zn11</chem> <chem>Cu63Sn37</chem> <chem>Cu90Sn10</chem> <chem>Cu58Sn35Zn7</chem> <chem>Cu80Sn10Zn10</chem> <chem>Sn9Pb91</chem> <chem>Sn42Pb58</chem> <chem>Sb42Pb58</chem> <chem>Sb29Pb71</chem>									
Unalloyed	10				65		24	99	x 142 ppm Zn
	10					59	24	93	x 668 ppm Sn + 142 ppm Zn
	10						83	93	x 668 ppm Sn + 142 ppm Zn
	10				26	57		93	x 668 ppm Sn + 142 ppm Zn
	10								Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Brass	11				65		24	100	✓
	11					59	24	94	x 668 ppm Sn
	11						83	94	x 668 ppm Sn
	11				26	57		94	x 668 ppm Sn
	11				32	57		100	✓
Bronze	16				65		24	105	x 142 ppm Zn [Sn counted twice]
	16					59	24	99	x 142 ppm Zn
	16						83	99	x 142 ppm Zn
	16				26	57		99	x 142 ppm Zn
	16								Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
Gunmetal	11					32	57	105	x 142 ppm Zn [Sn counted twice]
	11								Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	17				65		24	99	x 142 ppm Zn
	17					59	24	100	✓ [Sn counted twice]
	17						83	100	✓
	17				26	57		100	✓
									Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 44% Pb free (2875 ppm)

II constraint Cu₉₀Sn₁₀ → 81% Sn free (543 ppm)

III constraint : gunmetal with Sn=Zn → 79% Sn free (526 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO58C – Correlations SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total			
		Green	105	37	183	42	295	662			
			Pb								
			Sn								
			Cu								
Unalloyed	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 37 ppm Zn content as “natural”)
					Sn ₃₈ Pb ₆₂			Sb ₄₂ Pb ₅₈	Sb ₁₂ Pb ₈₈		
	17				76			7	100	✓	Unalloyed Cu + SnPb + Sb
	17					47		7	71	✗ 183 ppm Sn	Unalloyed Cu + Pb + Sb
	17						54	71		✗ 183 ppm Sn	Unalloyed Cu + SbPb
	17				38	16		71		✗ 183 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
					Sn ₄₄ Pb ₅₆						
	17				67	16		100		✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	46				76			7	129	✓ [Sn counted twice]	Bronze + SnPb + Sb
	46					47		7	100	✓	Bronze + Pb + Sb
Bronze	46					54		100		✓	Bronze + SbPb
	46				38	16		100		✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
					Sn ₄₄ Pb ₅₆						
	46				67	16		129		✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
					Sn ₃₇ Pb ₆₃						
	19				75			7	100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
					Sn ₄₂ Pb ₅₈			100		✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 80% Pb free (237 ppm)

II constraint Cu₉₀Sn₁₀ → 94% Sn free (171 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO88 – Correlations Cu/Sb (0.97), strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Green light	1561	186	2201	1608	14546	20100				
Pb											
Sn											
	Cu			Sn							
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 186 ppm Zn content as “non natural”)
<chem>Cu89Zn11</chem> <chem>Cu41Sn59</chem> <chem>Cu90Sn10</chem> <chem>Cu40Sn56Zn5</chem> <chem>Cu81Sn10Zn10</chem> <chem>Sn13Pb87</chem>								<chem>Sb42Pb58</chem>	<chem>Sb10Pb90</chem>		
Unalloyed	8				83			8	99	x 186 ppm Zn	Unalloyed Cu + SnPb + Sb
	8						72	8	88	x 2201 ppm Sn + 186 ppm Zn	Unalloyed Cu + Pb + Sb
	8							80	88	x 2201 ppm Sn + 186 ppm Zn	Unalloyed Cu + SbPb
	8				61	19			88	x 2201 ppm Sn + 186 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Brass	8					<chem>Sn15Pb85</chem>			99	x 186 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	9				83			8	100	✓	Brass + SnPb + Sb
	9						72	8	89	x 2201 ppm Sn	Brass + Pb + Sb
	9							80	89	x 2201 ppm Sn	Brass + SbPb
	9				61*	19			89	x 2201 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	9				72		19		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	19				83			8	110	x 186 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	19						72	8	99	x 186 ppm Zn	Bronze + Pb + Sb
	19							80	99	x 186 ppm Zn	Bronze + SbPb
	19				61*	19			99	x 186 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	19					<chem>Sn15Pb85</chem>			110	x 186 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	9					<chem>Sn12Pb88</chem>			8	99	x 186 ppm Zn
Gunmetal	9					<chem>Sn14Pb86</chem>			99	x 186 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	20				83			8	111	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	20						72	8	100	✓	Gunmetal + Pb + Sb
	20							80	100	✓	Gunmetal + SbPb
	20				61*	19			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	10					<chem>Sn14Pb86</chem>			100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 85% Pb free (12325 ppm)

II constraint Cu₉₀Sn₁₀ → 92% Sn free (2027 ppm)

III constraint : gunmetal with Sn=Zn → 92% Sn free (2015 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO92 – Correlations Cu/Sb (0.94), strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Green light	3180	589	2875	3402	17683	27729					
Pb												
Sn												
	Cu											
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 589 ppm Zn content as “non natural”)	
<chem>Cu84Zn16</chem> <chem>Cu53Sn47</chem> <chem>Cu90Sn10</chem> <chem>Cu48Sn43Zn9</chem> <chem>Cu73Sn14Zn14</chem> <chem>Sn14Pb86</chem>								<chem>Sb42Pb58</chem>	<chem>Sb16Pb84</chem>			
Unalloyed	11				74			12	98		x 589 ppm Zn	Unalloyed Cu + SnPb + Sb
	11					64		12	88		x 2875 ppm Sn + 589 ppm Zn	Unalloyed Cu + Pb + Sb
	11						76	88			x 2875 ppm Sn + 589 ppm Zn	Unalloyed Cu + SbPb
	11					47	29	88			x 2875 ppm Sn + 589 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Brass	11					<chem>Sn18Pb82</chem>						
	14				74	57	29	98			x 589 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	14					64		12	100	✓		Brass + SnPb + Sb
	14						76	12	90		x 2875 ppm Sn	Brass + Pb + Sb
	14					47*	29	90			x 2875 ppm Sn	Brass + SbPb
	14					57	29	100			x 2875 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Bronze	22				74			12	108		x 589 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	22					64		12	98		x 589 ppm Zn	Bronze + Pb + Sb
	22						76	98			x 589 ppm Zn	Bronze + SbPb
	22					47*	29	98			x 589 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	22					<chem>Sn18Pb82</chem>	57	29	108		x 589 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	13					<chem>Sn12Pb88</chem>	73		12	98	x 589 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
Gunmetal	13					<chem>Sn16Pb84</chem>			98		x 589 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	24				74			12	110	✓ [Sn counted twice]		Gunmetal + SnPb + Sb
	24					64		12	100	✓		Gunmetal + Pb + Sb
	24						76	100		✓		Gunmetal + SbPb
	24					47*	29	100		✓		Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
						<chem>Sn15Pb85</chem>	55	29	100	✓		Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 73% Pb free (12985 ppm)

II constraint Cu₉₀Sn₁₀ → 88% Sn free (2027 ppm)

III constraint : gunmetal with Sn=Zn → 80% Sn free (2286 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO93 – Correlations Cu/Sb (0.97), strong SnPb, red group lead antimonates.


	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Green	1742	78	706	1788	4578	8893		
		Pb							
		Sn							
		Cu							
		Cu							
Unalloyed	Cu	Cu ₇₁ Sn ₂₉	Cu ₉₀ Sn ₁₀	Cu ₆₉ Sn ₂₈ Zn ₃	Cu ₉₂ Sn ₄ Zn ₄	Sn ₁₃ Pb ₈₇	Sb ₄₂ Pb ₅₈	Sb ₂₈ Pb ₇₂	Unexplained (considering 78 ppm Zn content as “natural”)
	Brass								
	Bronze								
	Gunmetal								
Bronze	20			60			20 100	✓	Unalloyed Cu + SnPb + Sb
	20				52		20 92	x 706 ppm Sn	Unalloyed Cu + Pb + Sb
	20					72	92	x 706 ppm Sn	Unalloyed Cu + SbPb
	20			24	48		92	x 706 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	20								
	28					Sn ₂₅ Pb ₇₅			
	28			60			100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	28				52		20 108	✓ [Sn counted twice]	Bronze + SnPb + Sb
	28					72	20 100	✓	Bronze + Pb + Sb
	28			24*	48		100	✓	Bronze + SbPb
	28								Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	28					Sn ₂₅ Pb ₇₅			
	22					32	108	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
						Sn ₁₀ Pb ₉₀			
						58	20 100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	22					Sn ₂₀ Pb ₈₀			
						30	100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 46% Pb free (2109 ppm)

II constraint Cu₉₀Sn₁₀ → 73% Sn free (513 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO95 – Correlations Cu/Sb (1.03), SnPb, red correlation lead antimonates.

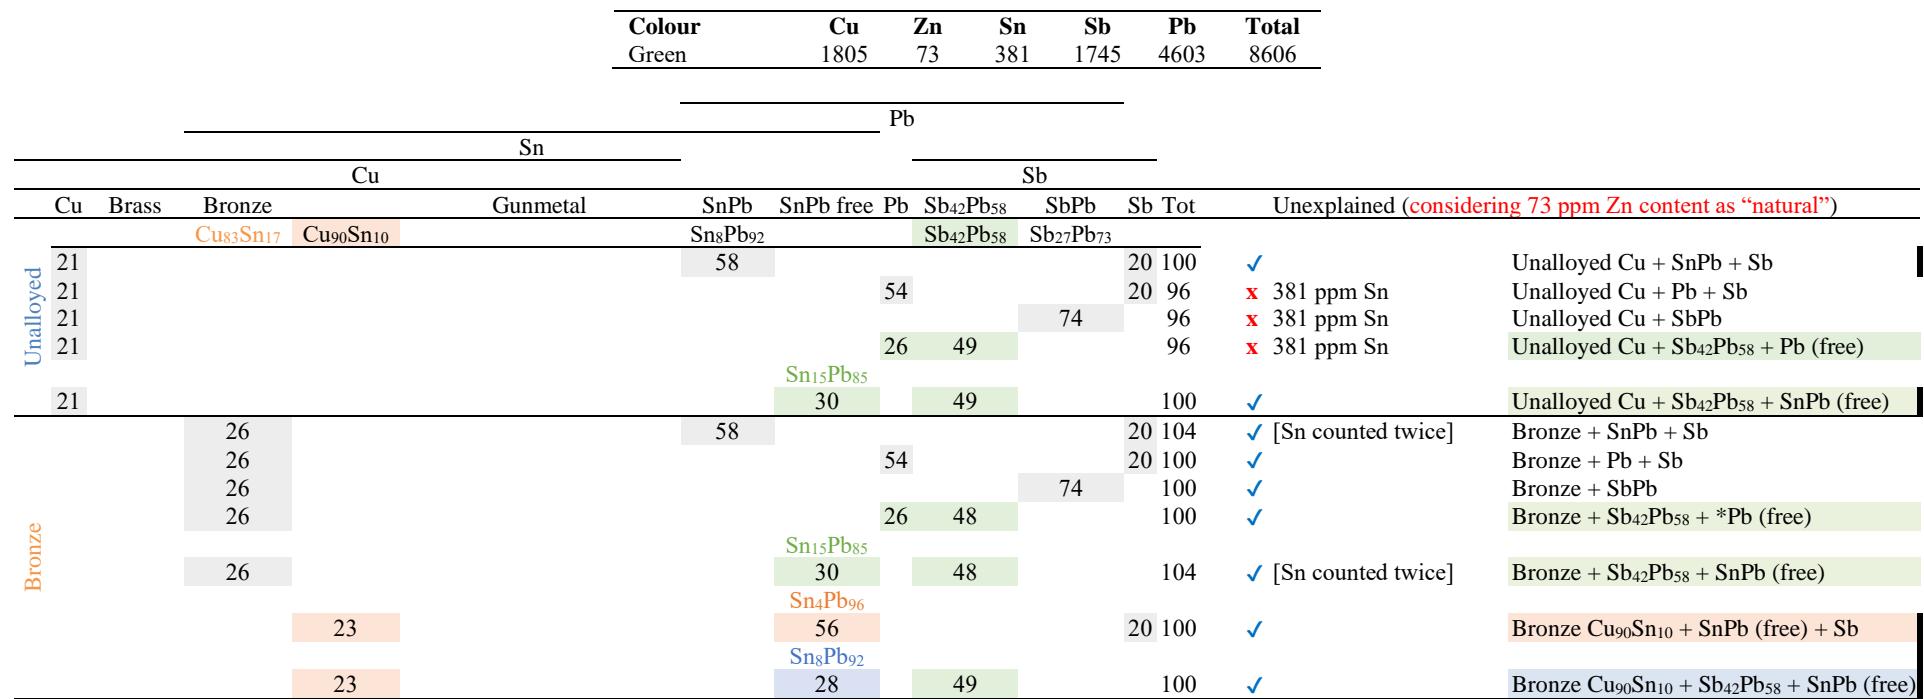

I constraint Sb₄₂Pb₅₈ → 48% Pb free (2194 ppm)

II constraint Cu₉₀Sn₁₀ → 47% Sn free (180 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO96 – Correlation strong SnPb.

		Colour	Cu	Zn	Sn	Sb	Pb	Total
		Green light	2579	187	896	1263	5929	10852
Pb								
Sn								
	Cu							
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
	Cu ₉₃ Zn ₇	Cu ₇₄ Sn ₂₆	Cu ₉₀ Sn ₁₀	Cu ₇₀ Sn ₂₄ Zn ₅	Cu ₈₇ Sn ₆ Zn ₆	Sn ₁₃ Pb ₈₇		Sb ₄₂ Pb ₅₈
								Sb ₁₈ Pb ₈₂
Unalloyed	24				63			12 98
	24					55		12 90
	24						66	90
	24				39	28		90
	24				47	28		98
Brass	25				63			12 100
	25					55		12 92
	25						66	92
	25				39*	28		92
	25				47	28		100
Bronze	32				63			12 107
	32					55		12 98
	32						66	98
	32				39*	28		98
	32				47	28		107
Gunmetal	26							
	26				60			12 98
	26				Sn ₁₃ Pb ₈₇			
	34				44	28		98
	34				27	45		100
Unexplained (considering 187 ppm Zn content as “non natural”)								
<p>x 187 ppm Zn Unalloyed Cu + SnPb + Sb</p> <p>x 896 ppm Sn + 187 ppm Zn Unalloyed Cu + Pb + Sb</p> <p>x 896 ppm Sn + 187 ppm Zn Unalloyed Cu + SbPb</p> <p>x 896 ppm Sn + 187 ppm Zn Unalloyed Cu + Sb₄₂Pb₅₈ + Pb (free)</p> <p>x 187 ppm Zn Unalloyed Cu + Sb₄₂Pb₅₈ + SnPb (free)</p> <p>✓ Brass + SnPb + Sb</p> <p>✓ Brass + Pb + Sb</p> <p>✓ Brass + SbPb</p> <p>✓ Brass + Sb₄₂Pb₅₈ + *Pb (free)</p> <p>✓ Brass + Sb₄₂Pb₅₈ + SnPb (free)</p> <p>x 187 ppm Zn [Sn counted twice] Bronze + SnPb + Sb</p> <p>x 187 ppm Zn Bronze + Pb + Sb</p> <p>x 187 ppm Zn Bronze + SbPb</p> <p>x 187 ppm Zn Bronze + Sb₄₂Pb₅₈ + *Pb (free)</p> <p>x 187 ppm Zn [Sn counted twice] Bronze + Sb₄₂Pb₅₈ + SnPb (free)</p> <p>x 187 ppm Zn Bronze Cu₉₀Sn₁₀ + SnPb (free) + Sb</p> <p>✓ [Sn counted twice] Gunmetal + SnPb + Sb</p> <p>✓ Gunmetal + Pb + Sb</p> <p>✓ Gunmetal + SbPb</p> <p>✓ Gunmetal + Sb₄₂Pb₅₈ + *Pb (free)</p> <p>✓ Gunmetal calc. + Sb₄₂Pb₅₈ + SnPb (free)</p>								

I constraint Sb₄₂Pb₅₈ → 71% Pb free (4185 ppm)

II constraint Cu₉₀Sn₁₀ → 68% Sn free (609 ppm)

III constraint : gunmetal with Sn=Zn → 79% Sn free (709 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO100A – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Green-red	2290	255	1801	1100	7719	13164				
	Pb										
	Sn										
	Cu		Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 255 ppm Zn content as “non natural”)	
	Cu ₉₀ Zn ₁₀	Cu ₅₆ Sn ₄₄	Cu ₉₀ Sn ₁₀	Cu ₅₃ Sn ₄₁ Zn ₆	Cu ₈₂ Sn ₉ Zn ₉	Sn ₁₉ Pb ₈₁	Sb ₄₂ Pb ₅₈	Sb ₁₂ Pb ₈₈			
Unalloyed	17					72			8 98	x 255 ppm Zn x 1801 ppm Sn + 255 ppm Zn x 1801 ppm Sn + 255 ppm Zn x 1801 ppm Sn + 255 ppm Zn	Unalloyed Cu + SnPb + Sb Unalloyed Cu + Pb + Sb Unalloyed Cu + SbPb Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	17						59		8 84		
	17							67	84		
	17					47 20			84		
Brass	17								98	x 255 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	19					72			8 100	✓	Brass + SnPb + Sb
	19						59		8 86	x 1801 ppm Sn	Brass + Pb + Sb
	19							67	86	x 1801 ppm Sn	Brass + SbPb
	19					47 20			86	x 1801 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
	19					61	20		100	✓	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	31					72			8 112	x 255 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	31						59		8 98	x 255 ppm Zn	Bronze + Pb + Sb
	31							67	98	x 255 ppm Zn	Bronze + SbPb
	31					47 20			98	x 255 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	31						61	20	112	x 255 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	19					70			8 98	x 255 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
Gunmetal	19						Sn ₁₇ Pb ₈₃				
	33					72			8 114	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	33						59		8 100	✓	Gunmetal + Pb + Sb
	33							67	100	✓	Gunmetal + SbPb
	33					47 20			100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	21					Sn ₂₀ Pb ₈₀	59	20	100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 80% Pb free (6200 ppm)

II constraint Cu₉₀Sn₁₀ → 86% Sn free (1546 ppm)

III constraint : gunmetal with Sn=Zn → 86% Sn free (1545 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO100B– Correlations Cu/Sb (1.10), SnPb, orange group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total			
	Green	1548	33	192	1404	2700	5876			
		Pb								
		Sn								
	Cu	Sb								
	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 33 ppm Zn content as “natural”)
	Cu ₈₉ Sn ₁₁	Cu ₉₀ Sn ₁₀		Sn ₇ Pb ₉₃			Sb ₄₂ Pb ₅₈	Sb ₃₄ Pb ₆₆		
Unallloyed	26			49			24	100	✓	Unalloyed Cu + SnPb + Sb
	26				46		24	97	✗ 192 ppm Sn + 33 ppm Zn	Unalloyed Cu + Pb + Sb
	26					70	97	97	✗ 192 ppm Sn + 33 ppm Zn	Unalloyed Cu + SbPb
	26				13	57		97	✗ 192 ppm Sn + 33 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Bronze	26			Sn ₂₀ Pb ₈₀	16	57		100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	30			49			24	103	✓ [Sn counted twice]	Bronze + SnPb + Sb
	30				46		24	100	✓	Bronze + Pb + Sb
	30					70	100	✓	Bronze + SbPb	
	30				13*	57		100	✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
		30		Sn ₂₀ Pb ₈₀	16	57		103	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
		29		Sn ₁ Pb ₉₉	47		24	100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
		29		Sn ₃ Pb ₉₇	13	57		100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 28% Pb free (761 ppm)

II constraint Cu₉₀Sn₁₀ → 10% Sn free (20 ppm)

III constraint : gunmetal with Sn=Zn → 83% Sn free (159 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO121A – Correlations Cu/Sb (1.04), strong SnPb, red group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Green light	1233	72	575	1189	3344	6413		
Pb									
		Sn			Sb				
		Cu			Sb				
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	
					Sn ₁₅ Pb ₈₅			Sb ₄₂ Pb ₅₈	
								Sb ₂₆ Pb ₇₄	
Unalloyed	19				62			19 100 ✓	Unalloyed Cu + SnPb + Sb
	19					53		19 91 ✗ 575 ppm Sn	Unalloyed Cu + Pb + Sb
	19						71	91 ✗ 575 ppm Sn	Unalloyed Cu + SbPb
	19				27	45		91 ✗ 575 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	19				Sn ₂₅ Pb ₇₅	36	45	100 ✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	29				62			19 109 ✓ [Sn counted twice]	Bronze + SnPb + Sb
	29					53		19 100 ✓	Bronze + Pb + Sb
	29						71	100 ✓	Bronze + SbPb
	29				27*	45		100 ✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	29				Sn ₂₅ Pb ₇₅	36	45	109 ✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	22				Sn ₁₂ Pb ₈₈	60		19 100 ✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	22				Sn ₂₀ Pb ₈₀	34	45	100 ✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 51% Pb free (1702 ppm)

II constraint Cu₉₀Sn₁₀ → 76% Sn free (438 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO121B – Correlation SnPb, red group lead antimonates.

		Colour	Cu	Zn	Sn	Sb	Pb	Total		
		Green light	1882	81	444	1389	4083	7879		
Pb										
Sn										
		Cu				Sb				
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	
						Sn ₁₀ Pb ₉₀			Sb ₄₂ Pb ₅₈ Sb ₂₅ Pb ₇₅	
Unalloyed	24					58			18 100 ✓	Unalloyed Cu + SnPb + Sb
	24						52		18 94 ✗ 444 ppm Sn	Unalloyed Cu + Pb + Sb
	24							70	94 ✗ 444 ppm Sn	Unalloyed Cu + SbPb
	24					28	42		94 ✗ 444 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	24					Sn ₁₇ Pb ₈₃	33	42	100 ✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
Bronze	30					58			18 106 ✓ [Sn counted twice]	Bronze + SnPb + Sb
	30						52		18 100 ✓	Bronze + Pb + Sb
	30							70	100 ✓	Bronze + SbPb
	30					28	42		100 ✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	30					Sn ₁₇ Pb ₈₃	33	42	106 ✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	27					Sn ₅ Pb ₉₅	55		18 100 ✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	27					Sn ₁₀ Pb ₉₀	31	42	100 ✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 53% Pb free (2166 ppm)

II constraint Cu₉₀Sn₁₀ → 53% Sn free (235 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO121C – Correlations Cu/Sb (0.98), strong SnPb, red group lead antimonates.

		Colour	Cu	Zn	Sn	Sb	Pb	Total
		Green light	1491	57	305	1516	3395	6765
Pb								
		Sn						
		Cu						
Unallloyed	Cu	Bronze	Brass	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
	22	Cu ₈₃ Sn ₁₇	Cu ₉₀ Sn ₁₀		Sn ₈ Pb ₉₂			Sb ₄₂ Pb ₅₈
Bronze	22				55			23 100
	22					51		23 95
	22						73	95
	22				19	54		95
	22							
	27				24	54		100
	27				55			23 105
	27					51		23 100
	27						73	100
	27				19	54		100
	27				Sn ₁₉ Pb ₈₁			
	25				24	54		105
	25				Sn ₄ Pb ₉₆			23 100
					Sn ₁₀ Pb ₉₀			
Sb								
Unexplained (considering 57 ppm Zn content as "natural")								
✓ Unalloyed Cu + SnPb + Sb ✗ 305 ppm Sn Unalloyed Cu + Pb + Sb ✗ 305 ppm Sn Unalloyed Cu + SbPb ✗ 305 ppm Sn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)								
✓ Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free) ✓ [Sn counted twice] Bronze + SnPb + Sb ✓ Bronze + Pb + Sb ✓ Bronze + SbPb ✓ Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free) ✓ [Sn counted twice] Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free) ✓ Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb ✓ Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)								

I constraint Sb₄₂Pb₅₈ → 38% Pb free (1301 ppm)

II constraint Cu₉₀Sn₁₀ → 46% Sn free (139 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO121D – Correlations Cu/Sb (0.91), SnPb, orange correlation lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total						
	Green light	2550	92	417	2819	4635	10513						
				Pb									
			Sn										
		Cu			Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 92 ppm Zn content as “natural”)		
Unalloyed	Cu ₈₆ Sn ₁₄	Cu ₉₀ Sn ₁₀			Sn ₈ Pb ₉₂			Sb ₄₂ Pb ₅₈	Sb ₃₈ Pb ₆₂				
	24				48			27	100	✓	Unalloyed Cu + SnPb + Sb		
	24					44		27	96	✗ 417 ppm Sn	Unalloyed Cu + Pb + Sb		
	24						72	27	96	✗ 417 ppm Sn	Unalloyed Cu + SbPb		
	24				7	64			96	✗ 417 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)		
Bronze	24				Sn ₃₆ Pb ₆₄			11	64	100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	28				48			27	104	✓ [Sn counted twice]	Bronze + SnPb + Sb		
	28					44		27	100	✓	Bronze + Pb + Sb		
	28						72	27	100	✓	Bronze + SbPb		
	28				7	64			100	✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)		
	28				Sn ₃₆ Pb ₆₄			11	64	104	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	27				Sn ₃ Pb ₉₇			45		27	100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	27				Sn ₁₅ Pb ₈₅			8	64	100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)	

I constraint Sb₄₂Pb₅₈ → 16% Pb free (743 ppm)

II constraint Cu₉₀Sn₁₀ → 32% Sn free (134 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO122 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Blue	2482	71	182	6345	2435	11515	
Pb								
		Sn				Pb		
		Cu				Sb		
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
					Sn ₇ Pb ₉₃			SbPb
								Sb Tot
								Unexplained (considering 71 ppm Zn content as “natural”)
Unalloyed	Cu ₉₃ Sn ₇	Cu ₉₀ Sn ₁₀			23			55 99 ✓
						21		55 98 ✗ 182 ppm Sn
							76	98 ✗ 182 ppm Sn
					-	Low Pb		98 ✗ -
								Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Bronze	22					Low Sn		
	23				23	-	Low Pb	- ✗ -
	23					21		55 101 ✓ [Sn counted twice]
	23						55 99 ✓	Bronze + SnPb + Sb
	23						77 99 ✓	Bronze + Pb + Sb
	23				-	Low Pb	99 ✗ -	Bronze + SbPb
								Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
						Low Sn		
	23				-	Low Pb	101 ✗ -	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	24				Low Sn	-	55 99 ✗ -	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	24				-	Low Pb	99 ✗ -	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 260% Pb less (6327 ppm missing)

II constraint Cu₉₀Sn₁₀ → 94% Sn less (94 ppm missing)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO184A – Correlations Cu/Sb (1.0), strong SnPb, red correlation lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total						
	Green	1908	166	670	1906	5311	9962						
		Pb											
		Sn											
		Cu											
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 166 ppm Zn content as “non natural”)	
		Cu ₉₂ Zn ₈	Cu ₇₄ Sn ₂₆	Cu ₉₀ Sn ₁₀	Cu ₇₀ Sn ₂₄ Zn ₆	Cu ₈₅ Sn ₇ Zn ₇	Sn ₁₁ Pb ₈₉		Sb ₄₂ Pb ₅₈	Sb ₂₆ Pb ₇₄			
Unalloyed	19					60				19	98	x 166 ppm Zn	Unalloyed Cu + SnPb + Sb
	19						53			19	92	x 670 ppm Sn + 166 ppm Zn	Unalloyed Cu + Pb + Sb
	19							72		92	92	x 670 ppm Sn + 166 ppm Zn	Unalloyed Cu + SbPb
	19					27	46			92	92	x 670 ppm Sn + 166 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	19												
Brass	21					60	34	46		98	x 166 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	21						53			19	100	✓	Brass + SnPb + Sb
	21							72		19	93	x 670 ppm Sn	Brass + Pb + Sb
	21					27*	46			93	93	x 670 ppm Sn	Brass + SbPb
	21					34	46			93	100	x 670 ppm Sn	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Bronze	26					60				19	105	x 166 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	26						53			19	98	x 166 ppm Zn	Bronze + Pb + Sb
	26							72		98	98	x 166 ppm Zn	Bronze + SbPb
	26					27*	46			98	98	x 166 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	26									105		x 166 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gunmetal	21						34	46					Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	21						58			19	98	x 166 ppm Zn	
	21						Sn ₈ Pb ₉₂						Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	28					60				19	107	✓ Sn counted twice	Gunmetal + SnPb + Sb
	28						53			19	100	✓	Gunmetal + Pb + Sb
	28							72		100	100	✓	Gunmetal + SbPb
	28					27*	46			100	100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	22									100		✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)
	32												
	46												

I constraint Sb₄₂Pb₅₈ → 50% Pb free (2680 ppm)

II constraint Cu₉₀Sn₁₀ → 68% Sn free (458 ppm)

III constraint : gunmetal with Sn=Zn → 75% Sn free (504 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO184B – Correlations Cu/Sb (0.96), SnPb, orange group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total					
	Green	2098	58	261	2196	4389	9001					
		Pb										
		Sn										
	Cu	Sb										
	Cu Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 58 ppm Zn content as “natural”)		
	Cu ₈₉ Sn ₁₁	Cu ₉₀ Sn ₁₀		Sn ₆ Pb ₉₄			Sb ₄₂ Pb ₅₈	Sb ₃₃ Pb ₆₇				
Unallloyed	23				52			25	100	✓	Unalloyed Cu + SnPb + Sb	
	23					49		25	97	✗ 261 ppm Sn	Unalloyed Cu + Pb + Sb	
	23						74		97	✗ 261 ppm Sn	Unalloyed Cu + SbPb	
	23				15	58			97	✗ 261 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
Bronze	23				Sn ₁₆ Pb ₈₄		18	58	100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	26			52				25	103	✓ [Sn counted twice]	Bronze + SnPb + Sb	
	26				49			25	100	✓	Bronze + Pb + Sb	
	26					74		100		✓	Bronze + SbPb	
	26				15	58			100	✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	26				Sn ₁₆ Pb ₈₄		18	58	103	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	26				Sn ₁ Pb ₉₉		49		25	100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	26				Sn ₂ Pb ₉₈		15	58	100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)	

I constraint Sb₄₂Pb₅₈ → 31% Pb free (1356 ppm)

II constraint Cu₉₀Sn₁₀ → 11% Sn free (28 ppm)

III constraint : gunmetal with Sn=Zn → 78% Sn free (203 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO184C – Correlations Cu/Sb (0.88), SnPb, orange group lead antimonates.

		Colour	Cu	Zn	Sn	Sb	Pb	Total	
		Green	2057	114	421	2343	4725	9660	
Pb									
Sn									
		Cu			Sb				
		Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈
			Cu ₉₅ Zn ₅	Cu ₈₃ Sn ₁₇	Cu ₉₀ Sn ₁₀	Cu ₇₉ Sn ₁₆ Zn ₄	Cu ₉₀ Sn ₅ Zn ₅	Sn ₈ Pb ₉₂	Sb ₄₂ Pb ₅₈
									Sb ₃₃ Pb ₆₇
Unalloyed	21					53			24 99
	21						49		24 94
	21							73	94
	21					15	58		94
	21								Unexplained (considering 114 ppm Zn content as "non natural")
Brass	22					Sn ₂₂ Pb ₇₈			
	22					20	58		99
	22								x 114 ppm Zn
	22					53			Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	22						49		
	22							73	
Bronze	26					15*	58		24 100
	26								✓
	26					20	58		x 421 ppm Sn
	26							73	Brass + Pb + Sb
	26					53			Brass + SbPb
	26								Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Gunmetal	27					15*	58		96
	27								✓
	27					20	58		x 421 ppm Sn
	27							73	Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)
	27					53			
	27								
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									
Sb									
Pb									
Sn									
Cu									

CO230 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total		
	Green	607	194	874	209	3504	5389		
Pb									
Sn									
Cu									
Brass Bronze Gunmetal SnPb SnPb free Pb Sb ₄₂ Pb ₅₈ SbPb Sb Tot									
<chem>Cu76Zn24</chem> <chem>Cu41Sn59</chem> <chem>Cu90Sn10</chem> <chem>Cu36Sn52Zn12</chem> <chem>Cu61Sn20Zn20</chem> <chem>Sn20Pb80</chem> <chem>Sb42Pb58</chem> <chem>Sb6Pb94</chem>									
Unalloyed	11			81			4 96	x 194 ppm Zn	Unalloyed Cu + SnPb + Sb
	11				65		4 80	x 874 ppm Sn + 194 ppm Zn	Unalloyed Cu + Pb + Sb
	11					69	80	x 874 ppm Sn + 194 ppm Zn	Unalloyed Cu + SbPb
	11			60	9		80	x 874 ppm Sn + 194 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
	11			<chem>Sn21Pb79</chem>					
Brass	15			81			96	x 194 ppm Zn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	15				65		4 100	✓	Brass + SnPb + Sb
	15					69	4 84	x 874 ppm Sn	Brass + Pb + Sb
	15			60*	9		84	x 874 ppm Sn	Brass + SbPb
	15			<chem>Sn21Pb79</chem>	76	9	100	✓	Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)
Bronze	27			81			4 113	x 194 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	27				65		4 96	x 194 ppm Zn	Bronze + Pb + Sb
	27					69	96	x 194 ppm Zn	Bronze + SbPb
	27			60	9		96	x 194 ppm Zn	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	27			<chem>Sn21Pb79</chem>	76	9	113	x 194 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
Gummetal	13				<chem>Sn19Pb81</chem>				Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	13			80			4 96	x 194 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	31				<chem>Sn20Pb80</chem>				
	31			75		9	96	x 194 ppm Zn	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)
	31						4 116	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	31				65		4 100	✓	Gunmetal + Pb + Sb
	31					69	100	✓	Gunmetal + SbPb
	31			60	9		100	✓	Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
	18			<chem>Sn17Pb83</chem>	72	9	100	✓	Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 92% Pb free (3216 ppm)


II constraint Cu₉₀Sn₁₀ → 92% Sn free (806 ppm)

III constraint : gunmetal with Sn=Zn → 78% Sn free (679 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO233C – Correlation strong SnPb, yellow correlation lead antimonates.

Colour	Cu	Zn	Sn	Sb	Pb	Total
Blue	2099	87	523	3349	4264	10320

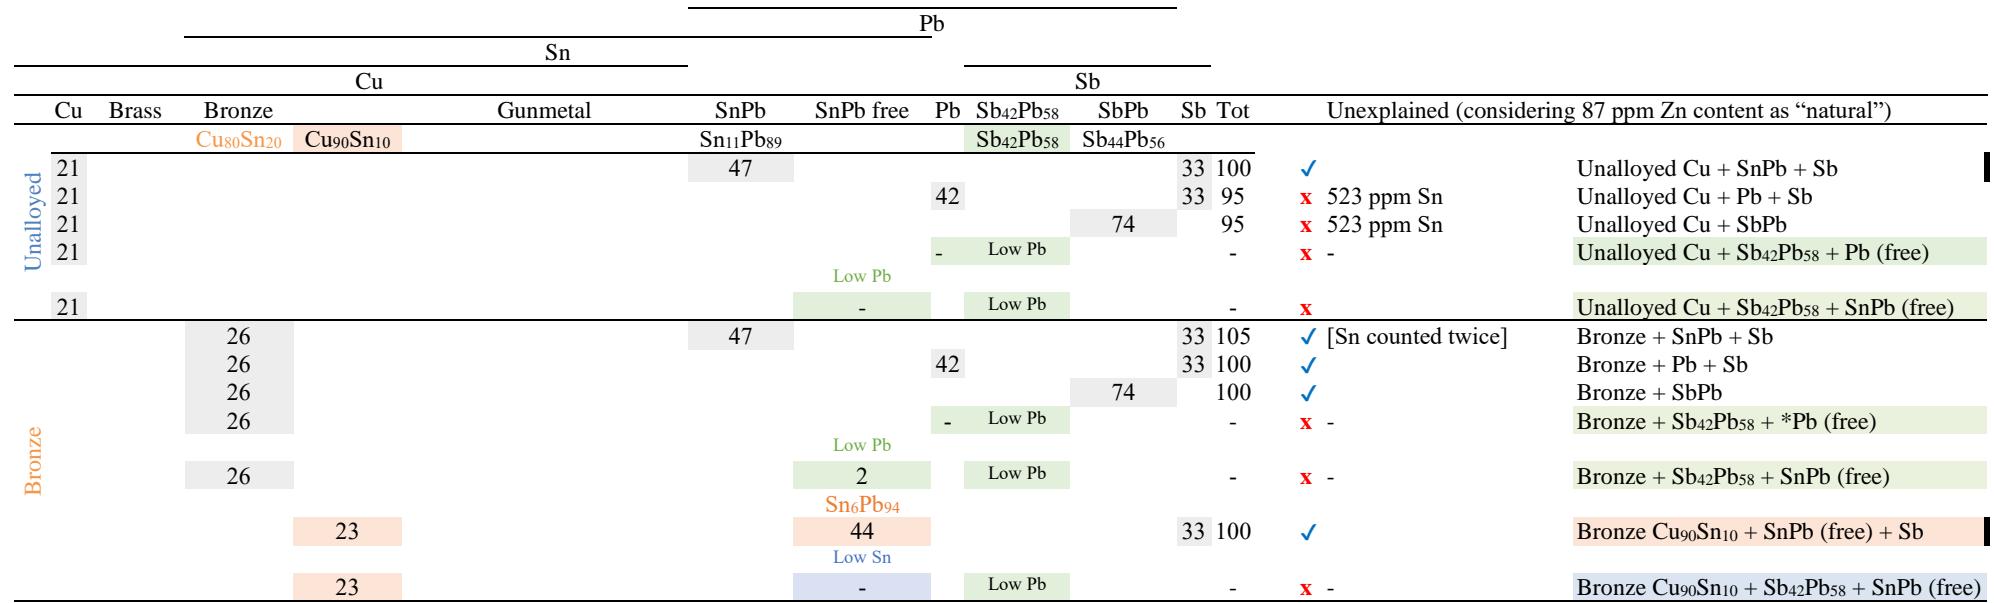

I constraint Sb₄₂Pb₅₈ → 8% less Pb (361 ppm missing)

II constraint Cu₉₀Sn₁₀ → 55% Sn free (289 ppm)

III constraint : gunmetal with Sn=Zn → 83% Sn free (436 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO325 – Correlation strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Green	1986	267	1203	718	9245	13419				
	Pb										
	Sn										
	Cu		Sb								
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈	Sb ₇ Pb ₉₃	Sb Tot	Unexplained (considering 267 ppm Zn content as “non natural”)
		Cu ₈₈ Zn ₁₂	Cu ₆₂ Sn ₃₈	Cu ₉₀ Sn ₁₀	Cu ₅₇ Sn ₃₅ Zn ₈	Cu ₇₉ Sn ₁₁ Zn ₁₁	Sn ₁₂ Pb ₈₈	Sb ₄₂ Pb ₅₈	Sb ₇ Pb ₉₃		
Unalloyed	15				78			5	98		x 267 ppm Zn Unalloyed Cu + SnPb + Sb
	15					69		5	89		x 1203 ppm Sn + 267 ppm Zn Unalloyed Cu + Pb + Sb
	15						74	89		x 1203 ppm Sn + 267 ppm Zn Unalloyed Cu + SbPb	
	15				62	13		89		x 1203 ppm Sn + 267 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)	
	15						70	13	98	x 267 ppm Zn Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Brass	17				78			5	100	✓	Brass + SnPb + Sb
	17					69		5	91	x 1203 ppm Sn Brass + Pb + Sb	
	17						74	91		x 1203 ppm Sn Brass + SbPb	
	17				62*	13		91		x 1203 ppm Sn Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	17				70	13		100		✓ Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Bronze	24				78			5	107	x 267 ppm Zn [Sn counted twice]	Bronze + SnPb + Sb
	24					69		5	98	x 267 ppm Zn Bronze + Pb + Sb	
	24						74	98		x 267 ppm Zn Bronze + SbPb	
	24				62*	13		98		x 267 ppm Zn Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)	
	24					70	13	107	x 267 ppm Zn [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)	
Gunmetal	16					76		5	98	x 267 ppm Zn Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb	
	16						Sn ₁₁ Pb ₈₉	98		x 267 ppm Zn Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)	
	26				78			5	109	✓ [Sn counted twice]	Gunmetal + SnPb + Sb
	26					69		5	100	✓	Gunmetal + Pb + Sb
	26						74	100	✓		Gunmetal + SbPb
	26				62*	13		100	✓		Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)
						Sn ₁₀ Pb ₉₀					Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)
					19	68	13	100	✓		

I constraint Sb₄₂Pb₅₈ → 89% Pb free (8254 ppm)

II constraint Cu₉₀Sn₁₀ → 82% Sn free (982 ppm)

III constraint : gunmetal with Sn=Zn → 78% Sn free (936 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO365 – Correlation strong SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total				
	Green	205	19	137	73	650	1084				
Pb											
Sn											
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb			
					Sn ₁₇ Pb ₈₃		Sb ₄₂ Pb ₅₈	SbPb	Sb Tot	Unexplained (considering 19 ppm Zn content as “natural”)	
							Sb ₄₂ Pb ₅₈	Sb ₁₀ Pb ₉₀			
Unallloyed	19					74			7 100	✓	Unalloyed Cu + SnPb + Sb
	19						61		7 87	✗ 137 ppm Sn	Unalloyed Cu + Pb + Sb
	19							68	87	✗ 137 ppm Sn	Unalloyed Cu + SbPb
	19					52	16		87	✗ 137 ppm Sn	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Bronze	19					Sn ₂₀ Pb ₈₀			100	✓	Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)
	32					74			7 113	✓ [Sn counted twice]	Bronze + SnPb + Sb
	32						61		7 100	✓	Bronze + Pb + Sb
	32							68	100	✓	Bronze + SbPb
	32					52*	16		100	✓	Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	32					Sn ₂₀ Pb ₈₀			113	✓ [Sn counted twice]	Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	21					Sn ₁₅ Pb ₈₅			7 100	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
	21					Sn ₁₇ Pb ₈₃			100	✓	Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 85% Pb free (550 ppm)

II constraint Cu₉₀Sn₁₀ → 83% Sn free (114 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO366 – Correlations Cu/Sb (1.27), strong SnPb, red group lead antimonates.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Green-blue	348	43	196	273	893	1753	
	Pb							
	Sn							
	Cu							
	Cu							
	Brass	Bronze						
	Cu ₆₄ Sn ₃₆	Cu ₉₀ Sn ₁₀						
Unalloyed	20			64		16	100	✓
	20				52	16	89	✗ 196 ppm Sn
	20					68	89	✗ 196 ppm Sn
	20			30	38		89	✗ 196 ppm Sn
	20							Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)
Bronze	32			64		16	109	✓ [Sn counted twice]
	32				52	16	98	✓
	32					68	98	✓
	32			30*	38		98	✓
	32							Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)
	23			Sn ₂₈ Pb ₇₂	42	109		Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)
	23			Sn ₁₅ Pb ₈₅	61			
				Sn ₂₃ Pb ₇₇	39	98	✓	Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb
								Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)

I constraint Sb₄₂Pb₅₈ → 58% Pb free (515 ppm)

II constraint Cu₉₀Sn₁₀ → 80% Sn free (158 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

CO530 – Correlation SnPb.

	Colour	Cu	Zn	Sn	Sb	Pb	Total	
	Green-red	7270	2442	5277	301	23672	38963	
Pb								
Sn								
	Cu			Sb				
	Cu	Brass	Bronze	Gunmetal	SnPb	SnPb free	Pb	Sb ₄₂ Pb ₅₈ SbPb Sb Tot
<chem>Cu75Zn25</chem> <chem>Cu58Sn42</chem> <chem>Cu90Sn10</chem> <chem>Cu48Sn35Zn16</chem> <chem>Cu60Sn20Zn20</chem> <chem>Sn18Pb82</chem> <chem>Sb42Pb58</chem> <chem>Sb1Pb99</chem>								
Unalloyed	19				74			1 94
	19					61		1 80
	19						62	80
	19				60	2		80
Brass	19							
	25				73			94
	25					61		1 100 ✓
	25						62	86
	25				60	2		86
	25				73			100 ✓
Bronze	32				74			1 107
	32					61		1 94
	32						62	94
	32				60	2		94
	32							
	32				73			107
Gunmetal	21							
	21				72			1 94
	38							
	38				74			1 114 ✓ [Sn counted twice]
	38					61		1 100 ✓
	38						62	100 ✓
	38				60	2		100 ✓
					Sn ₁₁ Pb ₈₉			
31								
67								
2								
100								
✓								
Unalloyed Cu + SnPb + Sb								
Unalloyed Cu + Pb + Sb								
Unalloyed Cu + SbPb								
Unalloyed Cu + Sb ₄₂ Pb ₅₈ + Pb (free)								
Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)								
Brass + SnPb + Sb								
Brass + Pb + Sb								
Brass + SbPb								
Brass + Sb ₄₂ Pb ₅₈ + *Pb (free)								
Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)								
Bronze + SnPb + Sb								
Bronze + Pb + Sb								
Bronze + SbPb								
Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)								
Bronze + Sb ₄₂ Pb ₅₈ + SnPb (free)								
Bronze + 2442 ppm Zn [Sn counted twice]								
Bronze + Pb + Sb								
Bronze + SbPb								
Bronze + Sb ₄₂ Pb ₅₈ + *Pb (free)								
Bronze + SnPb + Sb								
Bronze + SnPb (free) + Sb								
Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)								
Gunmetal + SnPb + Sb								
Gunmetal + Pb + Sb								
Gunmetal + SbPb								
Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)								
Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)								

I constraint Sb₄₂Pb₅₈ → 98% Pb free (23256 ppm)

II constraint Cu₉₀Sn₁₀ → 85% Sn free (4470 ppm)

III constraint : gunmetal with Sn=Zn → 54% Sn free (2835 ppm)

* If contained in the copper alloy → leaded brass, leaded bronze, leaded gunmetal.

SUMMARY

1) Samples with $Zn < 100$, showing Cu/Sb correlation.

	Unalloyed Cu + SnPb + Sb						Unalloyed Cu + Sb ₄₂ Pb ₅₈ + SnPb (free)						Bronze Cu ₉₀ Sn ₁₀ + SnPb (free) + Sb						Bronze Cu ₉₀ Sn ₁₀ + Sb ₄₂ Pb ₅₈ + SnPb (free)										
Sample ID	Cu	SnPb	Sb	Cu	Sb	SnPb	Cu	Sb ₄₂ Pb ₅₈	SnPb	Cu	Sb ₄₂ Pb ₅₈	SnPb	Cu ₉₀ Sn ₁₀	SnPb	Sb	Cu	Sb	SnPb	Cu ₉₀ Sn ₁₀	SnPb	Sb ₄₂ Pb ₅₈	Cu	Sb ₄₂ Pb ₅₈	SnPb					
CO366	20	64	Sn ₁₈ Pb ₈₂	16	1	1	3	20	38	42	Sn ₂₈ Pb ₇₂	1	2	2	23	61	Sn ₁₅ Pb ₈₅	16	1	1	3	23	39	Sn ₂₃ Pb ₇₇	38	1	2	2	SnPb
CO121A	19	62	Sn ₁₅ Pb ₈₅	19	1	1	3	19	45	36	Sn ₂₅ Pb ₇₅	1	2	2	22	60	Sn ₁₂ Pb ₈₈	19	1	1	3	22	34	Sn ₂₀ Pb ₈₀	45	1	2	2	SnPb
CO93	20	60	Sn ₁₃ Pb ₈₇	20	1	1	3	20	48	32	Sn ₂₅ Pb ₇₅	1	2	2	22	58	Sn ₁₀ Pb ₉₀	20	1	1	3	22	30	Sn ₂₀ Pb ₈₀	48	1	2	1	SnPb
CO95	21	58	Sn ₈ Pb ₉₂	20	1	1	3	21	49	30	Sn ₁₅ Pb ₈₅	1	2	1	23	56	Sn ₄ Pb ₉₆	20	1	1	2	23	28	Sn ₈ Pb ₉₂	49	1	2	1	SnPb
CO58A	21	57	Sn ₁₆ Pb ₈₄	21	1	1	3	21	49	29	[Sn ₃₁ Pb ₆₉]	1	2	1	23	55	Sn ₁₂ Pb ₈₈	21	1	1	2	23	26	Sn ₂₅ Pb ₇₅	49	1	2	1	SnPb
Com01	23	55	Sn ₁₀ Pb ₉₀	21	1	1	2	23	51	26	Sn ₂₁ Pb ₇₉	1	2	1	26	43	Sn ₅ Pb ₉₅	21	1	1	2	26	23	Sn ₁₂ Pb ₈₈	51	1	2	1	SnPb
CO121C	22	55	Sn ₈ Pb ₉₂	23	1	1	3	22	54	24	Sn ₁₉ Pb ₈₁	1	2	1	25	53	Sn ₄ Pb ₉₆	23	1	1	2	25	21	Sn ₁₀ Pb ₉₀	54	1	2	1	SnPb
CO100B	26	49	Sn ₇ Pb ₉₃	24	1	1	2	26	57	16	Sn ₂₀ Pb ₈₀	1	2	1	-	-	-	-	-	-	-	29	13	Sn ₃ Pb ₉₇	57	1	2	0	SnPb
CO184B	23	52	Sn ₆ Pb ₉₄	25	1	1	2	23	58	18	Sn ₁₆ Pb ₈₄	1	3	1	-	-	-	-	-	-	-	26	15	Sn ₂ Pb ₉₈	58	1	2	1	SnPb
Com80	20	54	Sn ₁₈ Pb ₈₂	25	1	1	3	20	60	19	Sn ₅₁ Pb ₄₉	1	3	1	22	52	Sn ₁₅ Pb ₈₅	25	1	1	2	22	17	Sn ₄₅ Pb ₅₅	60	1	3	1	SnPb
CO121D	24	48	Sn ₈ Pb ₉₂	27	1	1	2	24	64	11	[Sn ₃₆ Pb ₆₄]	1	3	0	27	45	Sn ₃ Pb ₉₇	27	1	1	2	27	8	Sn ₁₅ Pb ₈₅	64	1	2	0	SnPb

2) Samples with $Zn > 100$, showing Cu/Sb correlation.

	Brass + SnPb + Sb						Brass + Sb ₄₂ Pb ₅₈ + SnPb (free)						Gunmetal + SnPb + Sb						
	Brass	SnPb	Sb	Cu	Sb	SnPb	Brass	Sb ₄₂ Pb ₅₈	SnPb	Cu	Sb ₄₂ Pb ₅₈	SnPb	Gunmetal	SnPb	Sb G.	SnPb	Sb		
Com24	20 Cu ₉₅ Zn ₅ 59 Sn ₁₀ Pb ₉₀	20	1	1	3		20 Cu ₉₅ Zn ₅	49	31 Sn ₂₀ Pb ₈₀	1	2	2	-	-	-	-	-	SnPb	
Com61	25 Cu ₇₇ Zn ₂₃ 59 Sn ₈ Pb ₉₂	16	1	1	2		25 Cu ₇₇ Zn ₂₃	38	37 Sn ₁₃ Pb ₈₇	1	2	1	-	-	-	-	-	SnPb	
Com82	21 Cu ₉₂ Zn ₈ 53 Sn ₁₃ Pb ₈₇	27	1	1	3		21 Cu ₉₂ Zn ₈	64	16 Sn ₄₅ Pb ₅₅	1	3	1	-	-	-	-	-	SnPb	
Com25	15 Cu ₉₀ Zn ₁₀ 71 Sn ₁₁ Pb ₈₉	14	1	1	5		15 Cu ₉₀ Zn ₁₀	34	51 Sn ₁₆ Pb ₈₄	1	2	3	-	-	-	-	-	SnPb	
CO23A	22 Cu ₉₅ Zn ₅ 53 Sn ₈ Pb ₉₂	24	1	1	2		22 Cu ₉₅ Zn ₅	58	20 Sn ₂₂ Pb ₇₈	1	3	1	-	-	-	-	-	SnPb	
CO184C	26 Cu ₉₆ Zn ₄ 47 Sn ₁₁ Pb ₈₉	27	1	1	2		26 Cu ₉₆ Zn ₄	64	10 Sn ₅₁ Pb ₄₉	1	2	0	-	-	-	-	-	SnPb	
Com46	26 Cu ₉₃ Zn ₇ 49 Sn ₇ Pb ₉₃	24	1	1	2		26 Cu ₉₃ Zn ₇	58	16 Sn ₂₁ Pb ₇₉	1	2	1	-	-	-	-	-	SnPb	
Com97	24 Cu ₉₅ Zn ₅ 55 Sn ₁₂ Pb ₈₈	21	1	1	2		24 Cu ₉₅ Zn ₅	51	25 Sn ₂₇ Pb ₇₃	1	2	1	-	-	-	-	-	SnPb	
Com72	21 Cu ₇₅ Zn ₂₅ 64 Sn ₁₁ Pb ₈₉	15	1	1	3		21 Cu ₇₅ Zn ₂₅	36	43 Sn ₁₇ Pb ₈₃	1	2	2	-	-	-	-	-	SnPb	
Com36	26 Cu ₉₀ Zn ₁₀ 79 Sn ₂ Pb ₉₈	24	1	1	3		26 Cu ₉₀ Zn ₁₀	58	16 Sn ₇ Pb ₉₃	1	2	1	-	-	-	-	-	SnPb	
Com47	21 Cu ₉₂ Zn ₈ 60 Sn ₁₁ Pb ₈₉	19	1	1	3		21 Cu ₉₂ Zn ₈	46	34 Sn ₂₀ Pb ₈₀	1	2	2	27 Cu ₈₆ Sn ₄ Zn ₁₀	49 Sn ₂ Pb ₉₈	24	1	1	2	SnPb
CO184A	23 Cu ₉₂ Zn ₈ 55 Sn ₁₂ Pb ₈₈	23	1	1	2		23 Cu ₉₂ Zn ₈	54	23 Sn ₂₉ Pb ₇₁	1	2	1	-	-	-	-	-	SnPb	
Com50	9 Cu ₈₉ Zn ₁₁ 83 Sn ₁₃ Pb ₈₇	8	1	1	9		9 Cu ₈₉ Zn ₁₁	19	72 Sn ₁₅ Pb ₈₅	1	2	8	-	-	-	-	-	SnPb	
CO88	27 Cu ₉ Zn ₉ 48 Sn ₈ Pb ₉₂	24	1	1	2		27 Cu ₉ Zn ₉	58	15 Sn ₂₈ Pb ₇₂	1	2	1	-	-	-	-	-	SnPb	
Com73	25 Cu ₉ Zn ₉ 48 Sn ₈ Pb ₉₂	27	1	1	2		25 Cu ₉ Zn ₉	64	11 Sn ₃₅ Pb ₆₅	1	3	0	-	-	-	-	-	-	
Com78	21 Cu ₈₈ Zn ₁₂ 62 Sn ₅ Pb ₉₅	16	1	1	3		21 Cu ₈₈ Zn ₁₂	39	40 Sn ₈ Pb ₉₂	1	2	2	-	-	-	-	-	-	
Com11	21 Cu ₈₇ Zn ₁₃ 58 Sn ₇ Pb ₉₃	21	1	1	3		21 Cu ₈₇ Zn ₁₃	50	29 Sn ₁₄ Pb ₈₆	1	2	1	25 Cu ₇₇ Sn ₁₃ Zn ₁₀	62 Sn ₅ Pb ₉₅	16	1	1	2	SnPb
Com77	27 Cu ₉₂ Zn ₈ 46 Sn ₁₁ Pb ₈₉	26	1	1	2		27 Cu ₉₂ Zn ₈	63	10 Sn ₅₁ Pb ₄₉	1	2	0	-	-	-	-	-	-	
Com45	28 Cu ₈₉ Zn ₁₁ 48 Sn ₃ Pb ₉₇	23	1	1	2		28 Cu ₈₉ Zn ₁₁	56	16 Sn ₉ Pb ₉₁	1	2	1	-	-	-	-	-	SnPb	
Com10	24 Cu ₈₈ Zn ₁₂ 51 Sn ₉ Pb ₉₁	25	1	1	2		24 Cu ₈₈ Zn ₁₂	59	17 Sn ₂₅ Pb ₇₅	1	2	1	30 Cu ₈₄ Sn ₅ Zn ₁₁	48 Sn ₃ Pb ₉₇	23	1	1	2	SnPb
Com51	14 Cu ₈₄ Zn ₁₆ 74 Sn ₁₄ Pb ₈₆	12	1	1	5		14 Cu ₈₄ Zn ₁₆	29	57 Sn ₁₈ Pb ₈₂	1	2	4	-	-	-	-	-	-	
CO92	20 Cu ₉₅ Zn ₅ 59 Sn ₁₀ Pb ₉₀	20	1	1	3		20 Cu ₉₅ Zn ₅	49	31 Sn ₂₀ Pb ₈₀	1	2	2	-	-	-	-	-	SnPb	

	Gunmetal + Pb + Sb						Gunmetal + SbPb			Gunmetal + Sb ₄₂ Pb ₅₈ + *Pb (free)						Gunmetal calc. + Sb ₄₂ Pb ₅₈ + SnPb (free)													
	Gunmetal	Pb	Sb	Cu	Sb	SnPb	Gunmetal	SbPb	G	Sb	Gunmetal	Sb ₄₂ Pb ₅₈	Pb	G	Sb ₄₂ Pb ₅₈	Pb	Gunmetal	Sb ₄₂ Pb ₅₈	SnPb	G	Sb ₄₂ Pb ₅₈	SnPb							
Com24	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	SnPb					
Com61	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	21	Cu ₉₁ Sn ₅ Zn ₅	49	30	Sn ₁₇ Pb ₈₃	1	2	1	SnPb				
Com82	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-					
Com25	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	22	Cu ₈₆ Sn ₇ Zn ₇	64	14	Sn ₃₈ Pb ₆₂	1	3	1	SnPb				
CO23A	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	17	Cu ₈₁ Sn ₉ Zn ₉	34	49	Sn ₁₃ Pb ₈₇	1	2	3	SnPb				
CO184C	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	24	Cu ₉₀ Sn ₅ Zn ₅	58	19	Sn ₁₇ Pb ₈₃	1	2	1					
Com46	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	27	Cu ₉₂ Sn ₄ Zn ₄	64	9	Sn ₄₅ Pb ₅₅	1	2	0	SnPb				
Com97	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	28	Cu ₈₈ Sn ₆ Zn ₆	58	14	Sn ₁₁ Pb ₈₉	1	2	1					
Com72	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	25	Cu ₉₁ Sn ₄ Zn ₄	51	24	Sn ₂₃ Pb ₇₇	1	2	1	SnPb				
Com36	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	SnPb					
Com47	27	Cu ₈₆ Sn ₄ Zn ₁₀	48	24	1	1	2	27	Cu ₈₆ Sn ₄ Zn ₁₀	73	Sb ₃₃ Pb ₆₇	1	3	27	Cu ₈₆ Sn ₄ Zn ₁₀	58	15	1	2	1	-	-	-	-					
CO184A	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	22	Cu ₈₅ Sn ₇ Zn ₇	46	32	Sn ₁₆ Pb ₈₄	1	2	1	SnPb				
Com50	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	24	Cu ₈₆ Sn ₇ Zn ₇	54	23	Sn ₂₉ Pb ₇₁	1	2	1	SnPb				
CO88	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	10	Cu ₈₁ Sn ₁₀ Zn ₁₀	19	71	Sn ₁₄ Pb ₈₆	1	2	7	SnPb				
Com73	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	30	Cu ₈₃ Sn ₈ Zn ₈	58	12	Sn ₁₃ Pb ₈₇	1	2	0					
Com78	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	27	Cu ₈₄ Sn ₈ Zn ₈	64	9	Sn ₁₉ Pb ₈₁	1	2	0					
Com11	25	Cu ₇₇ Sn ₁₃ Zn ₁₀	59	16	1	1	2	25	Cu ₇₇ Sn ₁₃ Zn ₁₀	75	Sb ₂₂ Pb ₇₈	1	3	25	Cu ₇₇ Sn ₁₃ Zn ₁₀	39	36	1	2	1	24	Cu ₇₉ Sn ₁₁ Zn ₁₁	39	37	Sn ₂ Pb ₉₈	1	2	2	
Com77	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	24	Cu ₇₇ Sn ₁₂ Zn ₁₂	50	26	Sn ₄ Pb ₉₆	1	2	1					
Com45	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	29	Cu ₈₅ Sn ₈ Zn ₈	63	8	Sn ₃₇ Pb ₆₃	1	2	0	SnPb				
Com10	30	Cu ₈₄ Sn ₅ Zn ₁₁	47	23	1	1	2	30	Cu ₈₄ Sn ₅ Zn ₁₁	70	Sb ₃₃ Pb ₆₇	1	2	30	Cu ₈₄ Sn ₅ Zn ₁₁	56	15	1	2	1	-	-	-	-	-	-	-		
Com51	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	27	Cu ₇₉ Sn ₁₀ Zn ₁₀	59	15	Sn ₁₁ Pb ₈₉	1	2	1					
CO92	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	16	Cu ₇₃ Sn ₁₄ Zn ₁₄	29	55	Sn ₁₅ Pb ₈₅	1	2	3	SnPb				

3) Samples with Zn < 100, not showing Cu/Sb correlation.

